Melting and Transformation Temperatures of Mineral and Allied Substances

GEOLOGICAL SURVEY BULLETIN 1144-D

BAL-004632

Melting and Transformation Temperatures of Mineral and Allied Substances

By F. C. KRACEK

CONTRIBUTIONS TO GEOCHEMISTRY

GEOLOGICAL SURVEY BULLETIN 1144-D

UNITED STATES GOVERNMENT PRINTING OFFICE, WASHINGTON : 1963

UNITED STATES DEPARTMENT OF THE INTERIOR

STEWART L. UDALL, *Secretary*

GEOLOGICAL SURVEY

Thomas B. Nolan, *Director*

For sale by the Superintendent of Documents, U.S. Government Printing Office
Washington, D.C. 20402

CONTENTS

	Page
Abstract	1
General discussion	1
Acknowledgments	3
General references	3
Elements	4
Oxides	10
Oxide systems involving Al_2O_3	13
Oxide systems exclusive of Al_2O_3, B_2O_3, SiO_2	14
Silicate systems, binary	17
Silicate systems, ternary	21
Silicate systems, quaternary and higher	30
Silicate systems, miscellaneous	32
Carbonates	33
Systems, miscellaneous	36
References	63

ILLUSTRATIONS

Figure 1.	The system FeO	39
2.	The system SiO_2-Al_2O_3	40
3.	The system SiO_2-CaO	41
4.	The system SiO_2-FeO	42
5.	The system SiO_2-MgO	43
6.	The system CaO-Al_2O_3-SiO_2	44
7.	The system FeO-Al_2O_3-SiO_2	45
8.	The system K_2O-Al_2O_3-SiO_2	46
9.	The system MgO-SiO_2-Al_2O_3	47
10.	The system Na_2O-Al_2O_3-SiO_2	48
11.	The system CaO-FeO-SiO_2	49
12.	The system CaO-MgO-SiO_2	50
13.	The system MgO-FeO-SiO_2	51
14.	The join plane, SiO_2-FeO-$CaAl_2Si_2O_8$, (anorthite), of the system Al_2O_3-CaO-FeO-SiO_2	52
15.	The ternary section, $KAlSi_2O_6$ (leucite)-SiO_2-$CaAl_2Si_2O_8$ (anorthite), of the system Al_2O_3-CaO-K_2O-SiO_2	53
16.	The ternary section, $KAlSi_2O_6$ (leucite)-SiO_2-$CaMgSi_2O_6$ (diopside), of the system Al_2O_3-CaO-K_2O-MgO-SiO_2	54

ILLUSTRATIONS

Page

Figure 17. The ternary section, $NaAlSi_3O_8$ (soda feldspar)-$KAlSi_3O_8$ (potash feldspar)-$CaAl_2Si_2O_8$ (lime feldspar), of the system Al_2O_3-CaO-K_2O-Na_2O-SiO_2 ---------- 55

18. The join plane, Mg_2SiO_4 (forsterite)-$CaAl_2Si_2O_8$ (anorthite) SiO_2, of the system Al_2O_3-CaO-MgO-SiO_2 ---------- 56

19. The ternary section, $CaMgSi_2O_6$ (diopside)-Mg_2SiO_4 (forsterite) $CaAl_2Si_2O_8$ (anorthite), of the system Al_2O_3-CaO-MgO-SiO_2 ---------- 57

20. The ternary section, $NaAlSi_3O_8$ (albite)-$CaAl_2Si_2O_8$ (anorthite)-$CaMgSi_2O_6$ (diopside), of the system Al_2O_3-CaO-MgO-Na_2O-SiO_2---------- 58

21. The join plane, $NaAlSiO_4$ (nepheline, carnegieite) -FeO-SiO_2, of the system Al_2O_3-FeO-NaO-SiO_2----- 59

22. The section, $KAlSi_2O_6$ (leucite)-SiO_2-Fe_2SiO_4 (fayalite), of the system Al_2O_3-FeO-K_2O-SiO_2 ---------- 60

23. The ternary section, $KAlSi_2O_6$ (leucite)-SiO_2-Mg_2SiO_4 (forsterite), of the system Al_2O_3-K_2O-MgO-SiO_2----- 61

24. The ternary section, $KAlSi_2O_6$ (leucite)-SiO_2-Mg_2SiO_4 (forsterite), of the system Al_2O_3-K_2O-MgO-SiO_2----- 62

MELTING AND TRANSFORMATION TEMPERATURES OF MINERAL AND ALLIED SUBSTANCES

By F. C. Kracek

ABSTRACT

The temperatures of melting, boiling, and change of structural symmetry are compiled for compounds, eutectics, and solid solutions in oxide, silicate, and a few other systems. Primary emphasis is given to compounds of geologic interest; the compilation is not comprehensive of all phase equilibrium studies. Phase diagrams are given for 24 particularly complex systems that would be difficult to describe otherwise; for example, 11 diagrams of quaternary and higher order silicate systems show the temperature-composition stability fields for 56 compounds and for 6 two-liquid composition ranges.

For a given compound, the transition temperatures and the appropriate crystal systems are given for synthetic polymorphs as well as for those which occur naturally as minerals; polymorphs are identified by Greek letters or Roman numerals, and by names, according to usage. Temperatures are given, as available, for the following: decomposition, triple point, Curie point, specific heat anomaly, and solid solution, eutectic, peritectic, and incongruent melting points. Oxygen pressure and total pressure, including atmospheric, are stated if pertinent.

Data listed for 103 chemical elements are symbol, name, atomic number, atomic weight, melting point, boiling point, and any known transition temperature. Compilations of several groups of oxides are presented: 60 single oxides, 12 pairs involving Al_2O_3, and 70 pairs exclusive of Al_2O_3, B_2O_3, and SiO_2. (In a chemical system, each natural and synthetic compound is identified according to the ratio of oxides in mole percent.) Silicate systems compiled and presented are 25 binary systems, 61 ternary systems, and 5 miscellaneous ones; joins for 33 quaternary and higher systems are also listed, data for 11 being illustrated in diagrams, and the rest with references but without temperature data. The following are listed without temperature data; 38 single and binary carbonate systems, 72 miscellaneous, mostly ternary systems, including oxides, phosphates, sulfates, and fluorides, and the pertinent references.

GENERAL DISCUSSION

Scope of the tables.—These tables list the melting (congruent and incongruent) temperatures, boiling temperatures, and transition temperatures for the more important substances of interest to the geologist, the geochemist, and the petrologist. Eutectic and related data are given when the substance under discussion has been studied as part of a binary or higher system. The aim in compiling the tables has been to describe the known thermal reactions of the compounds and the systems briefly, but in enough detail to be of use to an investigator in the field where extensive reference books are not usually available.

Arrangement.—The entries are arranged alphabetically by chemical symbol (elements) or formula (compounds). Compounds composed of two or more oxides (except carbonates, sulfates, and other oxygen salts) are entered in the increasing alphabetical order of the constituent oxides.

Mineralogic names.—Minerals follow the nomenclature employed in Dana, E. S., and Ford, W. E., 1922, A textbook of mineralogy: New York, John Wiley & Sons, 720 p.

Description of systems.—The compositions of solution phases (liquid or solid) expressed in terms of percentage of the end components, molecular or by weight. For the molecular percentage the mole is taken as the accepted gram-formula weight. Thus, for a binary system the composition of a melt at a eutectic or other significant point may be stated as 18 percent of CaO or 82 percent of TiO_2, as shown below. Compositions of compounds in a system, on the other hand, are given in terms of the mole ratio of the components, as is usual in chemical practice:

CaO-TiO_2:-$CaTiO_3$, (1:1), Perovskite, melting point 1970°; eutectic with TiO_2, 18 percent CaO, 1460°.

This signifies that in the system composed of CaO and TiO_2 as components, there is a 1:1 compound, $CaTiO_3 = CaO \cdot TiO_2$, whose mineral name is Perovskite; this mineral melts at 1970°C, and it is a constituent of a eutectic with TiO_2, the eutectic melting at 1460°C. The composition of the eutectic melt is 18 percent CaO, 82 percent TiO_2. Only one of these percentage numbers is required to specify composition in a binary system, as it will be evident that in a system of n components, only $(n-1)$ percentage values suffice to specify the composition adequately.

Unless otherwise stated, compositions are given in weight percent. Mole percentages are indicated by mole percent; thus, for the composition in the example given above, 18 percent CaO is equivalent to 23.824 mole percent CaO.

Temperature scale.—The practical scale of temperature, originally planned to be a thermodynamic scale (International Critical Tables, v. 1, p. 52) was placed on a working basis by the high temperature gas thermometer work of Day and Sosman (1911, 1922) at the Geophysical Laboratory. Since 1914 the Geophysical Laboratory has used this scale adapted for practical use with thermocouples by L. H. Adams (1919, 1926). The Geophysical Laboratory, for the purposes of consistency, is still using this scale in the temperature measurements it reports. In 1927 the Seventh General Conference in Weights and Measures adopted a scale of temperatures which became known as the International Temperature Scale of 1927. The International Temperature Scale of 1927 was soon recognized to be faulty in the upper reaches of temperature, and a new scale, the International Temperature Scale of 1948, was adopted by the Conference in Weights and Measures in 1948, (H. F. Stimson, 1949). The International Temperature Scale of 1948 is discussed in relation to the International Temperature Scale of 1927, and the Geophysical Laboratory Scale by Sosman (1952); see also R. J. Corruccini (1949).

Sosman (1952) states:

> On the basis of the 1948 scale, the corrections made by Sosman and Anderson in 1933 at 1550°C and lower, none of which exceed +5°C, are reduced to about two-thirds their former (1927 scale) magnitude, and the original Geophysical [Laboratory] temperatures can usually be left without error beyond the experimental uncertainty. Temperatures beyond 1550°, however, will still have to be proportionately increased, to bring them into line with the International 1948 Scale. The melting point of pure silica as cristobalite, for example, originally 1713°, becomes 1723°.

Because of the possibility of further revision of the scale, and to avoid confusion, the temperatures given in this compilation are the unamended, original values, except where specifically denoted by the legend (International Temperature Scale). In particular, the melting-point determinations on silicates done at the Geophysical Laboratory are all referred to the Day and Sosman gas thermometer scale upon which the Adams (1919) standard thermocouple tables (International Critical Tables, v. 1, p. 57) are based.

For the work published from the School of Mineral Industries, Pennsylvania State University, and from the National Bureau of Standards, on the other hand, the data are given in terms of the International Temperature Scale of 1948. Such data are reproduced here without specifically calling attention to the scale used.

Estimated temperature values, as for elements, for which actual measurements have not been made, are enclosed in parentheses.

Precision (as distinct from the absolute accuracy) of the determinations of the transformation, where known, is indicated thus, ±3. Where no bracket is given, the last significant figure given is uncertain.

References to the literature.—Previous investigations are referred to in detail for the more complex systems. They are not given in general for single substances, particularly when the data are available in one or more handbooks in common use; this is done to avoid an unnecessarily long list of citations.

Acknowledgments

I wish to acknowledge the courtesy of the editors of the following journals for permission to reproduce the following figures: the American Journal of Science, for figures 1-7, 10, 13, 16, and 18-21; the Journal of Geology and University of Chicago Press, for figures 9, 17, and 24; the Journal of the American Ceramic Society, for figures 2, 3, 8, 12, 14, and 23; the American Mineralogist, for figure 22; and the Commission Géologie de Finlande, for figure 15. Thanks are also due Dr. Sydney P. Clark, Jr., for permission to reproduce figure 11.

General References

Simple compounds:

Landolt, Bornstein, Roth, and Scheel, 1923, Physikalisch-Chemische Tabellen: Berlin, Julius Springer, 5th ed. and supp., 2 v.

Tables annuelles de constantes et donnees numeriques de chimie, de physique et de technologie: Paris, Gauther-Villars, Chicago, Ill., Univ. Chicago Press, yearly volumes from 1910.

Mellor, J. W., 1922-1937, A comprehensive treatise on inorganic and theoretical chemistry: London, New York, Longmans, Green & Co., 16 v.

Gmelins Handbuch der anorganischen Chemie: 8th ed., Leipzig-Berlin, Verlag Chemie G. m. b. H., 1924-.

Abstract Journals.

Compounds and systems with silica, alumina, and other refractory oxides:

Levin, E. M., McMurdie, H. F., and Hall, F. P., 1956, Phase diagrams for ceramists: Columbus, Ohio, American Ceramic Society, 286 p.

International critical tables: New York, McGraw-Hill Book Co., 1928, v. 4, p. 83-97.

Eitel, Wilhelm, 1954, Physical chemistry of the silicates: Chicago, Ill., Univ. Chicago Press, 1592 p.

Bowen, N. L., 1928, The evolution of the igneous rocks: Princeton, N. J., Princeton Univ. Press, 332 p.; also reprinted by Dover Publications, Inc., New York.

ELEMENTS

Symbol	Name	Atomic No.	1956 Atomic weight	Melting point (degrees C)	Boiling point (degrees C)	Transition point (degrees C)
Ar	Argon	18	39.944	-189.31	-185.87	----------
Ac	Actinium	89	227	(1200)[a]	(3300)	----------
Ag	Silver	47	107.880	960.8	2193	----------
Al	Aluminum	13	26.98	660.1	2450	----------
Am	Americium	95	(243)	--------	--------	----------
As	Arsenic	33	74.91	814[b]	615[c]	----------
At	Astatine	85	(211)	(300)	(380)	----------
Au	Gold	79	197.0	1063	2707	----------
B	Boron	5	10.82	2027	3927	----------
Ba	Barium	56	137.36	710	1638	375
Be	Beryllium	4	9.013	1283	2477	----------
Bi	Bismuth	83	209.00	271.3	1559	----------
Bk	Berkelium	97	(245)	--------	--------	----------
Br	Bromine	35	79.916	-7.2	58.3	----------
C	Carbon	6	12.011	--------	4347[c]	----------
Ca	Calcium	20	40.08	850	1482	450
Cd	Cadmium	48	112.41	320.9	765	----------
Ce	Cerium	58	140.13	804	2927	-133, 393, 440

Cf	Californium	98	(248)	-------	-------	-------
Cl	Chlorine	17	35.457	-101.0	-34.06	-------
Cm	Curium	96	(245)	-------	-------	-------
Co	Cobalt	27	58.94	1495	2877	447, 850, 1150[d]
Cr	Chromium	24	52.01	1903	2642	1840
Cs	Cesium	55	132.91	28.5	685	-------
Cu	Copper	29	63.54	1083	2582	-------
Dy	Dysprosium	66	162.51	1500	2327	-------
E	Einsteinium	99	(255)	-------	-------	-------
Er	Erbium	68	167.27	1527	(2630)	-------
Eu	Europium	63	152.0	(830)	(1430)	-------
F	Fluorine	9	19.00	-219.62	-188.14	-227.60
Fe	Iron	26	55.85	1539	2887	760[d], 910, 1400
Fm	Fermium	100	(252)	-------	-------	-------
Fr	Francium	87	(223)	(27)	(680)	-------
Ga	Gallium	31	69.72	29.78	2237	2.6[e]
Gd	Gadolinium	64	157.26	-------	-------	-------
Ge	Germanium	32	72.60	937.3	(2700)	-------
H	Hydrogen	1	1.0080	-259.31[f]	-252.89	-------
D	Deuterium	1	2.00147	-254.52	-249.56	-------
He	Helium	2	4.003	-272.2[g]	-268.94	-------
				-270.97[h]		

690-216 O - 63 - 2

ELEMENTS

Symbol	Name	Atomic No.	1956 Atomic weight	Melting point (degrees C)	Boiling point (degrees C)	Transition point (degrees C)
Hf	Hafnium	72	178.58	1977	(5200)	1500
Hg	Mercury	80	200.61	-38.87	356.58	----------
Ho	Holmium	67	164.94	(1500)	(2300)	----------
I	Iodine	53	126.91	113.7	184.35	----------
In	Indium	49	114.82	156.17	2047	----------
Ir	Iridium	77	192.2	2443	4130	----------
K	Potassium	19	39.100	63.4	766	----------
Kr	Krypton	36	83.8	-157.21	-153.23	----------
La	Lanthanum	57	138.92	920	3367	-163, 548, 709
Li	Lithium	3	6.940	180.55	1331	-196
Lu	Lutetium	71	174.99	(1730)	(1930)	----------
Md	Mendelevium	101	(256)	--------	--------	----------
Mg	Magnesium	12	24.32	650	1120	----------
Mn	Manganese	25	54.94	1244	2087	727, 1101, 1137
Mo	Molybdenum	42	95.95	2610	(4800)	----------
N	Nitrogen	7	14.008	-209.97	-195.82	-237.53
Na	Sodium	11	22.991	97.82	889	----------
Nb	Niobium	41	92.91	2497	4900	----------

Nd	Neodymium	60	144.27	1024	(3090)	-164, 508, 714
Ne	Neon	10	20.183	-248.59	-246.08	----------
Ni	Nickel	28	58.71	1453	2840	350-400[d]
Np	Neptunium	93	(237)	640	--------	----------
O	Oxygen	8	16.000	-218.76[f] -218.92[f]	-182.96	-229.37, -249.26
Os	Osmium	76	190.2	2700	(4230)	----------
P	Phosphorus,	15	30.975	--------	--------	-77.15[j]
	yellow, cubic	---	--------	44.1	280	-2.3[k]
	red, triclinic	---	--------	590[i]	431[c]	----------
	violet	---	--------	593[i]	--------	----------
Pa	Protoactinium	91	231	(1200)	(4000)	----------
Pb	Lead	82	207.21	327.3	1750	----------
Pd	Palladium	46	106.7	1549.5[l] 1552[m]	3130	----------
Pm	Promethium	61	(145)	(1000)	(2700)	----------
Po	Polonium	84	210	254	962	97
Pr	Praseodymium	59	140.92	935	3017	798
Pt	Platinum	78	195.09	1755[l] 1769[m]	3800	----------
Pu	Plutonium	94	(242)	1300	--------	----------
Ra	Radium	88	226.05	700	(1500)	----------
Rb	Rubidium	37	85.48	38.8	700	-30

ELEMENTS

Symbol	Name	Atomic No.	1956 Atomic weight	Melting point (degrees C)	Boiling point (degrees C)	Transition point (degrees C)
Re	Rhenium	75	186.22	3147	(5600)	----------
Rh	Rhodium	45	102.91	1960	3960	----------
Rn	Radon	86	222	-71	-61.8	----------
Ru	Ruthenium	44	101.1	2500	4110	1035, 1200, 1500
S	Sulphur	16	32.066	119.25[n]	444.60	95.5[o]
Sb	Antimony	51	121.76	630.5	1440	95, 413
Sc	Scandium	21	44.96	1400	3900	----------
Se	Selenium					
	gray trigonal	34	78.96	217.4	685	150[p]
Si	Silicon	14	28.09	1410	2680	----------
Sm	Samarium	62	150.35	1052	(1590)	917
Sn	Tin	50	118.70	231.9	2690	18[q]
Sr	Strontium	38	87.63	770	1384	----------
Ta	Tantalum	73	180.95	2997	5400	----------
Tb	Terbium	65	158.93	(1400)	(2500)	----------
Tc	Technetium	43	(99)	(2100)	(4600)	----------
Te	Tellurium	52	127.61	449.8	1097	348?
Th	Thorium	90	232.05	1695	4200	225
Ti	Titanium	22	47.90	1812	3280	884

Tl	Thallium	81	204.39	303.6	1457	232, 153[r]
Tm	Thulium	69	168.94	(1630)	(2100)	
U	Uranium	92	238.07	1133	(3900)	662, 776
V	Vanadium	53	50.95	1917	3380	
W	Tungsten	74	183.86	3380	(5500)	650
Xe	Xenon	54	131.30	-111.8	-108.11	
Y	Yttrium	39	88.92	(1490)	(4400)	
Yb	Ytterbium	70	173.04	824	(1530)	798
Zn	Zinc	30	65.38	419.5	908	
Zr	Zirconium	40	91.22	1852	(4380)	862

[a] Figures in parentheses are estimates.

[b] 36 atmospheres.

[c] Sublimation point.

[d] Curie point.

[e] 11,600 atmosphere.

[f] Triple point.

[g] 25.3 atmosphere.

[h] 2 liquids.

[i] 43 atmosphere.

[j] 1 atmosphere.

[k] 5,800 atmosphere.

[l] Day and Sosman scale.

[m] International, 1948.

[n] Monoclinic.

[o] Rhombic-monoclinic, 1 atmosphere.

[p] Red-gray.

[q] Gray-white

[r] 37,800 atmosphere.

OXIDES

Ag_2O Dissociation (1 atm) 191°C.

Al_2O_3 (a) High-temperature phases: α, Corundum: trigonal melting point (pure) 2040°C. β aluminas: hexagonal isomorphous compounds from alkali or alkaline earth melts, formed in the ratio 1:11 for Na_2O, K_2O, MgO to Al_2O_3, and 1:6 for CaO, SrO, BaO to Al_2O_3. ζ alumina: $LiAl_5O_8$, cubic, from melts containing Li_2O.

(b) Transition aluminas: produced in calcination of aluminum compounds, or in oxidation of aluminum metal. Varieties ρ, χ and κ result on dehydration of α trihydrate; η and θ from β trihydrate, γ and δ from α monohydrate, but all have been made by suitable dehydration and rehydration treatment of a single sample of fine-grained α trihydrate. All varieties convert to α at or below about 1100°C. δ may result from combustion of aluminum metal. η is obtained in oxidation of aluminum metal at its melting point. κ was obtained in thermal decomposition of hydrated aluminum chloride. (Russell and others, 1956.)

As_2O_3 Arsenolite, cubic (labile), melting point 275°C; sublimation point 193°C.

Claudetite, monoclinic, melting point 313°C.

As_2O_5 Vitreous only, decomposes (1 atm) 315°C.

B_2O_3 Trigonal melting point 450°C.

BaO Melting point 1925°C.

BeO Bromellite melting point 2530°C.

Bi_2O_3 Bismite, I rhombic melting point 820°C; II cubic, glows 680°C transition point II to I, 704°C; boiling point 1890°C.

CO_2 Sublimation point (1 atm) −78° to 48°C; triple point (5.112 atm) −56.60°C.

CaO Melting point 2570°C; boiling point 2850°C.

CeO_2 Ceria, melting point 2600°C; partly decomposes 2500°C.

Ce_2O_3 Melting point 1692°C.

CoO Melting point 1935°C.

Co_3O_4 Dissociates (1 atm) at 970°C to CoO and O_2.

Co_2O_3 Dissociates 895°C.

Cr_2O_3 Melting point 1990°C; transition point 33°C.

CrO_2 Loses 0, 300°C.

CrO_3 Melting point 196°C, liquid decomposes to Cr_2O_3 and O_2.

CuO Tenorite, melting point more than 1240°C (75 atm O_2), dissociates 1104°C (1 atm) to Cu_2O and O_2; eutectic of CuO and Cu_2O 1080°C (0.51 atm O_2) in a melt of 86 percent Cu, 14 percent O_2; C_p anomalies −40°C, −60°C. These depend on thermal history. (Smyth and Roberts, 1920.)

Cu_2O Cuprite, melting point 1235°C; transition point natural translucent to opaque, 56°C.

FeO Natural "Jozite" is ferromagnetic.
Artificial "Wüstite" is Fe deficient; lower limit stability 570°C decomposes to Fe and Fe_3O_4 below 570°C: ferromagnetic.
Artificial, eutectic with Fe solid solution 1371°C; artificial O-rich Wüstite incongruent melting point 1424°C to Fe_3O_4 and liquid (24 percent O); Wüstite forms 2 liquid layers with excess Fe solid solution (0.16 to 22.60 percent O); C_p anomaly in metastable −88°C. (Darken and Gurry, 1945, 1946.) See figure 1.

Fe_3O_4 Magnetite, artificial, forms limited solid solution both with excess Fe and excess O; O rich oxidizes in air (1/5 atm O_2) below 1388°C; melting point 1597°C; magnetic transition point natural 580°C, artificial 510° to 680°C; C_p anomaly −159°C; magnetic anomaly −160°C. (Darken and Gurry, 1946.)

Fe_2O_3 Hematite, dissociates in air (1/5 atm O_2) 1388°C; (1 atm O_2) 1457°C, to magnetite and O_2; orthobaric melting point is unknown, transition point 1030. (Greig and others, 1935; Darken and Gurry, 1946.)
α, paramagnetic, isomorphous with corundum.
γ, ferromagnetic, isomorphous with magnetite; produced on oxidation of magnetite, also on dehydration of γ FeOOH (Lepidocrocite).

Ga_2O_3 Melting point 1740°C; dimorphous: α, isomorphous with corundum; β, monoclinic, transition point 650°C.

GeO_2 Soluble, quartz type, melting point 1116°C±4°C.
Insoluble, rutile type, labile, melting point 1086°C±5°C; transition point 1033°C±10°C; volatilizes above 1250°C.

H_2O Water, melting point 0.000°C, boiling point 100.000°C (thermometric fixed points at 1 atm); orthobaric triple point 0.01°C (International 1948 Scale).
Triple points of high pressure modifications:
(1) I - III - L, 2047 atmosphere, −22.0°C
(2) I - II - III, 2100 atmosphere, −34.7°C
(3) II - III - V, 3397 atmosphere, −24–3°C
(4) III - V - L, 3416 atmosphere, −17°C
(5) V - VI - L, 6175 atmosphere, 0.16°C
(6) VI - VII - L, 21678 atmosphere, 81.6°C
(Bridgman, 1937).
D_2O, heavy water melting point 3.82°C, boiling point 101.42°C (1 atm).

HfO_2 Hafnia, melting point 2810°C.

HgO Montroydite, dissociates in air (1/5 atm O_2) 426°C, (1 atm O_2) 496°C.

La_2O_3 Melting point 2315°C±20°C; boiling point about 4200°C.

MgO Periclase, melting point 2800°C.

MnO Manganosite, melting point 1850°C; 2 liquids with Mn; oxides to Mn_3O_4 in air below 1200°C; C_p anomaly −155°C.

Mn_3O_4 Hausmannite, stable in air below 1200°C; oxidizes in air to Mn_2O_3 below 877°C; melting point 1567°C; transition point, tetragonal to cubic, 1160°C. (Van Hook and Keith, 1958.)

Mn_2O_3 Braunite, dissociates in air (1/5 atm O_2) 877°C, (1 atm) 1090°C to Mn_2O_4 plus O_2; transition point 600°C.

MnO_2 Polianite, dissociates in air 530°C±50°C, in 1 atm O_2 565°C±50°C; C_p anomaly −181°C.
Pyrolusite is partially hydrated, has structure like Polianite.

MoO_3 Molybdite, melting point 795°C with sublimation.

NiO Bunsenite, melting point 1990°C.

Ni_3O_4 Dissociates to NiO and O_2 at less than 600°C.

Ni_2O_3 Unstable in anhydrous condition.

P_2O_5 (Tabular) melting point more than 570°C; (acicular) melting point 569°C; tends to remain glassy; sublimation point about 360°C; sublimation to glassy state, 400° to 500°C.

PbO Massicot, melting point 886°C; transition point tetragonal to rhombic 488°C; volatilizes below 750°C.

Pb_3O_4 Minium, artificial dissociates (1 atm O_2) 601°C to $PbO+O_2$.

PbO_2 Plattnerite, artificial dissociation (1 atm O_2) 344°C to $Pb_3O_4+O_2$ when precipitated; 313°C when electrolytic.

SO_2 Melting point −75.46°C, boiling point −10.0°C.

SO_3 Melting point (prismatic icelike) 16° to 8°C; (low asbestoslike) 32.5°C; (high asbestoslike, at 2.29 atm) 62.2°C; sublimation point 44.8°C.

Sb_2O_3 Valentinite, rhombic, melting point 656°C, boiling point 1550°C.
Senarmontite, cubic melting point 656°C.
Transition point rhombic to cubic 557°C.
Oxidizes in air to SbO_2 below 930°C.

SbO_2 Cervantite, melting point unknown; dissociates in free air to Sb_2O_3 liquid $+O_2$ at 930°C.

Sb_2O_5 Dissociates in air at 380°C to SbO_2+O_2.

SiO_2 Quartz melting point (metastable) about 1470°C; transition point low trigonal to high hexagonal 573°C±3°C; transition point Quartz-Tridymite 867°C±3°C;
Tridymite, melting point (metastable) about 1670°C; transition point rhombic to low hexagonal 105°C, low hexagonal to high hexagonal 163°C; transition point Tridymite to Cristobalite 1470°C±10°C;
Cristobalite, melting point 1713°C±10°C (Day and Sosman scale), 1723°C±10°C (International 1948 scale); transition point rhombic to cubic 200° to 270°C depending on thermal history. (Fenner, 1913; Greig, 1927a.)

SnO_2 Cassiterite, melting point 1127°C with decomposition; transition point 410°C.

SrO Melting point 2430°C.

TeO_2 Tellurite, melting point 732.6°C, sublimation point above 450°C; droplets solidify vitreous.

ThO_2 Melting point 3050°C.

TiO_2 Rutile, melting point 1825°C.
Anatase, artificial, by dehydrating TiO_2 gel at about 900°C transition to Rutile in presence of flux at or above 400°C without flux 915°C; α to β Anatase transition point 642°C;
Brookite, transition in presence of flux to Rutile below 900°C;
Decomposes to $Ti_2O_3+O_2$ above 1600°C.

UO_2 Melting point 2176°C.

V_2O_5 Melting point 690°C; liquid decomposes 1750°C.

WO_3 Tungstite, melting point 1473°C.

ZnO Zincite, artificial melting point 1975°C; sublimation point 1800°C.

ZrO_2 Baddeleyite, melting point 2690°C; transition point 625°C, 1000°C, 1900°C; boiling point about 4300°C.

OXIDE SYSTEMS INVOLVING Al_2O_3

$BaO-Al_2O_3$:-$3BaO \cdot Al_2O_3$, (3:1), eutectic with BaO, 1660°C; melting point 1750°C; eutectic with (1:1), 1710°C.

-$BaO \cdot Al_2O_3$, (1:1), Barium spinel, melting point 1830°C; eutectic with (1:6), 1790°C.

-$BaO \cdot 6Al_2O_3$ (1:6), melting point 1900°C; eutectic with Al_2O_3, 1890°C. (Toropov and Galakhov, 1952.)

$BeO-Al_2O_3$:-$BeO \cdot Al_2O_3$, (1:1), Chrysoberyl, eutectic with BeO, 1835°C; melting point 1870°C; eutectic with (1:3), 1850°C.

-$BeO \cdot 3Al_2O_3$, (1:3), melting point 1910°C; eutectic with Al_2O_3, 1890°C. (Lang and others, 1952; Foster and Royal, 1949.)

$CaO-Al_2O_3$:-$3CaO \cdot Al_2O_3$, (3:1), incongruent melting to CaO and liquid, 41 percent Al_2O_3, 1535°C; eutectic with (5:3), 50 percent Al_2O_3, 1395°C.

-$5CaO \cdot 3Al_2O_3$, (5:3), melting point 1455°C; eutectic with (1:1), 53 percent Al_2O_3, 1400°C.

-$CaO \cdot Al_2O_3$, (1:1), melting point 1600°C; eutectic with (3:5), 67 percent Al_2O_3, 1590°C.

-$3CaO \cdot 5Al_2O_3$, (3:5), composition is in question, may be $CaO \cdot 2Al_2O_3$, melting point 1720°C; eutectic with Al_2O_3, 76 percent Al_2O_3, 1700°C. (Rankin and Wright, 1915; Goldsmith, 1948.)

$FeO-Al_2O_3$:-$3FeO \cdot Al_2O_3$, (3:1), decomposes below liquidus to (1:1) and FeO, 1230°C.

-$FeO \cdot Al_2O_3$, (1:1), Hercynite, incongruent melting to Al_2O_3 and liquid, 12 percent Al_2O_3, 1440°C; eutectic with FeO, 7 percent Al_2O_3, 1305°C. (McIntosh and others, 1937.)

$FeO-Fe_2O_3-Al_2O_3$:-(Muan and Gee, 1956.)

$Fe_2O_3-Al_2O_3$:-$Fe_2O_3 \cdot Al_2O_3$, (1:1), is unstable below 1318°C relative to the phase assemblage: Hematite solid solution plus Corundum solid solution. (Muan, 1958a.)

$Ga_2O_3-Al_2O_3$:-$Ga_2O_3 \cdot Al_2O_3$, (1:1), decomposes below the liquidus to Ga_2O_3 solid solution, 825°C; α Al_2O_3 solid solution plus β Ga_2O_3 solid solution coexist in solvus, 800° to 2000°C; limits of homogeneity: α Al_2O_3 solid solution, 0 to 28 mole percent Ga_2O_3; β Ga_2O_3 solid solution, 34 to 100 mole percent Ga_2O_3 at 800°C; 31 to 100 mole percent Ga_2O_3 at 2000°C. α solid solution and β solid solution liquidus descends with a slope discontinuity in region of the solvus from melting point Al_2O_3, 2035°C, to melting point Ga_2O_3, 1740°C. (Hill and others, 1952.)

$MgO-Al_2O_3$:-$MgO \cdot Al_2O_3$, (1:1), Spinel, melting point 2135°C; eutectic with MgO, 45 percent MgO, 2030°C; eutectic with Al_2O_3, 5 percent MgO, 1860°C. Spinel solid solution coexists with Al_2O_3 and with liquid, solid solution limit 15 percent MgO, 1860°C. (Rankin and Merwin, 1916; Roy, R., and others, 1953.)

690-216 O - 63 - 3

$MnO-Al_2O_3$:-$MnO \cdot Al_2O_3$, (1:1), incongruent melting to Al_2O_3 and liquid, 71 percent MnO, 1560°C; eutectic with MnO, 76 percent MnO, 1520°C. (Hay and others, 1934.)

$PbO-Al_2O_3$:-$PbO \cdot Al_2O_3$, (1:1), incongruent melting to Al_2O_3 and liquid, 91 percent PbO, 985°C; eutectic with 94 percent PbO, 865°C. (Geller and Bunting, 1943.)

$TiO_2-Al_2O_3$:-$TiO_2 \cdot Al_2O_3$, (1:1), melting point 1860°C; eutectic with TiO_2, 19.5 percent Al_2O_3, 1705°C; eutectic with Al_2O_3, 60 percent Al_2O_3, 1840°C; transition 1820°C. (Bunting, 1933; Lang and others, 1952; Wartenberg and Reusch, 1932.)

$UO_2-Al_2O_3$:-No compounds; eutectic, 75 percent Al_2O_3, 1930°C; UO_2+2 immiscible liquids, 51 to 75 percent Al_2O_3, 1930°C. (Lambertson and Mueller, 1953a.)

OXIDE SYSTEMS EXCLUSIVE OF Al_2O_3, B_2O_3, SiO_2.

$BaO-MgO$ No compounds; eutectic 41 percent MgO, 1500°C.

$BaO-TiO_2$ $BaO \cdot TiO_2$, (1:1), melting point 1612°C; transition point 112.7°C; (Rase and Roy, 1955a.)

$BaO-ZrO_2$ $BaO \cdot ZrO_2$, (1:1), melting point 2650°C; eutectic with BaO, 10 mole percent ZrO_2, 1440°C; eutectic with ZrO_2, 90 percent ZrO_2, 2050°C.

$BeO-CaO$ Eutectic, 44 percent CaO, 1470°C.

$BeO-CeO_2$ Minimum 1960°C, 25 percent CeO_2.

$BeO-CoO$ Minimum 1750°C, 65 percent BeO.

$BeO-Cr_2O_3$ Minimum 2210°C, 30 percent BeO.

$BeO-Cu_2O$ Eutectic 1200°C, about 1 percent BeO.

$BeO-Fe_3O_4$ Minimum 1580°C, 15 percent BeO.

$BeO-La_2O_3$ Minimum 1400°C, 25 percent BeO.

$BeO-MgO$ Minimum 1950°C, 48 percent BeO.

$BeO-Mn_3O_4$ Minimum 1540°C, 16 percent BeO.

$BeO-NiO$ Eutectic 1900°C, 12 percent BeO.

$BeO-ThO_2$ Minimum 2210°C, 20 percent BeO. All systems above with BeO by (Wartenberg, Reusch, and others, 1937).

$BeO-TiO_2$ Minimum 1670°C (eutectic?), 15 percent BeO, (Lang and others, 1952.)

$BeO-ZrO_2$ Eutectic 2200°C, 75 percent BeO. (Wartenberg, Reusch, and others, 1937.)

$CaO-CeO_2$ Minimum 1980°C, 30 percent CaO.

$CaO-CoO$ Eutectic 1420°C, 36 percent CaO.

$CaO-Cu_2O$ Eutectic 1140°C, 27 percent CaO.

$CaO-Fe_2O_3$ $2CaO \cdot Fe_2O_3$, (2:1), melting point 1449°C; eutectic with CaO, 42.0 percent CaO, 1438°C.

$CaO \cdot Fe_2O_3$, (1:1), incongruent melting to (2:1) plus liquid, 24 percent CaO, 1216°C; eutectic with (1:2), 1 atm O_2, 21.5 percent CaO, 1206°C.

	$CaO \cdot 2Fe_2O_3$, (1:2), disproportionates to (1:1) plus Hematite below 1172°C; incongruent melting to Hematite solid solution plus liquid. 78.0 percent Fe_2O_3 (1 atm O_2) 1228°C. Magnetite plus Hematite plus liquid 81.5 percent Fe_2O_3, (1 atm O_2) 1430°C. (Phillips and Muan, 1958.)
$CaO-Mn_3O_4$	Minimum 1450°C, 15 percent CaO.
CaO-NiO	Eutectic 1750°C, 36 percent CaO.
CaO-SrO	Continuous solid solution.
CaO-ThO2	Eutectic 2300°C, 24 percent CaO. All above systems with CaO by (Wartenberg, Reusch, and others, 1937.)
$CaO-Cr_2O_3$	Readily oxidized to chromate. (Ford and White, 1949.)
$CaO-Fe_2O_3$	$2CaO \cdot Fe_2O_3$, (2:1), incongruent melting to CaO and liquid 38 percent CaO, 1436°C. $CaO \cdot Fe_2O_3$, (1:1), incongruent melting to (2:1) and liquid 24.5 percent CaO, 1216°C; eutectic with Fe_2O_3, 7 percent CaO, 1205°C; not a true binary system because of dissociation of Fe_2O_3 to FeO. (Sosman and Merwin, 1916.)
CaO-MgO	Eutectic 2360°C, 66 percent CaO. (Rankin and Merwin, 1916.)
$CaO-TiO_2$	$CaTiO_3$, (1:1), Perovskite, melting point 1970°C; eutectic with TiO_2, 18 percent CaO, 1460°C; transition point 1260°C. $Ca_3Ti_2O_7$, (3:2), incongruent melting at 1750°C to (1:1) and liquid 60 percent CaO; eutectic with CaO, 63 percent CaO, 1695°C. (DeVries and others, 1954a); see also (Coughanour and others, 1954; Berezhnoy, 1950; Roth, 1958.)
$CaO-ZrO_2$	$CaZrO_3$, (1:1), melting point 2550°C; eutectic with ZrO_2 solid solution, 24 percent CaO, 2390°C; eutectic with CaO, 60 percent CaO, 2250°C. (Ruff and others, 1929.)
$CeO_2-Cr_2O_3$	$CeO_2 \cdot Cr_2O_3$(?), melting point 2440°C; eutectic with Cr_2O_3 2240°C.
$CeO_2-Fe_3O_4$	Minimum 1510°C, 30 percent CeO_2.
CeO_2-MgO	Minimum 2250°C, 20 percent CeO_2.
$CeO_2-Mn_3O_4$	Minimum 1540°C, 20 percent CeO_2. For systems with CeO_2 above, see (Wartenberg and Eckhardt, 1937.)
CeO_2-ZrO_2	Two series solid states at liquidus; eutectic 2310°C. (Duwez and Odell, 1950.)
CoO-MgO	Continuous series solid solution. (Wartenberg and Prophet, 1932.)
$CoO-ZrO_2$	Minimum 1730°C. (Wartenberg and Gurr, 1931.)
Cr_2O_3-FeO	$FeCr_2O_4$, Chromite, melting point 1670°C.
Cr_2O_3-MgO	$MgCr_2O_4$, melting point 2200°C; eutectic with MgO 2100°C, 33 percent MgO; eutectic with Cr_2O_3 2100°C, 8 percent MgO. (Wilde and Rees, 1943.)
$Cr_2O_3-ZrO_2$	Minimum 2320°C. (Wartenberg and Gurr, 1931.)
Cu_2O-MgO	Eutectic 1120°C, 20 percent MgO. (Wartenberg and Prophet, 1932.)

$CuO-PbO$	Eutectic 698°C, 41 percent PbO.
$FeO-MgO$	Continuous series solid solution. (Bowen and Schairer, 1935.)
$FeO-MnO$	Two series solid solution, peritectic relation, 1430°C. (Hay and others, 1934.)
$FeO-Mn_2O_3$	(Fe, Zn, Mn)O·(Fe, Mn)$_2O_3$, Franklinite, melting point above 1420°C.
$FeO-TiO_2$	$FeTiO_3$, (1:1), Ilmenite, natural melting point 1450°C; artificial melting point 1470°C; transition point 215°C; eutectic with TiO_2 1330°C, 68 percent TiO_2. Fe_2TiO_4, (2:1), Pseudobrookite, artificial melting point 1470°C; eutectic with (1:1) 1320°C; eutectic with FeO 1305°C, 5 percent TiO_2. (Grieve and White, 1939.)
Fe_2O_3-MgO	Fe_2O_3·MgO, Magnesioferrite, melting point 1750°C with loss of O_2. (Roberts and Merwin, 1931.)
$Fe_2O_3-Mn_2O_3$	Subliquidus limited solid state fields: Fe_2O_3, 0 to 14 percent Mn_2O_3 at 600°C, 0 to 19 percent Mn_2O_3 at 1050°C; Mn_2O_3, 71 to 100 percent Mn_2O_3 at 600°C, 36 to 100 percent Mn_2O_3 at 1000°C. (Mason, 1944.)
$Fe_2O_3-ZrO_2$	Minimum 1520°C. (Wartenberg and Gurr, 1931.)
K_2O-GeO_2	$K_2O·GeO_2$, (1:1), melting point 842°C; eutectic with (1:2) 710°C, 63.6 percent GeO_2. $K_2O·2GeO_2$, (1:2), melting point 797°C, eutectic with (1:4) 789°C, 70.4 percent GeO_2. $K_2O·4GeO_2$, (1:4), melting point 1038°C; eutectic with GeO_2 1006°C, 85.1 percent GeO_2. (Schwarz, 1929.)
La_2O_3-MgO	$La_2O_3·MgO$, melting point 2030°C; eutectic with La_2O_3, 1970°C, 8 percent MgO; eutectic with MgO, 1990°C, 34 percent MgO.
$La_2O_3-ZrO_2$	$La_2O_3·3ZrO_2$(?), incongruent melting point 2300°C; eutectic with La_2O_3 2080°C, 20 percent ZrO_2. (Wartenberg and Gurr, 1931.)
Li_2O-GeO_2	$2Li_2O·GeO_2$, melting point 1298°C. $Li_2O·GeO_2$, melting point 1239°C. (Schwarz, 1929.)
$MgO-GeO_2$	(Robbins and Levin, 1959.)
$MgO-Mn_3O_4$	Continuous liquidus without eutectic or minimum.
$MgO-NiO$	Continuous solid solution. (Wartenberg and Prophet, 1932.)
$MgO-TiO_2$	Mg_2TiO_4, melting point 1732°C. $MgTiO_3$, melting point 1630°C. $MgTi_2O_5$, melting point 1652°C. (Coughanour and DeProsse, 1953.)
$MgO-ZrO_2$	Two series solid solution, eutectic 2070°C; α-β ZrO_2 transition point 2550°C.
$MnO-TiO_2$	$MnTiO_3$, (1:1), Pyrophanite, incongruent melting to (2:1) and liquid, 60 percent TiO_2, 1360°C. Mn_2TiO_4, (2:1), melting point 1450°C, eutectic with MnO, 34 percent TiO_2, 1330°C. (Grieve and White, 1940.)

Mn_3O_4-ZrO_2	Minimum 1460°C. (Wartenberg and Gurr, 1931.)
Na_2O-GeO_2	Na_2GeO_3, (1:1), melting point 1083°C; eutectic with (1:2), 76 percent GeO_2, 778°C. $Na_2Ge_2O_5$, (1:2), melting point 799°C; eutectic with (1:4), 78.5 percent GeO_2, 789°C. $Na_2Ge_4O_9$, (1:4), melting point 1052°C; eutectic with GeO_2, 89 percent GeO_2, 1042°C. (Schwarz, 1929.)
Na_2O-TiO_2	Na_2TiO_3, melting point 1030°C. $Na_2Ti_2O_5$, melting point 985°C. $Na_2Ti_3O_7$, melting point 1128°C. (Washburn and Bunting, 1934.)
SnO_2-ZrO_2	SnO_2 volatilizes before fluxing occurs.
SrO-ZrO_2	$SrZrO_3$, melting point above 2700°C.
ThO_2-TiO_2	Minimum, 45 percent TiO_2, 1640°C. (Wartenberg and Eckhardt, 1937.)
ThO_2-ZrO_2	Continuous solid solution at liquidus probably; unmixing solvus, maximum about 2700°C, 50 mole percent ThO_2. (Ruff and others, 1929.)
TiO_2-ZrO_2	$ZrTiO_4$, incongruent melting to ZrO_2 solid solution and liquid, 55 percent TiO_2 1850°C, eutectic with TiO_2 solid solution, 70 percent TiO_2, 1760°C. (Brown and Duwez, 1954; Coughanour, Roth, and DeProsse, 1954; Sosman and Andrews, 1951.)
UO_2-CaO	$UO_2 \cdot CaO$ and $UO_2 \cdot 2CaO$, both decomposes below liquidus, 1850°C and 1790°C, respectively; eutectic UO_2 solid solution and CaO, 38 mole percent UO_2, 2080°C; solid solution limits at eutectic 55 to 100 mole percent UO_2. (Alberman and others, 1951.)
UO_2-MgO	No compounds; eutectic MgO and UO_2, 30 percent MgO, 2100°C; UO_2 in equilibrium with 2 liquids, about 8 to 24 percent MgO, about 2200°C. (Lambertson and Mueller, 1953b.)
UO_2-ThO_2	Continuous series solid solution. (Lambertson, Mueller and Gunzel, 1953.)
UO_2-ZrO_2	Two series solid solutions meet at a eutectic, about 52 percent ZrO_2, 2540°C. Solvus for face-centered UO_2 solid solution and tetragonal. ZrO_2 solid solution, maximum about 1930°C, 52 mole percent ZrO_2. (Lambertson and Mueller, 1953c.)
ZnO-ZrO_2	Eutectic 1810°C; ZnO volatilizes. (Wartenberg and Gurr, 1931; Wartenberg and Eckhardt, 1937.)

SILICATE SYSTEMS, BINARY

Al_2O_3-SiO_2	$3Al_2O_3 \cdot 2SiO_2$, (3:2), Mullite, incongruent melting to Corundum plus liquid of 55 percent Al_2O_3, 1810°C; eutectic with Cristobalite 94.5 percent SiO_2, 1959°C. (Bowen and Greig, 1924; Schairer, 1942.) See figure 2.

(3:2) melts congruently 1875°C; eutectic with Corundum 1860°C. (Toropov and Galakhov, 1951.)

(3:2) forms solid solution to 79 percent Al_2O_3. (Toropov and Galakhov, 1958.)

Liquidus relations of Bowen and Greig (1924) are confirmed, Mullite phase has range of homogeneity 72 to 78 percent Al_2O_3. (Trőmel and others, 1957.)

$Al_2O_3 \cdot SiO_2$, (1:1), Sillimanite, Andalusite, Kyanite, all decompose to Mullite and SiO_2; Kyanite between 1000°C and 1325°C; Andalusite between 1325°C and 1410°C; Sillimanite between 1345°C and 1550°C. (Greig, 1926.)

Andalusite synthesis (Roy, D. M., 1954.)

Kyanite-Sillimanite equilibrium curve 18,200 bars at 1000°C; 21,000 bars at 1300°C, with Kyanite field on the high pressure side of curve. (Clark and others, 1957.)

B_2O_3-SiO_2 — No compounds, no liquid immiscibility, eutectic near 100 percent B_2O_3, 450°C.

BaO-SiO_2 — Ba_2SiO_4, (2:1), melting point above 1700°C; eutectic with (1:1), 24.5 percent SiO_2, 1551°C.

$BaSiO_3$, (1:1), melting point 1604°C; eutectic with (2:3), 40 percent SiO_2, 1437°C.

$Ba_2Si_3O_8$, (2:3), melting point 1450°C; solid solution with (1:2).

$BaSi_2O_5$, (1:2), Sanbornite, melting point 1420°C; solid solution with (2:3); eutectic with tridymite, 50 percent SiO_2, 1374°C.

Cristobalite liquidus: no liquid immiscibility in contradistinction from systems of MgO, CaO and SrO with SiO_2. (Eskola, 1922; Glushkova, 1957; Greig, 1927a.)

BeO-SiO_2 — Eutectic of BeO, SiO_2 and liquid, 95 percent SiO_2, 1670°C.

Be_2SiO_4, (2:1), Phenacite, decomposes 1560°C, below eutectic of system. (Morgan and Hummel, 1949.)

CaO-SiO_2 — Ca_3SiO_5 (3:1), disproportionates below the liquidus, to CaO and (2:1), 1900°C; unstable below 1250°C.

Ca_2SiO_4, (2:1) melting point 2130°C; eutectic with CaO, 30.5 percent SiO_2, 2065°C; tetramorphous, α, α (Bredigite), transition point 1437°C; α, γ transition point 725°C; β, Larnite, is labile at 1 bar, stable above 137 bars; D. M. Roy (1958). Transition behavior is influenced by additions of Mg_2SiO_4, $Ca_3(PO_4)_2$ and other substances in solid solution (Bredig, 1950). For the influence of grain size and departures from stoichiometry upon α' to β, or α' to γ transitions, see Guinier and Yannaquis (1957). Transition of α' to γ results in about 10 percent volume increase. (Rankin and Wright, 1915; Roy, D. M., 1958; Bredig, 1950; Muan and Osborn, 1951.)

$Ca_3Si_2O_7$, (3:2), incongruent melting to (2:1) and liquid, 44.5 percent SiO_2, 1475°C; eutectic with (1:1), 45.5 percent SiO_2, 1455°C.

$CaSiO_3$, (1:1), melting point 1540°C; Wollastonite, monoclinic; transition at 1125°C to Pseudowollastonite, pseudohexagonal; eutectic with Tridymite, 63 percent SiO_2, 1436°C.

Cristobalite liquidus, liquid immiscibility 72 to 99 percent SiO_2, 1698°C. (Rankin and Wright, 1915; Greig, 1927a.) See figure 3.

$CoO-SiO_2$

Co_2SiO_4, (2:1), melting point 1420°C; eutectic with CoO 1377°C.
$CoSiO_3$, (1:1), may exist as incongruent melting phase, breaks up into SiO_2 and liquid at 1400°C; eutectic with (2:1), 1382°C. (Asanti and Kohlmeyer, 1951.)
Cristobalite liquidus with liquid immiscibility 1725°C. (Greig, 1927b.)

$Cr_2O_3-SiO_2$

No compounds, eutectic 1710°C. Liquid immiscibility overlying field of Cr_2O_3, 5 to 95 percent Cr_2O_3, 2200°C. (Bunting, 1930b; Keith, 1954.)

Cu_2O-SiO_2

No compounds, eutectic with 8 percent SiO_2, 1060°C; liquid immisibility overlying Cristobalite, 36 to 95 percent SiO_2, 1690°C. (Berezhnoy and others, 1952.)

$FeO-SiO_2$

Fe_2SiO_4, (2:1), Fayalite, melting point 1205°C; eutectic with Wüstite, 24 percent SiO_2, 1177°C; eutectic with Tridymite 38 percent SiO_2, 1178°C.
Cristobalite and two liquids, 58 to 97 percent SiO_2, 1690°C. (Bowen and Schairer, 1932; Greig, 1927b; Muan, 1958c.) See figure 4.

$Fe_2O_3-SiO_2$

No compounds; liquidus temperatures are not determined. Cristobalite and two immiscible liquids of very wide range. Eutectic probably near 100 percent SiO_2.
At 1 atmosphere pressure of air, Fe_2O_3; dissociates to Fe_3O_4 and oxygen above 1388°C. (Bowen and others, 1930; Darken and Gurry, 1946; Greig, 1927b; Muan, 1958c.)

K_2O-SiO_2

K_2SiO_3, (1:1), melting point 976°C, transition point 725°C, transition point 750°C; eutectic with (1:2), 45.5 percent SiO_2, 780°C.
$K_2Si_2O_5$, (1:2), melting point 1045°C; transition point 217°C, transition point 593°C; eutectic with (1:4), 67.6 percent SiO_2, 742°C.
$K_2Si_4O_9$, (1:4), melting point 770°C; transition point 592°C; pressure lowers melting point 60°C per kilobars, raises transition point 28°C per kilobar; eutectic with Quartz 72.5 percent SiO_2, 769°C. (Kracek, Bowen, and Morey, 1937; Goranson and Kracek, 1932.)

Li_2O-SiO_2

Li_4SiO_4, (2:1), incongruent 1255°C; eutectic with (1:1), 55.3 percent SiO_2, 1024°C.
Li_2SiO_3, (1:1), melting point 1201°C.
$Li_2Si_2O_5$, (1:2), incongruent melting to (1:1) and liquid, 80.1 percent SiO2, 1033°C; eutectic with Tridymite, 82.2 percent SiO_2, 1028°C; transition point 936°C. (Jaeger and Klooster, 1914; Kracek, 1930b; Kracek, 1939.)

$MgO-SiO_2$

Mg_2SiO_4, (2:1), Forsterite, melting point 1890°C; eutectic with MgO, 36 percent SiO_2, 1850°C.
$MgSiO_3$, (1:1), Enstatite, and its varieties, incongruent melting to (2:1), and liquid, 60.9 percent SiO_2, 1557°C; slow transition Protoenstatite to Enstatite, 1260°C; Protoenstatite - Clinoenstatite 700°C cooling, 1000 to 1100°C heating. (Foster, 1951b.)
Cristobalite and immiscible liquids, 69 to 99 percent SiO_2, 1695°C. (Bowen and Anderson, 1914; Greig, 1927a.) See figure 5.

$MnO-SiO_2$

Controlled atmosphere in furnace to retain Mn in 2+ state.

Mn_2SiO_4, (2:1), Tephroite, melting point 1345°C; eutectic with MnO, 25.5 percent SiO_2, 1317°C; eutectic with (1:1), 38.3 percent SiO_2, 1251°C.

$MnSiO_3$, (1:1), Rhodonite, incongruent melting to Tridymite plus liquid, 44.5 percent SiO_2, 1291°C.

Cristobalite plus 2 liquids, 55 to 99 percent SiO_2, 1705°C. (Glasser, 1958a), with references to earlier data.

$Mn_3O_4-SiO_2$

In air atmosphere (0.21 atmosphere O_2). System is a portion of Mn-Si-O.

Mn_3O_4 (cubic) + Mn_3O_4 (tetragonal), 1160°C.

Mn_3O_4 (tetragonal) + Mn_2O_3, 877°C.

Mn_3O_4 (cubic) + Tephroite + liquid, 33 percent SiO_2, 1230°C.

Mn_2SiO_4 Tephroite, + $MnSiO_3$ solid solution + liquid, 34 percent SiO_2, 1206°C.

Mn_3O_4 (cubic) + Mn_2O_3 solid solution + $MnSiO_3$ solid solution 1168°C.

$MnSiO_3$ solid solution + Tridymite + liquid, 42 percent SiO_2, 1272°C.

Mn_2O_3 solid solution + $MnSiO_3$ solid solution + Tridymite, 1048°C.

Cristobalite + 2 liquids, 55 to 99 percent SiO_2, 1700°C. (Muan, 1959.)

Na_2O-SiO_2

Na_4SiO_4, (2:1), incongruent melting point 1118°C; eutectic with (1:1), 43.1 percent SiO_2, 1022°C.

Na_2SiO_3, (1:1), melting point 1089°C; eutectic with (1:2), 62.1 percent SiO_2, 837°C.

$Na_2Si_2O_5$, (1:2), melting point 874°C; eutectic with Quartz, 74.2 percent SiO_2, 789°C; metastable eutectic with Tridymite, about 75 percent SiO_2, 770°C; 6 slowly inverting polymorphous phases A, B, C, D, E, F; rapid transition in A, 678°C, 707°C; rapid transition in E 549°C, 573°C, 593°C. (Morey and Bowen, 1925; Kracek, 1930a; d'Ans and Löffler, 1930; Kracek, Morey, and England, 1953.)

$NiO-SiO_2$

2 immiscible liquids, 1725°C; eutectic with SiO_2, 90 percent SiO_2. (Greig, 1927b.)

$P_2O_5-SiO_2$

Compounds $SiO_2 \cdot P_2O_5$ and $3SiO_2 \cdot P_2O_5$ crystallize rapidly, whereas the components tend to remain vitreous. (Huttner, 1908; Tamman, 1925.)

$PbO-SiO_2$

Pb_4SiO_6, (4:1), incongruent melting to PbO and liquid 6.7 percent SiO_2, 725°C; transition 120° to 155°C, transition 720°C; eutectic with (2:1), 8.2 percent SiO_2, 714°C.

Pb_2SiO_4, (2:1), melting 743°C; eutectic with (1:1), 15.4 percent SiO_2, 716°C.

$PbSiO_3$, (1:1), melting point 762; eutectic with Quartz, 29 percent SiO_2, 732°C.

Cristobalite and immiscible liquid pair probable. (Geller and others, 1934.)

$Pb_3Si_2O_7$, (3:2), Barysilite, natural melting point 690°C; artificial does not crystallize in 20 hours at 705°C.

$PbSiO_3$, (1:1), natural melting point 764°C; eutectic with SiO_2, 26.9 percent SiO_2, 732°C.

Rb_2O-SiO_2

$Rb_2Si_2O_5$, (1:2), melting point 1115°C.

$Rb_2Si_4O_9$, (1:4), melting point 957°C. (Kracek, 1933.)

SnO-SiO_2 — No liquid immiscibility found at 80 and 90 percent SiO_2, at 1715°C and 1725°C, respectively. (Greig, 1927a.)

SrO-SiO_2 — Sr_2SiO_4, (2:1), melting above 1700°C; eutectic with (1:1), 34.5 percent SiO_2, 1545°C.
$SrSiO_3$, (1:1), melting point 1580°C; eutectic with Tridymite, 53.5 percent SiO_2, 1358°C.
Cristobalite and two immiscible liquids, 70 to 97.5 percent SiO_2, 1692°C. (Eskola, 1922; Greig, 1927a.)

TiO_2-SiO_2 — No compounds; eutectic of SiO_2 and Rutile, 10.5 percent TiO_2, 1550°C.
Rutile and 2 immiscible liquids, 19 to 93 percent TiO_2, 1780°C.
Rutile, TiO_2, melting point 1830°C. (DeVries, Roy, and Osborn, 1954b.)

ZnO-SiO_2 — Zn_2SiO_4, (2:1), Willemite, melting point 1512°C; eutectic with ZnO, 22.5 percent SiO_2, 1507°C; eutectic with Tridymite, 50.9 percent SiO_2, 1432°C.
Cristobalite and 2 immiscible liquids, 65 to 98 percent SiO_2, 1695°C. (Bunting, 1930a.)

ZrO_2-SiO_2 — $ZrSiO_4$, (1:1), Zircon, decomposes to oxides below liquidus, 1540°C.
Eutectic with SiO_2, ZrO_2 and liquid 1670°C. (Curtis and Sowman, 1953.)

SILICATE SYSTEMS, TERNARY

Al_2O_3-BaO-SiO_2 — $BaO \cdot Al_2O_3 \cdot 2SiO_2$, (1:1:2), Celsian, monoclinic; Paracelsian, orthorhombic, topazlike; (Spencer, 1942); melting above 1700°C.
$3BaO \cdot 3Al_2O_3 \cdot 2SiO_2$, (3:3:2), decomposes below liquidus, (Toropov, Galakhov and Bondar, 1954, 1955.)
Field boundaries and melting relations for (1:1:2) and mullite, silica and Ba silicates. (Thomas, 1950.)

Al_2O_3-CaO-SiO_2 — $CaO \cdot Al_2O_3 \cdot 2SiO_2$, (1:1:2), Anorthite, melting point 1550°C.
$2CaO \cdot Al_2O_3 \cdot SiO_2$, (2:1:1), melting point 1590°C.
Melting relations and field boundaries for (1:1:2), (2:1:1) and adjoining binary and unary compounds have been determined. (Rankin and Wright, 1915; Greig, 1927a; Goldsmith, 1948; Langenberg and Chipman, 1956.)
For ternary equilibrium diagram, see figure 6.

Al_2O_3-FeO-SiO_2 — $2FeO \cdot 2Al_2O_3 \cdot 5SiO_2$ (2:2:5), Iron Cordierite, incongruent melting to Mullite and liquid 1210°C.
$3FeO \cdot Al_2O_3 \cdot 3SiO_2$, (3:1:3), Almandine, dry could not be crystalized; natural (3:1:3) decomposes 900°C.
For ternary equilibrium diagram, see figure 7. Lowest ternary eutectic. (Fe Cordierite, Tridymite, Fayalite), 1083°C. (Schairer and Yagi, 1952; Langenberg and Chipman, 1956.)

Al_2O_3-Fe_2O_3-SiO_2 — Ternary diagram giving equilibrium phases at 1000°C; solid solution with a gap, solid solution Al_2O_3 and solid solution Fe_2O_3. (Nowotny and Funk, 1951; see also Muan, 1958a.)

690-216 O - 63 - 4

Al_2O_3-K_2O-SiO_2

$K_2O \cdot Al_2O_3 \cdot SiO_2$, (1:1:1) in octahedra prepared with aid of fluxes, melts well above 1700°C.

$K_2O \cdot Al_2O_3 \cdot 2SiO_2$, (1:1:2); low temperature hexagonal; similar to natural Kaliophilite below 900°C; above 1000°C orthorhombic; hexagonal Kalsilite is formed only in presence of some Na_2O, between 650°C and 1200°C. (Rigby and Richardson, 1947.) Hexagonal Kalsilite is phase stable below 840°C, a second high orthorhombic modification in some melts with $NaAlSiO_4$ present. (Tuttle and Smith, 1953.) Melts above 1700°C; eutectic with (1:1:4), 1615°C.

$K_2O \cdot Al_2O_3 \cdot 4SiO_2$, (1:1:4), Leucite, melting point 1686°C; cubic above (603°C) 627°C.

$K_2O \cdot Al_2O_3 \cdot 6SiO_2$, (1:1:6), Potash feldspar, incongruent melting to (1:1:4) and liquid, 1150°C; eutectic with SiO_2 990°C.

For ternary equilibrium diagram, see figure 8; lowest ternary eutectic with Potash feldspar, $K_2Si_4O_9$, $K_2Si_2O_5$, 695°C. (Schairer, 1955; Schairer and Bowen, 1947b See figure 8.

Al_2O_3-Li_2O-SiO_2

$Li_2O \cdot Al_2O_3 \cdot 2SiO_2$, (1:1:2), Eucryptite, melting point 1405°C; α-β transition point 970°C; transition point lowered by solid solution with (1:1:4) to about 900°C; interrupted series solid solution at liquidus with (1:1:4); transition point about 1410°C.

$Li_2O \cdot Al_2O_3 \cdot 4SiO_2$, (1:1:4), Spodumene, melting point 1425°C; α-β transition point 510°C; transition point lowered in solid solution by (1:1:2) to 485°C, by (1:1:8) to 460°C; solid solution with excess SiO_2 at liquidus; eutectic with Tridymite, 1356°C.

$Li_2O \cdot Al_2O_3 \cdot 8SiO_2$ (1:1:8), Petalite, decomposes below liquidus to Quartz and (1:1:4), 680°C. (Roy, Rustum, and Osborn, 1949; Roy, Rustum, Roy, D. M. and others, 1950; Krishna-Murthy and Hummel, 1954; Hatch, 1943.)

Al_2O_3-MgO-SiO_2

$2MgO \cdot 2Al_2O_3 \cdot 5SiO_2$, (2:2:5), Cordierite, incongruent melting to Mullite and liquid, 1460°C.

$4MgO \cdot 5Al_2O_3 \cdot 2SiO_2$, (4:5:2), Sapphirine, incongruent melting to $MgO \cdot Al_2O_3$, Spinel, and liquid, 1482°C.

For ternary equilibrium diagram see figure 9; lowest ternary eutectic with $MgO \cdot SiO_2$, Tridymite and Cordierite, 1345°C. (Rankin and Merwin, 1918; Bowen and Greig, 1924; Greig, 1927a; Schairer, 1942; Foster, 1950, 1951a; Keith and Schairer, 1952.)

Al_2O_3-MnO-SiO_2

$2MnO \cdot 2Al_2O_3 \cdot 5SiO_2$, (2:2:5), Manganese Cordierite, incongruent melting to mullite and liquid about 1168°C.

$3MnO \cdot 3Al_2O_3 \cdot 3SiO_2$, (3:1:3), Spessartite, melting above 1200°C.

Partial study of system at the liquidus. (Snow, 1943.)

Al_2O_3-Na_2O-SiO_2

$Na_2O \cdot Al_2O_3 \cdot 2SiO_2$, (1:1:2), Nepheline, hexagonal, low temperature; Carnegieite, cubic, high temperature; transition point 1248°C pure, solid solution of Albite raises transition point to 1280°C, solid solution of Na_2SiO_3 lowers transition point to 1163°C; Carnegieite, melting point 1526°C; ternary eutectic of Na_2SiO_3, $Na_2Si_2O_5$ and 1:1:2, 760°C.

$NaO \cdot Al_2O_3 \cdot 4SiO_2$, (1:1:4), Jadeite, no sharp melting point at 1 atmosphere; decomposes to glass as low as 800°C; the glass devitrifies to a mixture of (1:1:2) and (1:1:6) in solid solution. Thermochemical data indicates that Jadeite should be formed by reaction Albite + Nepheline = 2 Jadeite at 25°C and 1 atmosphere. The stability of Jadeite is favored by increased pressure. At higher temperatures increasingly higher pressures are required, reaching 17,000 atmospheres at 927°C. (Kracek, Neuvonen, and Burley, 1951; Kelley and others, 1953.) Synthesis of Jadeite has been accomplished by above reaction at pressures and temperatures related by $P=(1000+18.5t)$ kg per cm^2. (Robertson and others, 1957.)

$Na_2O \cdot Al_2O_3 \cdot 6SiO_2$, (1:1:6), Albite, melting point 1118°C, ternary eutectic with Quartz, $Na_2Si_2O_5$, 740°C.

For ternary equilibrium diagram see figure 10; lowest ternary eutectic with $Na_2Si_2O_5$, Albite and Nepheline 732°C. (Schairer and Bowen, 1956.)

Al_2O_3-PbO-SiO_2

$4PbO \cdot Al_2O_3 \cdot 2SiO_2$, (4:1:2), incongruent melting to an unidentified compound and liquid, 837°C.

$8PbO \cdot Al_2O_3 \cdot 4SiO_2$, (8:1:4), incongruent melting at (4:1:2) and liquid, 735°C.

$6PbO \cdot Al_2O_3 \cdot 6SiO_2$, (6:1:6), melting point 811°C.

Detailed study of high PbO compositions in the ternary system. (Geller and Bunting, 1943.)

Al_2O_3-TiO_2-SiO_2

No ternary compounds; fields of mullite and corundum, $TiAl_2O_5$, rutile and cristobalite; ternary eutectic of cristobalite, Rutile and $TiAl_2O_5$, about 1480°C. (Agamawi and White, 1951.)

Al_2O_3-ZnO-SiO_2

No ternary compounds; fields of ZnO, Zn_2SiO_4, Cristobalite, $ZnAl_2O_4$, mullite and corundum; lowest ternary eutectic Zn_2SiO_4, cristobalite and $ZnAl_2O_4$, 1305°C. (Bunting, 1932.)

B_2O_3-BaO-SiO_2

$3BaO \cdot 3B_2O_3 \cdot 2SiO_2$, (3:3:2), melting point 1009°C.

Field of 2 liquids extends from BaO-B_2O_3 boundary far towards BaO-SiO_2 boundary over fields of $BaO \cdot 4B_2O_3$, Tridymite, and Cristobalite.

Lowest ternary eutectic with $BaO \cdot 4B_2O_3$, $BaO \cdot 2B_2O_3$ and Tridymite, 810°C. (Levin and Ugrinic, 1953; Levin and Cleek, 1958.)

B_2O_3-CaO-SiO_2

$CaO \cdot B_2O_3 \cdot 2SiO_2$, (1:1:2), Danburite, decomposes to 2 liquids 996° to 1002°C.

$5CaO \cdot B_2O_3 \cdot SiO_2$, (5:1:1), melting point 1419°C.

Field of 2 liquids extends completely across the system from CaO-B_2O_3 to CaO-SiO_2, overlying fields of CaO. $2B_2O_3$, (1:1:2), and SiO_2. (Flint and Wells, 1936; Morey and Ingerson, 1937.)

B_2O_3-Li_2O-SiO_2

$Li_2B_2O_4$-Li_2SiO_3, eutectic, 22 percent Li_2SiO_3, 803°C. (Klooster, 1910a, b.)

B_2O_3-Na_2O-SiO_2

$Na_2O \cdot B_2O_3 \cdot 2SiO_2$, (1:1:2), melts above 730°C; extent of field of (1:1:2) could not be determined owing to reluctance to crystallize.

No liquid immiscibility in the system. (Morey, 1951.)

B_2O_3-PbO-SiO_2

$5PbO \cdot B_2O_3 \cdot SiO_2$, (5:1:1), incongruent melting to 2PbO. SiO_2 and liquid about 550°C.

Liquid immiscibility extends into system from PbO-B_2O_3 to part overlying fields of $PbO \cdot 2B_2O_3$ and SiO_2. (Geller and Bunting, 1939.)

B_2O_3-ZnO-SiO_2

No ternary compounds.

Liquid immiscibility area extends completely across system from ZnO-SiO_2 to ZnO-B_2O_3 boundaries. It partly overlies fields of $ZnO \cdot B_2O_3$, $5ZnO \cdot 2B_2O_3$, Zn_2SiO_4 and SiO_2. (Ingerson, Morey and Tuttle, 1948.)

BaO-CaO-SiO_2

The binary join $CaSiO_3$-$BaSiO_3$: $2CaO \cdot BaO \cdot 3SiO_2$(2:1:3) incongruent melting to $CaSiO_3$ and liquid 52 percent $BaSiO_3$, 1320°C. (Eskola, 1922.)

BaO-Na_2O-SiO_2

The binary join $Na_2Si_2O_5$-$BaSi_2O_5$: eutectic, 33 percent $BaSi_2O_5$, 797°C. (Greene and Morgan, 1941.)

BaO-TiO_2-SiO_2

The binary join $BaTiO_3$-SiO_2: $BaO \cdot TiO_2SiO_2$, (1:1:1), melting point 1400°C; eutectic with $BaTiO_3$, 32 percent SiO_2, 1260°C; eutectic with (1:1:2), 67 percent SiO_2, 1246°C.

$BaO \cdot TiO_2 \cdot 2SiO_2$, (1:1:2), melting point 1250°C; eutectic with SiO_2, 70 percent SiO_2, 1245°C.

$BaO \cdot TiO_2 \cdot 3SiO_3$, (1:1:3), decomposes below liquidus to (1:1:2) and Tridymite, 965°C.

Cubic to hexagonal $BaTiO_3$ transition point raised to 1575°C by limited solid solution. (Rase and Roy, 1955a, b.)

CaO-FeO-SiO_2

$CaO \cdot FeO \cdot SiO_2$, (1:1:1), Ca-Fe Olivine, melting point 1208°C.

The join $CaSiO_3$-(1:1:1), forms the only binary system within the ternary; eutectic at 20 percent $CaSiO_3$, 1203°C.

$2CaO \cdot FeO \cdot 2SiO_2$, (2:1:2), Fe Akermanite, stable only below 775°C; decomposes into (1:1:1) and $CaSiO_3$ 775°C.

$CaO \cdot FeO \cdot 2SiO_2$, (1:1:2), Hedenbergite, stable only below 965°C; decomposes into $CaSiO_3$ solid solution; melting relations are ternary, there being no crystalline $FeSiO_3$, but mixtures 0 to 72 percent $FeSiO_3$ behave in binary manner(Bowen, Schairer, and Posnjak,1933, p. 217.)

No ternary eutectic in System, but the field of Ca-Fe olivines which are solid solution of variable orthosilicate composition, has a minimum along the boundary with wollastonite solid solution about 1100°C.

Courses of crystallization of Wollastonite solid solution and Ca-Fe Olivines solid solution are outlined(Bowen, Schairer, and Posnjak, 1933, figures 9-25.)

For ternary diagram, see figure 11. (Bowen, Schairer, and Posnjak, 1933; Allen and Snow, 1955.)

CaO-Fe_2O_3-SiO_2

Partial study of system outlines fields in $CaSiO_3$, $Ca_3Si_2O_7$, Ca_2SiO_4, and CaO.

Extent of 2 liquid region from Fe_2O_3-SiO_2 towards CaO-SiO_2 boundary was not determined. (Burdick, 1940; Greig, 1927b; Iwasé and Nisioka, 1938; Phillips and Muan, 1958.)

$CaO-K_2O-SiO_2$

$2CaO \cdot K_2O \cdot 9SiO_2$, (2:1:9), incongruent melting to β Ca SiO_3 and liquid 1050°C; eutectic with $K_2O \cdot 4SiO_2$ 730°C; ternary eutectic with $K_2O \cdot 4SiO_2$ and Quartz 720°C; ternary eutectic with $K_2O \cdot 2SiO_2$ and $K_2O \cdot 4SiO_2$ 720°C.

$CaO \cdot 4K_2O \cdot 10SiO_2$, (1:4:10) melting point 946°C.

$CaO \cdot 2K_2O \cdot 6SiO_2$, (1:2:6), melting point 959°C.

β $CaO \cdot K_2O \cdot 6SiO_2$, (3:1:6), incongruent melting to β Ca SiO_3 and liquid 1020°C; dimorphous, transition point 985°C.

$CaO \cdot 2K_2O \cdot 3SiO_2$, (1:2:3), incongruent melting to (1:1:1) and liquid 1005°C; eutectic with $K_2O \cdot SiO_2$ 900°C; eutectic with $K_2O \cdot 2SiO_2$ 900°C; eutectic with (1:4:10), 895°C; eutectic with (1:2:6) 895°C; ternary eutectic with $K_2O \cdot SiO_2$, and $K_2O \cdot 2SiO_2$, 770°C.

$CaO \cdot K_2O \cdot SiO_2$, (1:1:1), melting point 1630°C.

Region of good glasses: fields of (2:1:9) and of (3:1:6), composition limits 2 to 15 percent CaO, 67 to 73 percent SiO_2. (Morey, Kracek, and Bowen, 1930.)

$CaO-Li_2O-SiO_2$

The binary join $Li_4SiO_4-Ca_2SiO_4$, $6Li_2O \cdot 4CaO \cdot 5SiO_2$, (6:4:5), melting point 1108°C; eutectic with Li_4SiO_4 1090°C; eutectic with (4:6:5), 1065°C.

$4Li_2O \cdot 6CaO \cdot 5SiO_2$, (4:6:5), melting point 1090°C; eutectic with Ca_2SiO_4, 1050°C. (Schwarz, 1921; Wallace, 1909.)

$CaO-MgO-SiO_2$

$CaO \cdot MgO \cdot 2SiO_2$, (1:1:2), Diopside, melting point 1391°C; forms continuous solid state with $MgO \cdot SiO_2$.

$2CaO \cdot MgO \cdot 2SiO_2$, (2:1:2), Akermanite, melting point 1454°C; low temperature limit of stability was studied in hydrothermal experiments: mixtures of oxides in ratio (2:1:2) yielded $CaSiO_3$ as Wollastonite and CaO. $MgO \cdot SiO_2$ as Monticellite when heated below 700°C to 750°C at pressures up to 4000 bars. Above 750°C Akermanite was formed. Results have bearing on the problem of the petrogenetic grid of the Bowen (1940) decarbonation series: (Harker and Tuttle, 1956.)

$CaO \cdot MgO \cdot SiO_2$, (1:1:1), Monticellite, incongruent melting to MgO plus liquid, 1503°C.

$3CaO \cdot MgO \cdot 2SiO_2$, (3:1:2), Merwinite, incongruent melting to Ca_2SiO_4 plus liquid, 1575°C.

For ternary diagram, see figure 12. (Ferguson and Merwin, 1919; Greig, 1927a; Ricker and Osborn, 1954; Bowen, 1914; Schairer and Bowen, 1942; Osborn, 1943; Bredig, 1950; Atlas, 1952.)

$CaO-MnO-SiO_2$

$CaSiO_3-MnSiO_3$, Wollastonite-Rhodonite, isodimorphous series solid solution; α-β $CaSiO_3$ transition point raised to 1374°C. (Voos, 1935.)

$Ca_2SiO_4-Mn_2SiO_4$, Tephroite, solid solution with a minimum, 15 mole percent Tephroite, 1170°C; Glaucochroite, $CaMnSiO_4$, is interpreted as equimolar solid solution (Kallenberg, 1914; Tokody, 1928.)

$CaO-Na_2O-SiO_2$

$CaO \cdot 2Na_2O \cdot 3SiO_2$, (1:2:3), incongruent melting to (2:1:3) and liquid 1141°C; eutectic with $Na_2O \cdot SiO_2$, 1060°C.

$2CaO \cdot Na_2O \cdot 3SiO_2$, (2:1:3), melting point 1284°C; eutectic with $Na_2O \cdot 2SiO_2$, 862°C.

$3CaO \cdot Na_2O \cdot 6SiO_2$, (3:1:6), Devitrite, incongruent melting to β $CaSiO_3$ and liquid 1047°C.

Region of good glasses: field of Devitrite and adjoining regions, 5 to 15 percent CaO, 67 to 74 percent SiO_2.
Lowest ternary eutectic with Devitrite, Quartz, Na_2O. $2SiO_2$, 725°C. (Morey and Bowen, 1925; Morey, 1930.)

$CaO-P_2O_5-SiO_2$

$7CaO \cdot P_2O_5 \cdot 2SiO_2$, (7:1:2), Nagelschmidtite, melting point indefinite; interpreted as series of solid solution of $Ca_3(PO_4)_2$ in Ca_2SiO_4 rather than as a compound by Bredig (1943, 1950); phase found in phosphate slag is biaxial positive, parallel extinction, $\alpha = 1.652$, $\gamma = 1.661$, $G = 3.035$.

$5CaO \cdot P_2O_5 \cdot SiO_2$, (5:1:1), Silicocarnotite, decomposes 1300°C to solid solution phases; compound has solid solution range of composition; biaxial, 2V nearly 90°, $\alpha = 1.632$, $\beta = 1.636$, $\gamma = 1.640$.

$Ca_2SiO_4-Ca_3(PO_4)_2$ system, two series solid solution at liquidus, transition point 1900°C; Ca_2SiO_4 rich and $Ca_3(PO_4)_2$ rich solid solution with gap below liquidus; below 1300°C, (5:1:1), solid solution separate from the two series; transitions in Ca_2SiO_4 and in $Ca_3(PO_4)_2$ are lowered by solid solution. (Bredig, 1950.)

$Ca_3(PO_4)_2-SiO_2$ system, eutectic of $Ca_3(PO_4)_2$, Cristobalite and liquid, about 8 percent SiO_2, 1540°C; Cristobalite and 2 liquids, 12.5 to about 95 percent SiO_2, about 1680°C. (Trömel and others, 1948.)

Liquid immiscibility area extends from $CaO-SiO_2$, 1698°C, far towards $CaO-P_2O_5$. (Barrett and McCaughey, 1942; Greig, 1927a; Tromel, 1932, 1943; Bredig, 1943, 1950; St. Pierre, 1953; Trömel and others, 1948; Hill, Faust, and Reynolds, 1944.)

$CaO-SrO-SiO_2$

The binary join $CaSiO_3-SrSiO_3$, solid solution series with a minimum, 56 percent $SrSiO_3$, 1475°C. (Eskola, 1922.)

$CaO-TiO_2-SiO_2$

$CaTiSiO_5$, (1:1:1), Titanite (Sphene), melting point 1382°C; eutectic with $CaTiO_3$, 1375°C; eutectic with Tridymite, 1373°C; eutectic with $CaSiO_3$, 1373°C; eutectic with TiO_2, Rutile, 1375°C.

Liquid immiscible region extends from $CaO-SiO_2$ to $CaO-TiO_2$ boundary, in part overlying the fields of Cristobalite and Rutile. (DeVries, Roy, and Osborn, 1953, 1955; Berezhnoi, 1950; Iwasé and Fukusima, 1936; Iwasé and Nisioka, 1936.)

$CaO-ZnO-SiO_2$

$2CaO \cdot ZnO \cdot 2SiO_2$, (2:1:2), melting point 1425°C; ternary eutectic with Tridymite and Zn_2SiO_4, 1170°C; eutectic with Zn_2SiO_4 and ZnO, 1259°C; eutectic with ZnO and Ca_2SiO_4, 1345°C; eutectic with $CaSiO_3$ and $Ca_3Si_2O_7$, 1365°C; with $CaSiO_3$ and Tridymite, 1223°C.

Liquid immiscible region extends from $CaO-SiO_2$ to $ZnO-SiO_2$, in part overlying the field of Cristobalite. (Segnit, 1954.)

$Cr_2O_3-MgO-SiO_2$

No ternary compounds; lowest temperatures are near $MgO-SiO_2$ binary; lowest ternary eutectic with $MgSiO_3$, SiO_2, $MgCr_2O_4$, with about 2 percent Cr_2O_3 added to eutectic of $MgSiO_3$ and SiO_2, 1546°C.

Liquid immiscible region extends from $MgO-SiO_2$ to $MgO-Cr_2O_3$, partly overlying fields of Cr_2O_3, $MgCr_2O_4$ (Picrochromite) and Cristobalite.
Field of $MgCr_2O_4$, Picrochromite, separates field of MgO, Periclase, from that of 2 liquids. (Keith, 1954.)

$FeO-Fe_2O_3-SiO_2$ Two-liquid region overlying Cristobalite across system near SiO_2 corner. (Greig, 1927b.)
Ternary eutectic of Fayalite, Grunerite and Fe_2O_3, 40FeO, $20Fe_2O_3$, $40SiO_2$. (Hallimond and Whiteley, 1919); this eutectic is not possible because $FeSiO_3$ does not crystallize in binary system $FeO-SiO_3$. (Bowen, Schairer and Posnjak, 1933.)
1600°C section of system (Gurry and Darken, 1950.)

$FeO-K_2O-SiO_2$ $K_2O \cdot FeO \cdot 5SiO_2$, (1:1:5), melting point 900°C.
$K_2O \cdot FeO \cdot 3SiO_2$, (1:1:3), melting point 900°C.
Two-liquid region over Cristobalite along $FeO-SiO_2$ boundary, (Roedder, 1952.)

$FeO-MgO-SiO_2$ No ternary compounds.
$Fe_2SiO_4-Mg_2SiO_4$, the Olivine series solid solution.
The join $FeSiO_3-MgSiO_3$, this is not a binary system because $FeSiO_3$ is not a crystalline compound; the Mg SiO_3 end is composed of solid solution series of orthopyroxene and clinopyroxenes.
No ternary eutectic in system. Low temperatures on liquidus lie on $FeO-SiO_2$ boundary of composition triangle.
Reaction point Pyroxene ($MgSiO_3$), Olivine, Tridymite, liquid, 1305°C.
Reaction point Pyroxene, Cristobalite, Tridymite, liquid, 1470°C.
2 liquid region extends from $FeO-SiO_2$ to $MgO-SiO_2$ overlying Cristobalite near SiO_2 corner.
For ternary diagram, see figure 13. (Bowen and Schairer, 1935.)

$FeO-MnO-SiO_2$ No ternary compounds, no ternary eutectic, low temperature on liquidus lie at $FeO-SiO_2$ binary.
$Fe_2SiO_4-Mn_2SiO_4$ join, the Knebelite series solid solution. (Fayalite-Tephroite series.)
$FeSiO_3-MnSiO_3$ join is not a binary system, because Fe SiO_3 is not a crystalline compound; $MnSiO_3$ end is comprised of Rhodonite series solid solution.
FeO-MnO; two series solid solution with a transition point 1430°C; liquidus slopes down to boundary with the Knebelite series solid solution.
Two immiscible liquids region near SiO_2 corner extends completely from $FeO-SiO_2$ join to $MnO-SiO_2$ join, overlying Cristobalite field. (Hay, White and McIntosh, 1935; Maddocks, 1935; White, 1943.)

$FeO-Na_2O-SiO_2$ Na_2FeSiO_4, (1:1:1), melting point 976°C; reaction point with Na_2SiO_3, $Na_2Si_2O_5$ and liquid 724°C; reaction point with FeO, $Na_2Si_2O_5$ and liquid 720°C.
Liquid immiscible along $FeO-SiO_2$ border.
Lowest ternary eutectic with Fayalite, $Na_2Si_2O_5$, SiO_2 and liquid below 500°C. (Carter and Ibrahim, 1952.)

Fe_2O_3-K_2O-SiO_2

$K_2O \cdot Fe_2O_3 \cdot 6SiO_2$, (1:1:6), Iron Orthoclase, incongruent melting to (1:1:4) and liquid 920°C.

$K_2O \cdot Fe_2O_3 \cdot 4SiO_2$, (1:1:4), Iron Leucite, incongruent melting to Fe_2O_3 and liquid 1050°C. (Faust, 1936.)

Fe_2O_3-Na_2O-SiO_2

$Na_2O \cdot Fe_2O_3 \cdot 4SiO_2$, (1:1:4), Acmite, incongruent melting to Fe_2O_3 and liquid, 990°C; eutectic with $Na_2Si_2O_5$, 810°C; eutectic with (5:1:8), 817°C.

$5Na_2O \cdot Fe_2O_3 \cdot 8SiO_2$, (5:1:8), melting point 838°C; eutectic with Na_2SiO_3, 837°C, eutectic with Fe_2O_3, 816°C.

$6Na_2O \cdot 4Fe_2O_3 \cdot 5SiO_2$, (6:4:5), melting point above 1091°C.

$2Na_2O \cdot Fe_2O_3 \cdot SiO_2$, (2:1:1), melting point above 1145°C.

Liquid immiscible along Fe_2O_3-SiO_2 border. (Bowen, Schairer, and Willems, 1930.)

K_2O-Li_2O-SiO_2

$K_2O \cdot Li_2O \cdot 4SiO_2$, (1:1:4), melting point (870°C?) 820°C.

$2K_2O \cdot Li_2O \cdot 6SiO_2$, (2:1:6), melting point 815°C.

$5K_2O \cdot Li_2O \cdot 6SiO_2$, (5:1:6), melting point (880°C?) 857°C.

$5K_2O \cdot 2Li_2O \cdot 7SiO_2$, (5:2:7), melting point (900°C?) 880°C.

$5K_2O \cdot Li_2O \cdot 4SiO_2$, (5:1:4), melting point (830°C?).

The phase diagram is dominated by fields of $Li_2O \cdot SiO_2$ and SiO_2. Modified from Sheybany (1948).

K_2O-MgO-SiO_2

$K_2O \cdot 5MgO \cdot 12SiO_2$, (1:5:12), incongruent melting to Mg SiO_3 and liquid, 1174°C.

$K_2O \cdot MgO \cdot 5SiO_2$, (1:1:5), melting point 1089°C; eutectic with $K_2Si_4O_9$, 730°C; eutectic with Tridymite, 963°C; eutectic with Mg_2SiO_4, 1053°C.

$K_2O \cdot MgO \cdot 3SiO_2$, (1:1:3), melting point 1134°C; eutectic with $K_2Si_2O_5$, 933°C; eutectic with (1:1:5), 1030°C; eutectic with Mg_2SiO_4, 1131°C.

$K_2O \cdot MgO \cdot SiO_2$, (1:1:1), melting point 1650°C; eutectic with K_2SiO_3, 950°C; eutectic with $K_2Si_2O_5$, 910°C; eutectic with (1:1:3), 1110°C.

Liquid immiscible along MgO-SiO_2 border, overlying Cristobalite. (Roedder, 1951b.)

K_2O-Na_2O-SiO_2

No ternary compounds in portion of system K_2SiO_3-Na_2SiO_3-SiO_2.

K_2SiO_3-Na_2SiO_3 join, eutectic 745°C.

$K_2Si_2O_5$-$Na_2Si_2O_5$ join, limited series solid solution of $K_2Si_2O_5$; solid solution $Na_2Si_2O_5$, a minimum at 705°C; solid solution $Na_2Si_2O_5$, transition point at 742°C at the liquidus.

Eutectic $Na_2Si_2O_5$, $K_2Si_2O_5$, Quartz and liquid 540°C. Modified from Kracek (1932).

K_2O-PbO-SiO_2

$K_2O \cdot PbO \cdot 4SiO_2$, (1:1:4), melting point 757°C.

$K_2O \cdot 4PbO \cdot 8SiO_2$, (1:4:8), melting point 779°C.

$K_2O \cdot 2PbO \cdot 2SiO_2$, (1:2:2), melting point 918°C.

$2K_2O \cdot PbO \cdot 3SiO_2$, (2:1:3), incongruent melting to (1:2:2) and liquid, 806°C. (Geller and Bunting, 1936.)

K_2O-ZnO-SiO_2

$K_2O \cdot ZnO \cdot SiO_2$, (1:1:1), field of stability and melting point were not determined.

Field of Willemite intrudes between those of ZnO and SiO_2. (Ingerson and others, 1948.)

Li_2O-MgO-SiO_2

(Krishna-Murthy and Hummel, 1955.)

Li_2O-Na_2O-SiO_2	The join Na_2SiO_3-Li_2SiO_3, continuous series solid solution from Na_2SiO_3 to $NaLiSiO_3$, with a liquidus minimum, 38.5 percent Li_2SiO_3, 845°C. $NaLiSiO_3$, (1:1:2), incongruent melting to Li_2SiO_3 solid solution and liquid, 847°C. The join $Na_2Si_2O_5$-$Li_2Si_2O_5$ is not binary at liquidus because of incongruent melting of $Li_2Si_2O_5$. Lowest ternary eutectic $Na_2Si_2O_5$, $Li_2Si_2O_5$ and Quartz, 637°C. (Kracek, 1939a, b.)
Li_2O-ZrO_2-SiO_2	$4Li_2O \cdot 3ZrO_2 \cdot 5SiO_2$, (4:3:5), melting point 1152°C. (Schwarz, 1921.)
MgO-TiO_2-SiO_2	Incomplete study. Liquidus has a minimum below 1500°C. (Berezhnoi, 1950; Massazza and Sirchia, 1958.)
MgO-ZrO_2-SiO_2	Compatibility triangles outlined. (Foster, 1951b.)
MnO-TiO_2-SiO_2	$MnSiO_3$-$MnTiO_3$, eutectic, 22.3 mole percent $MnTiO_3$, 1120°C; solid solution limit 38 to 100 mole percent $MnTiO_3$. (Smolensku, 1912.)
Na_2O-PbO-SiO_2	$Na_2O \cdot 2PbO \cdot SiO_2$, (1:2:1), melting point 840°C; transition point 790°C; β decomposes to PbO and Na_2SiO_3, 590°C. $Na_2O \cdot 3PbO \cdot 6SiO_2$, (1:3:6). $Na_2O \cdot 2PbO \cdot 3SiO_2$, (1:2:3), melting point 615°C. $Na_2O \cdot 3PbO \cdot 7SiO_2$, (1:3:7). $3Na_2O \cdot 3PbO \cdot 11SiO_2$, (3:3:11). (Krakau and others, 1937; Grebenshchikov, 1949.)
Na_2O-P_2O_5-SiO_2	$5Na_2O \cdot P_2O_5 \cdot 4SiO_2$, (5:1:4), incongruent melting to (9:2:6) and liquid, 953°C. $9Na_2O \cdot 2P_2O_5 \cdot 6SiO_2$, (9:2:6), melting point 1100°C. $15Na_2O \cdot 5P_2O_5 \cdot 6SiO_2$, (15:5:6), incongruent melting to (9:2:6) and liquid, 987°C. Two liquids over Cristobalite in SiO_2-P_2O_5 rich region. (Turkdogan and Maddocks, 1952.)
Na_2O-ZrO_2-SiO_2	Na_2O-SiO_2 rich portion of system investigated to 1100°C, disclosing fields of Na_4SiO_4, $Na_6Si_2O_7$, Na_2SiO_3, Na_2ZrO_3, Na_2ZrSiO_5 and $Na_4Zr_2Si_3O_{12}$. (d'Ans and Löffler, 1930.)
TiO_2-Ti_2O_3-SiO_2	Exploratory study. (Roy, Rustum, and others, 1952.)
TiO_2-ZrO_2-SiO_2	No ternary compounds. Ternary eutectic SiO_2, TiO_2, ZrO_2 and liquid, 1500°C. (Sowman and Andrews, 1951; McTaggart and Andrews, 1957.)

Additional References

Al_2O_3-B_2O_3-SiO_2	Dietzel and Scholze (1955).
Al_2O_3-SrO-SiO_2	Dear (1957).
B_2O_3-P_2O_5-SiO_2	Horn and Hummel (1955).
CaO-CaF_2-SiO_2	$3CaO \cdot CaF_2 \cdot 2SiO_2$, Cuspidine, Brisi (1957).
CaO-Cr_2O_3-SiO_2	Glasser and Osborn (1958).

690-216 O - 63 - 5

$MgO-MnO-SiO_2$	Glasser (1958b).
$PbO-P_2O_5-SiO_2$	Paetsch and Dietzel (1956).
$SrO-ZrO_2-SiO_2$	Dear (1958).

SILICATE SYSTEMS, QUATERNARY AND HIGHER

$Al_2O_3-CaO-Cr_2O_3-MgO-SiO_2$	7 percent R_2O_3 plane ($75MgO \cdot Al_2O_3$, $25MgO \cdot Cr_2O_3$) parallel to the $CaO-MgO-SiO_2$ base. 7 percent R_2O_3 plane ($50MgO \cdot Al_2O_3$, $50MgO \cdot Cr_2O_3$) parallel to the $CaO-MgO-SiO_2$ base. (Berry, Allen and Snow, 1950; also Warshaw and Keith, 1954.)
$Al_2O_3-CaO-FeO-SiO_2$	Study of several joins in the quaternary system: (a) $FeO-Al_2O_3-CaAl_2Si_2O_8$, Anorthite; (b) $FeO-SiO_2-CaAl_2Si_2O_8$, see figure 14; (c) $FeO-CaSiO_3-CaAl_2Si_2O_8$; (d) $FeO-CaSiO_3-Ca_2Al_2SiO_7$, Gehlinite; (e) $FeO-Ca_2Al_2SiO_7-CaAl_2Si_2O_8$; (f) $FeO-Ca_2Al_2SiO_7$; (g) $FeO-Ca_2SiO_4-Ca_2Al_2SiO_7$; (h) $Ca_2Al_2SiO_7-Ca_2FeSi_2O_7$, Iron Akermanite. (Schairer, 1942; Muan and Osborn, 1951.)
$Al_2O_3-CaO-Fe_2O_3-SiO_2$	0, 2, 5, 10 and 20 percent Fe_2O_3 planes parallel to base $CaO-Ca_2SiO_4-5CaO \cdot 3Al_2O_3$. (Lea and Parker, 1934; Swayze, 1946a, b.)
$Al_2O_3-CaO-Fe_2O_3-MgO-SiO_2$	$CaO-5CaO \cdot 3Al_2O_3-2CaO \cdot Fe_2O_3-Ca_2SiO_4$; modified by 5 percent MgO. (Swayze, 1946a, b.)
$Al_2O_3-CaO-K_2O-SiO_2$	$CaO-5CaO \cdot 3Al_2O_3-K_2O \cdot 23CaO \cdot 12SiO_2$; (Taylor, 1942.) $KAlSi_2O_6$, Leucite-$CaAl_2Si_2O_8$, Anorthite-SiO_2; see figure 15. (Schairer and Bowen, 1947a, b.)
$Al_2O_3-CaO-K_2O-MgO-SiO_2$	$KAlSi_2O_6$, Leucite-$CaMgSi_2O_6$, Diopside-SiO_2; see figure 16. $KAlSi_2O_6-CaMgSi_2O_6$ binary section. (Bowen and Schairer, 1929; Bowen, 1937.)
$Al_2O_3-CaO-K_2O-Na_2O-SiO_2$	$NaAlSi_3O_8$, Albite-$KAlSi_3O_8$ Potash Feldspar-$CaAl_2Si_2O_8$ Anorthite; see figure 17. (Franco and Schairer, 1951.)
$Al_2O_3-CaO-MgO-SiO_2$	$CaO-MgO-5CaO \cdot 3Al_2O_3-Ca_2SiO_4$, with 0 and 5 percent MgO. (McMurdie and Insley, 1936.) $SiO_2-Mg_2SiO_4$, Forsterite-$CaAl_2Si_2O_8$, Anorthite. See figure 18. (Andersen, 1915.) $CaSiO_3-CaMgSi_2O_6$, Diopside-$CaAl_2Si_2O_8$ Anorthite. (Osborn, 1942.) $Ca_2Al_2SiO_7$, Gehlinite-$Ca_2MgSi_2O_7$, Akermanite, binary solid solution. (Osborn and Schairer, 1941; Ferguson and Buddington, 1920.) $CaSiO_3-Ca_2Al_2SiO_7-Ca_2MgSi_2O_7$. (Osborn and Schairer, 1941.)

	$CaMgSi_2O_6$, Diopside-$CaAl_2Si_2O_8$, Anorthite-Mg_2SiO_4, Forsterite; see figure 19. (Osborn and Tait, 1952.)
	MgO-Ca_2SiO_4-$MgO \cdot Al_2O_3$, Spinel. (Prince, 1951.)
	$MgO \cdot Al_2O_3$-Ca_2SiO_4-$Ca_2Al_2SiO_7$, Gehlinite. (Prince, 1951.)
	MgO-Al_2O_3-Ca_2SiO_4. (Prince, 1951.)
	10 percent MgO plane. (Prince, 1954.)
	$CaAl_2Si_2O_8$, Anorthite-$Ca_2MgSi_2O_7$, Akermanite. (DeWys and Foster, 1956; Prince, 1954.)
Al_2O_3-CaO-MgO-Na_2O-SiO_2	$NaAlSi_3O_8$, Albite-$CaAl_2Si_2O_8$, Anorthite-$CaMgSi_2O_6$, Diopside; see figure 20. (Bowen, 1915.)
	$CaMgSi_2O_6$-$NaAlSiO_4$, Nepheline, Carnegieite. (Bowen, 1922.)
	$CaMgSi_2O_6$-$NaAlSiO_4$-$NaAlSi_3O_8$, Albite, a portion of $CaMgSi_2O_6$-$NaAlSiO_4$-SiO_2. (Yoder, 1950, and from the unpublished work of Schairer.)
Al_2O_3-CaO-Na_2O-SiO_2	Na_2SiO_3-$CaSiO_3$-$NaAlSiO_4$, Nepheline-$CaAl_2Si_2O_8$, Anorthite. (Spivak, 1944.)
	$CaSiO_3$-$NaAlSiO_4$-$CaAl_2Si_2O_8$. (Gummer, 1943.)
Al_2O_3-CaO-Na_2O-P_2O_5-SiO_2	(Melent'ev and Ol'shanskiy, 1952.)
Al_2O_3-CaO-Na_2O-TiO_2-SiO_2	$NaAlSi_3O_8$, Albite-$CaAl_2Si_2O_8$, Anorthite-$CaTiSiO_5$, Titanite. (Prince, 1943.)
Al_2O_3-FeO-Fe_2O_3-SiO_2	(Muan, 1957a, 1958b.)
Al_2O_3-CaO-P_2O_5-SiO_2	$Ca_3(PO_4)_2$-Al_2O_3-SiO_2. (St. Pierre, 1953; Hartmann and Haegermann, 1953.)
Al_2O_3-CaO-TiO_2-SiO_2	$CaSiO_3$-$CaAl_2Si_2O_8$, Anorthite-$CaTiSiO_5$, Titanite. (Iwase and Nisioka, 1936.)
Al_2O_3-FeO-Fe_2O_3-SiO_2	Projection of the curved surface bounding mixtures that form 2 liquid layers, onto the FeO-Fe_2O_3-SiO_2 base. (Greig, 1927b; Muan, 1957a, b, 1958a, b, c); Muan and Gee, 1956.)
Al_2O_3-FeO-Na_2O-SiO_2	FeO-SiO_2-$NaAlSiO_4$, Nepheline. See figure 21. (Bowen, 1937.)
Al_2O_3-FeO-K_2O-SiO_2	$KAlSi_2O_6$, Leucite-Fe_2SiO_4, Fayalite-SiO_2. See figure 22. (Roedder, 1951a.)
Al_2O_3-K_2O-MgO-SiO_2	$KAlSi_2O_6$, Leucite-Mg_2SiO_4, Forsterite-SiO_2 ternary system. See figure 23.
	Mg_2SiO_4-$KAlSi_2O_6$-$Mg_2Al_4Si_5O_{18}$, Cordierite.
	$KAlSi_2O_6$-$Mg_2Al_4Si_5O_{18}$-SiO_2.
	$MgSiO_3$-$KAlSi_2O_6$-$Mg_2Al_4Si_5O_{18}$.
	$Mg_2Al_4Si_5O_{18}$-$KAlSi_3O_8$, Potash Feldspar-$3Al_2O_3 \cdot 2SiO_2$, Mullite. (Schairer, 1954, 1955.)

Al_2O_3-K_2O-Na_2O-SiO_2	$NaAlSiO_4$, Nepheline, Carnegieite-$KAlSiO_4$, Kaliophilite, Kalsilite-SiO_2. See figure 24. (Schairer, 1950.)
	$NaAlSiO_4$-$KAlSiO_4$; Nephelite-Carnegieite transition point is raised by solid solution from 1248° to 1404°C; Nephelite solid solution - Kaliophilite transition point is raised from 1540° to 1580°C. (Bowen, 1917.)
	$KAlSi_3O_8$-$NaAlSi_3O_8$. (Schairer, 1950); Structure study (Smith and Tuttle, 1957.)
Al_2O_3-Li_2O-MgO-SiO_2	$Mg_2Al_4Si_5O_{18}$, Cordierite-$LiAlSi_2O_6$, Spodumene. (Karkhanavala and Hummel, 1953; Prokopowitz and Hummel, 1956.)
Al_2O_3-MgO-ZrO_2-SiO_2	No quaternary compounds. (Herold and Smothers, 1954.)
Al_2O_3-MnO-Y_2O_3-SiO_2	$Mn_3Al_2Si_3O_{12}$, Spessartite-$Y_6Al_{10}O_{24}$, Yttrogarnet; system illustrates complete substitution of Al for Si. (Yoder and Keith, 1951.)
B_2O_3-CaO-Na_2O-SiO_2	Effects of additions of 1 and 5 percent B_2O_3 on the liquidus for Devitrite, $Na_2Ca_3Si_6O_{16}$. (Morey, 1932.)
CaO-FeO-MgO-SiO_2	$CaSiO_3$-$CaMgSiO_4$, Monticellite-FeO, fields of Magnesiowustite, Olivine Melilite and Ca SiO_3, Pseudowollastonite; all fields except $CaSiO_3$ are solid solution. (Schairer and Osborn, 1950.)
CaO-Fe_2O_3-MgO-SiO_2	(Rait, 1949.)
CaO-MgO-MnO-TiO_2-SiO_2	$CaMgSi_2O_6$, Diopside-$MnTiO_3$; (Iwase and Nisioka, 1938.)
CaO-MgO-TiO_2-SiO_2	(Berezhnoy, 1950; Iwase and Nisioka, 1938; Nisioka, 1935.)
CaO-MnO-SiO_2-SiO_2	(Iwase and Nisioka, 1936.)
FeO-Fe_2O_3-MgO-SiO_2	(Muan and Osborn, 1956.)
	Additional Systems
Al_2O_3-CaO-P_2O_5-SiO_2	$Ca_3(PO_4)_2$-$CaAl_2Si_2O_8$, Anorthite-SiO_2 section. (St. Pierre, 1956.)
CaO-MgO-P_2O_5-SiO_2-CaF_2	$3Ca_3(PO_4)_2 \cdot CaF_2$-$MgSiO_3$-$SiO_2$ section. (Bobrownicki and Swiecki, 1955.)
CaO-MgO-P_2O_5-SiO_2	$Ca_3(PO_4)_2$-$MgSiO_3$-SiO_2 section. (Sata, 1958.)
MgO-Fe_2O_3-TiO_2-SiO_2	(Rao, 1957.)

SILICATES, MISCELLANEOUS

$CaSiO_3$-CaF_2	Eutectic, 47 mole percent CaF_2, 1128°C. (Karandeeff, 1910; Boak and Olander, 1955.)

$FeO-FeS-SiO_2$	$FeS-SiO_2$, liquid immiscible, 5 to 95 percent SiO_2 over Cristobalite, 1690°C. FeO-FeS, eutectic 36 percent FeO, 920°C. Ternary eutectic FeO, Fe_2SiO_4, FeS, below 920°C. (Ol'shanskiy, 1950.)
$NaF-Na_2O-SiO_2$	Na_2SiO_3-NaF, eutectic, 39 mole percent NaF, 795°C. (Booth and others, 1933.)
$CaO-Na_2O-SO_3-SiO_2$	$SiO_2-Na_2SiO_3-CaSiO_3-Na_2SO_4-CaSO_4$, solubility relations at 1200°C. $Na_2SiO_3-Na_2SO_4$, eutectic 7 percent Na_2SO_4, 868°C. (Kordes and others, 1951.)
$Na_2SiO_3-Na_2WO_4$	Na_2SiO_3 in equilibrium with 2 liquids, 14 to 99 percent Na_2SiO_3, 1080°C; eutectic near 100 percent Na_2WO_4, 696°C. (Tammann, 1925.)

CARBONATES

Ag_2CO_3	Dissociates (1 atm CO_2) 219°C. (Drake and Benton, 1934; Watanabe, 1933; Centnerszwer, and Krustinsons, 1926.)
$CaCO_3$	Witherite, melting point (90 atm CO_2) 1740°C; dissociates 0.068 atm CO_2, 1204°C; transition points 806°C, 968°C. (Dutoit, 1927; Finkelstein, 1906; Lander, 1949, 1951a.)
$BaCO_3 \cdot BaO$	(Finkelstein, 1906); existence disproved by Lander (1951.)
$BaK_2(CO_3)_2$	Melting point 800°C. (Le Chatelier, 1887.)
$CaNa_2(CO_3)_2$	Melting point 740°C. (Le Chatelier, 1887.)
$CaCO_3-CaCO_3$	Melting diagram. (Boeke, 1913.)
$BeCO_3 \cdot 4H_2O$	Decomposes with loss of H_2O, 100°C.
$CaCO_3$	Calcite, melting point (1038) bars CO_2), 1339°C; eutectic of $CaCO_3$, CaO plus liquid (40 bars CO_2), 50 mole percent CaO, 1240°C; dissociates (1 atm CO_2), 897°C; dissociation pressure at higher temperature, log P(bars CO_2) $= \frac{-11,355}{T(°K)} - 5.388 \log T$ (°K) + 26.244. Heat of dissociation calculated 39.44 kcal per mol at 898.6°C and 35.79 kcal per mol at 1240°C; transition point 970°C found by Boeke (1912) may not exist. (Smyth and Adams, 1923; Johnston, 1910; Boeke, 1912; Harker and Tuttle (1955) observed higher pressure, lower temperatures in dissociates. Aragonite metastable at room temperature and above, inverts to Calcite about 425°C at 1 atmosphere pressure; reversible transition point Calcite-Aragonite P(bars) = 16 T (°C) + 1400, MacDonald (1956); P(bars) = 17 T (°C) + 3600, Clark (1957); agrees with value calculated for 1 bar pressure, −195°C (79°K) from Jamieson (1953). Vaterite, transition to Calcite from 430° to 440°C.

$CaCO_3$-K_2CO_3	(Kröger and others, 1943.)
$CaCO_3$-Na_2CO_3-K_2CO_3	1 atm CO_2 isotherms. (Niggli, 1919.)
$CaK_2(CO_3)_2$	Melting point 814°C.
$CaCO_3$-Li_2O	(Eitel and Skaliks, 1929.)
$CaNa_2(CO_3)_2$	Melting or decomposition, (54.2 atm CO_2), 812°C; eutectic with (Na_2, Ca) CO_3 solid solution, 38 percent $CaCO_3$, 805°C. (Eitel, 1925; Niggli, 1916.)
(Ca, Fe, Mg, Mn)CO_3	Ankerite, dissociates in two steps, 610° to 770°C and 900°C.
CaO-MgO-CO_2	$CaO \cdot MgO \cdot (CO_2)_2$, Dolomite, dissociates to $CaCO_3$, MgO, CO_2 at 1 atm CO_2, about 500°C; to CaO, MgO, CO_2 at 890°C. High CO_2 pressure equilibrium was measured for dissociation of Dolomite to Magnesian Calcite+ MgO+CO_2 to 20,000 psi(1378 bars)875°C, Graf and Goldsmith (1955), revised in Graf and Goldsmith (1958); measured to 40,000 psi(2756 bars), 940°C. (Harker and Tuttle, 1955.) Magnesian Calcite, solid solution of Mg in Calcite. Excess Ca solid solution in Dolomite. Solid solution Ca in Magnesite, determined up to 900°C at pressure high enough to prevent dissociation. Details given in Graf and Goldsmith (1955) and Harker and Tuttle (1955).
$CaCO_3 \cdot NaAlSiO_4$	Cancrinite, artificial, incongruent melting to Nepheline and liquid, (107 atm CO_2), 1253°C. (Eitel, 1925).
CaO-MnO-CO_2	A complete series of solid solution exists from Ca CO_3 to $MnCO_3$ at temperatures above 550°C and pressures sufficient to prevent dissociation. (75.9 bars at 550°C rising to 1550 bars at 750°C for dissociation of $MnCO_3$). Unmixing of these solid solutions is observed in the $MnCO_3$-rich region below 550°C. One limb of the solvus approaches the 1:1 composition, the other limb 80 mole percent $MnCO_3$, as temperature falls to 450°C. Below 400°C no equilibrium is attained either in hydrothermal runs or in presence of Li_2CO_3 as flux. Kutnahorite, $CaMn(CO_3)_2$, is a phase in which the random arrangement of Ca ions and Mn ions of the solid solution is replaced by an ordered one with Ca and Mn in alternate layers of the lattice. This phase becomes disordered at temperatures above 450°C. The heat of dissociation of $MnCO_3$ is calculated to be 26.0±0.4 kcal per mol. (Goldsmith and Graf, 1957.)
$CaCO_3 \cdot 2Ca_2SiO_4$	Spurrite, incongruent melting to Ca_2SiO_4 plus liquid, (122 atm CO_2), 1380°C. Artificial differs from natural mineral. Transition natural to artificial (120 atm CO_2), 1200°C., (Eitel, 1923.)

	Mixture $5CaCO_3 \cdot 2SiO_2$ crystallized readily to Spurrite at 172 bars CO_2, 950°C; equilibrium values along $P(CO_2)$ –T curve were measured from 25 to 310 bars, 700° to 1000°C. Tilleyite, $2CaCO_3 \cdot Ca_3Si_2O_7$, did not crystallize in above experiments. (Tuttle and Harker, 1957.)
$CdCO_3$	Otavite, dissociation, (1 atm CO_2), 344°C. (Andrussov, 1925; Centnerszwer, 1930; Jander, 1928.)
$CoCO_3$	Spherocobaltite, dissociation to basic carbonates. (Krustinsons, 1933.)
$CuCO_3$	Appears to be unstable relative to CuO and CO_2. (Maier, 1929; Kelley and Anderson, 1935.)
$Cu_3(OH)_2(CO_3)_2$	Azurite, decomposes about 200°C.
$FeCO_3$	Siderite, dissociation (1 atm CO_2) 450°C. (Fleissner, 1925; Friedrich and Smith, 1912.)
K_2CO_3	Melting point 895°C, 422°C; vapor pressure of liquid 0.047 atmosphere at 1400°C. (Howarth and Turner, 1931.)
K_2CO_3-Li_2CO_3	(Eitel and Skaliks, 1929.)
K_2CO_3-Na_2CO_3	(Reisman, 1959.)
Li_2CO_3	Melting point 735°C, 401°C; vapor pressure of liquid 0.177 atmosphere at 1100°C. (Howarth and Turner, 1931.)
$LiNaCO_3$	Melting point 514°C; eutectic with Na_2CO_3, 61 percent Na_2CO_3, 510°C; eutectic with Li_2CO_3, 44 percent Li_2CO_3, 510°C. (Eitel and Shaliks, 1929.)
$MgCO_3$	Magnesite, conflicting data on dissociation, dissociates to basic carbonates, (Centnerszwer and Bruzs, 1925); basic carbonates disproved on X-ray evidence, (Huttig and Frankenstein, 1930); most consistent dissociation pressure measurements by Marc and Simek (1913); (1 atm CO_2), 404°C. (Kelley and Anderson, 1935.) High temperature and pressure equilibrium studied up to 40,000 psi (2750 bars), about 900°C by Harker and Tuttle (1955).
$MgCO_3 \cdot 3H_2O$	Nesquehonite, prepared by treating $MgCl_2$ solution at 14°C with K_2CO_3 solution. Loses $1H_2O$ over H_2SO_4 at room temperature; dried at 100°C, 150°C, 200°C with increasing loss of H_2O and some CO_2. (Menzel, Bruckner, Schultz, 1930.)
$MgNa_2(CO_3)_2$	Melting point at 124 atm CO_2, 677°C. (Eitel and Skaliks, 1929.)
$MnCO_3$	Rhodochrosite, dissociates 1 atm CO_2, 369°C. (Krustinsons, 1932, 1933.) Dissociation curve to high pressure CO_2 from 375° to 575°C is given by $\log P(\text{bars}) = \frac{5740}{T(°K)} + 8.852$, and from 575° to 775°C by

	$\log P(\text{bars}) = \frac{-10,320}{T(°K)} - 11.910 \log T(°K) + 49.127$. The calculated heat of dissociation is 26.0±0.4 kcal per mol. (Goldsmith and Graf, 1957.)
Na_2CO_3	Melting point 851°C; transition points 361°C, 489°C; vapor pressure of liquid 0.085 atmosphere, 1400°C. (Howarth and Turner, 1930.)
Na_2CO_3-Na_2S	Eutectic 38 percent Na_2S, 756°C. (Tammann and Oelsen, 1930.)
$PbCO_3$	Cerrusite, dissociates to basic carbonates. (Centnerszwer, Falk and Awerbach, 1925; Bružs, 1926; Colson, 1905, 1909.) 1 atm CO_2, 293°C. Kelley and Anderson, 1935; Peretti, 1957.)
$2PbCO_3 \cdot PbO \cdot H_2O$	Hydrocerrusite, decomposes below 400°C.
$SrCO_3$	Strontianite, melting point (60 atm CO_2), 1497°C; dissociate, 0.152 atm CO_2. 1091°C; transition rhombic to trigonal, 925°C. (Dutoit, 1927; Lander, 1951a; Rossini and others, 1952.)
$ZnCO_3$	Smithsonite, sluggish dissociation (1 atm CO_2), varies from 300° to 400°C. (Centnerszwer, 1930; Friedrich, 1911.)
	$P(CO_2)$-T curve passes through 689 bars at 310°C, 2067 bars at 410°C, and 3445 bars at 460°C. (Harker and Hutta, 1956.)

SYSTEM, MISCELLANEOUS

In this section are included references not elsewhere covered for systems of oxides and other substances of interest in synthetic studies.

(a) Three oxides:

Al_2O_3-BeO-MgO	(Geller, Yavorsky, Steierman, and Creamer, 1946.)
Al_2O_3-BeO-ThO_2	- - - - - - - - - - - - - - - do - - - - - - - - - - - - - -
Al_2O_3-BeO-TiO_2	(Lang, Fillmore, and Maxwell, 1952.)
Al_2O_3-BeO-ZrO_2	(Geller, Yavorsky, Steierman, and Creamer, 1946.)
Al_2O_3-CaO-Cr_2O_3	(Vasenin, 1939.)
Al_2O_3-CaO-Fe_2O_3	(Hansen, Brownmiller, and Bogue, 1928; McMurdie, 1937; Swayze, 1946a, b.)
Al_2O_3-CaO-K_2O	Al_2O_3-3CaO·Al_2O_3-K_2O·Al_2O_3 (Brownmiller, 1935.)
Al_2O_3-CaO-P_2O_5	(Stone, Egan, and Lehr, 1956; St. Pierre, 1956.)
Al_2O_3-Cr_2O_3-MgO	(Wilde and Rees, 1943.)
Al_2O_3-FeO-MnO	(Hay, McIntosh, Rait, and White, 1937.)
Al_2O_3-MgO-ZrO_2	(Salldau and Zhirmova, 1945.)
BeO-CeO_2-ZrO_2	(Ruff, Ebert and Loerpabel, 1932; Lang, Roth, and Fillmore, 1954.)
BeO-Cr_2O_3-ZrO_2	(Lang, Roth, and Fillmore, 1954.)

(a) Three oxides Continued:

$BeO-MgO-ThO_2$	(Lang, Maxwell, and Geller, 1949.)
$BeO-MgO-ZrO_2$	- - - - - - - - - - do - - - - - - - - - -
$BeO-TiO_2-ZrO_2$	(Lang, Roth, and Fillmore, 1954.)
$Bi_2O_3-MoO_3-PbO$	(Zambonini, 1920.)
$Bi_2O_3-PbO-WO_3$	- - - - do - - - - -
$CaO-Cr_2O_3-MgO$	(Ford and Rees, 1949.)
$CaO-Fe-Fe_2O_3$	(Martin and Vogel, 1932; White, 1943.)
$CaO-FeO-Fe_2O_3$	(Krings and Shackmann, 1935; White, 1938; Gurry and Darken, 1950.)
$CaO-Fe_2O_3-Fe_3O_4$	(Burdese and Brisi, 1952.)
$CaO-MgO-SnO_2$	(Coughanour and others, 1955.)
$CaO-MgO-TiO_2$	- - - - - - - - - do - - - - - - - - -
$CaO-ThO_2-Z_2O_2$	(Ruff, Ebert, and Loerpabel, 1932.)
$Cr_2O_3-MoO_3-PbO$	(Jaeger and Germs, 1921.)
$Cr_2O_3-PbO-WO_3$	- - - - - - do - - - - - - -
$FeO-Fe_2O_3-MgO$	(Roberts and Merwin, 1931.)
$FeO-Fe_2O_3-Mn_xO_y$	(Gurry and Darken, 1950.)
$FeO-MnO-TiO_2$	(Grieve and White, 1940.)
$MgO-SnO_2-TiO_2$	(Coughanour and others, 1955.)
$MgO-ThO_2-ZrO_2$	(Ruff, Ebert, and Loerpabel, 1932.)
$PbO-TiO_2-V_2O_5$	(Belyayev and Nesterova, 1952.)

(b) Four or more oxides:

$Al_2O_3-CaO-Fe_2O_3-K_2O$	(Taylor, 1938.)
$Al_2O_3-CaO-Fe_2O_3-Na_2O$	(Eubank and Bogue, 1948.)
$Al_2O_3-CaO-Fe_2O_3-MgO$	(Rait, 1949.)
$BaO-Na_2O-Nb_2O_3-TiO_2$	(Roy, Rustum, and others, 1953.)
$CaO-MgO-SnO_2-TiO_2$	(Coughanour and others, 1955.)

(c) Phosphates:

P_2O_5	(Hill, Faust, and Hendricks, 1943.)
$CaO-P_2O_5$	(Trömel, 1943; Hill, Faust, and Reynolds, 1944.)
$CaO-FeO-P_2O_5$	(Oelsen and Maetz, 1941.)
$CaO-Na_2O-P_2O_5$	$CaP_2O_6-Na_2P_2O_6$. (Morey, 1952.)
$Fe_2O_3-P_2O_5$	(Wentrup, 1936.)
$K_2O-Li_2O-P_2O_5$	KPO_3-LiPO_3 (Bergmann and Sholokovich, 1953.)
$K_2O-P_2O_5-SO_3$	$K_2SO_4-K_2P_2O_6$. (Bergmann and Sholokovich, 1953.)

690-216 O - 63 - 6

(c) Phosphates Continued:

Li_2O-P_2O_5-SO_3	$Li_2P_2O_6$-Li_2SO_4. (Bergmann and Sholokhovich, 1953.)
Na_2O-P_2O_5	(Turkdogan and Maddocks, 1952; Morey and Ingerson, 1944.)
Al_2O_3-CaO-Na_2O-P_2O_5-SiO_2	(Melent'ev and Ol'shanskiy, 1952.)

(d) Sulfates:

CuO-K_2O-Na_2O-SO_3	(Bellanca and Carapezza, 1951.)
K_2SO_4-$CaSO_4$	- - - - - - - - - do - - - - - - - - -
K_2SO_4-Li_2SO_4	(Nacken, 1907.)
K_2O-PbO-SO_3-WO_3	(Belyayev and Nesterova, 1952.)
Li_2SO_4-$MgSO_4$	(Rea, 1938.)
Li_2SO_4-Na_2SO_4	(Nacken, 1907.)
Na_2SO_4-$CuSO_4$	(Bellanca and Carapezza, 1951.)
Na_2O-PbO-SO_3-WO_3	(Belyayev, 1952.)
PbO-$PbSO_4$	(Jaeger and Germs, 1921.)
$PbSO_4$-$PbCrO_4$	- - - - - - - - do - - - - - - -
$PbSO_4$-$PbMoO_4$	- - - - - - - - do - - - - - - -
$PbSO_4$-$PbWO_4$	- - - - - - - - do - - - - - - -

(e) Fluorides of interest for model systems:

BeF_2-NaF	(Thilo and Schröder, 1951; Roy, D. M., and others, 1953.)
BeF_2-PbF_2	(Roy, D. M., and others, 1954.)
KF-MgF_2	(DeVries and Roy, 1953.)
KF-ThF_4	(Asker and others, 1952.)
LiF-MgF_2	(Bergmann and Dergunov, 1941; Counts and others, 1953.)

(f) Oxides, halides:

Al_2O_3-CaF_2	(Pascal, 1913.)
Al_2O_3-CaF_2-CaO	(Eitel, 1938a, b.)
Al_2O_3-CaF_2-Na_3AlF_6	(Pascal, 1913.)
Al_2O_3-Na_3AlF_6	(Pascal, 1913; Drossbach, 1936.)
CaF_2-CaO	(Eitel, 1938b.)
CaF_2-CaO-Ca_2SiO_4	- - - - do - - - -
$CaCO_3$-Na_2CO_3-Na_2Cl_2	(Niggli, 1916.)

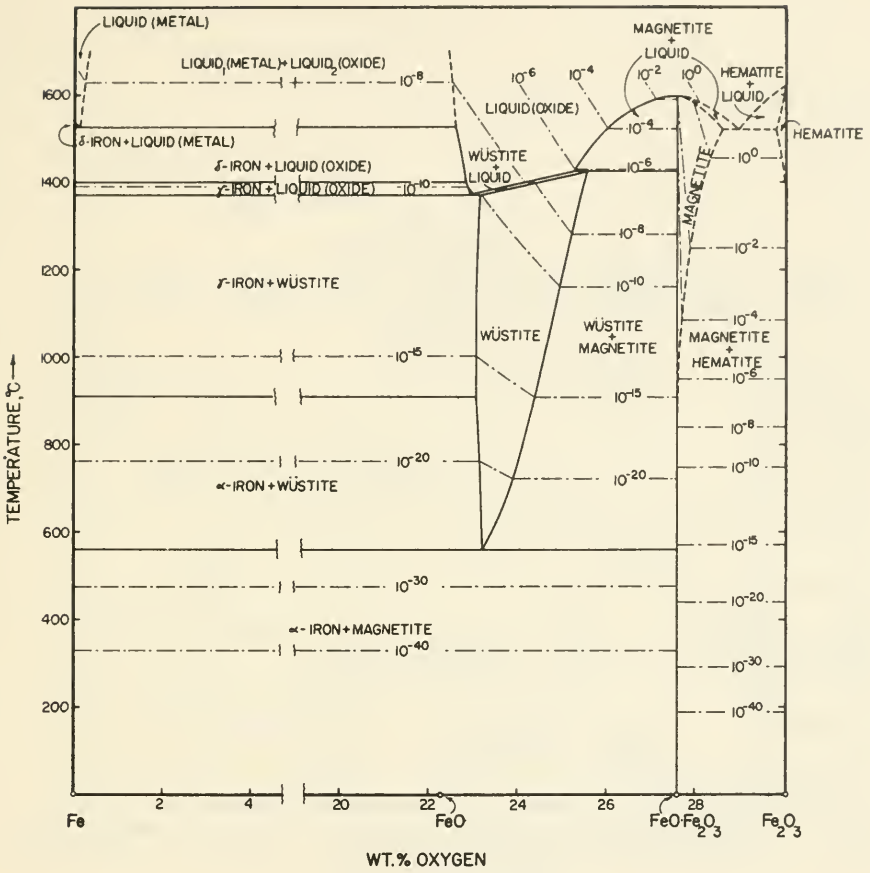

Figure 1.— The system: Fe-O. From Muan (1958d), reprinted by permission of the American Journal of Science; data are mainly from Darken and Gurry (1945, 1946). Solid lines are boundary curves separating phase areas labelled in the diagram; dash-dot curves are oxygen isobars in atmospheres. Boundary curves in the upper part of the figure are dashed where experimental data are lacking; in the upper right corner, dashed curves are inferred for oxygen pressures greater than 1 atmosphere.

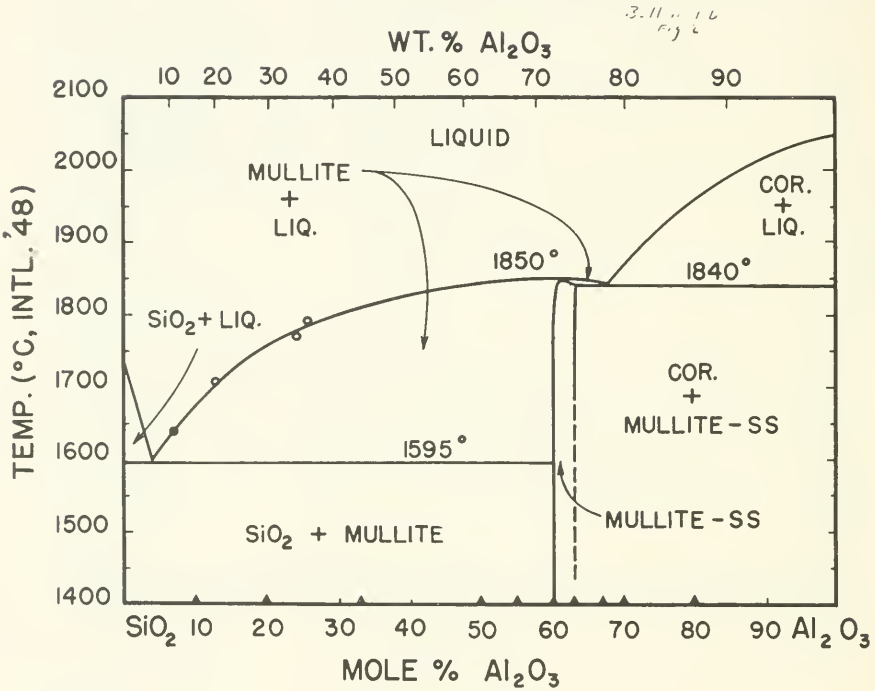

Figure 2.— The system: SiO_2-Al_2O_3. From Shigeo Aramaki and Rustum Roy (written communication, 1959), showing the incongruent melting of mullite.

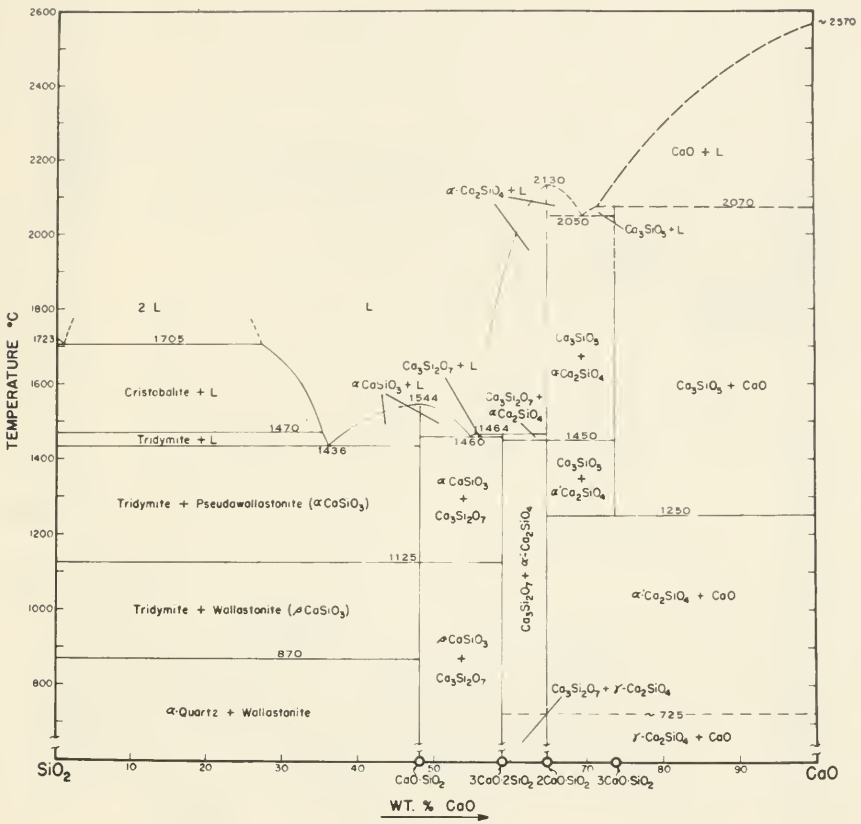

Figure 3.– The system: SiO_2-CaO. From Phillips and Muan (1958) reprinted by permission of the American Ceramic Society. Composite diagram based on Rankin and Wright (1915), Greig (1927a), Glasser and Osborn (1958), D. M. Roy (1958), and Welch and Gutt (1959).

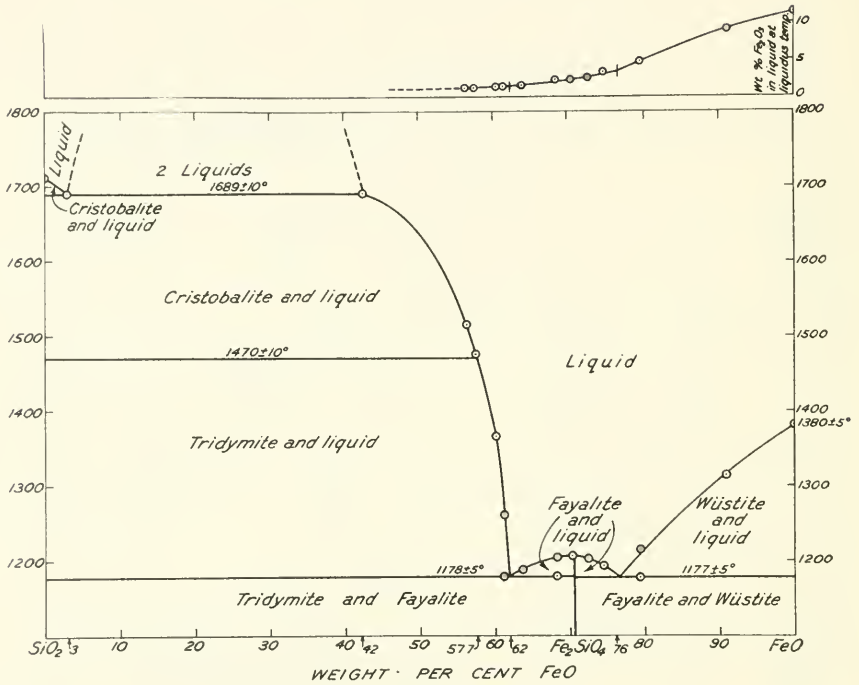

Figure 4.— The system: SiO_2-FeO. From Bowen and Schairer (1932); reprinted by permission of the American Journal of Science. The system is binary only when small amounts of Fe_2O_3 in the liquids are disregarded.

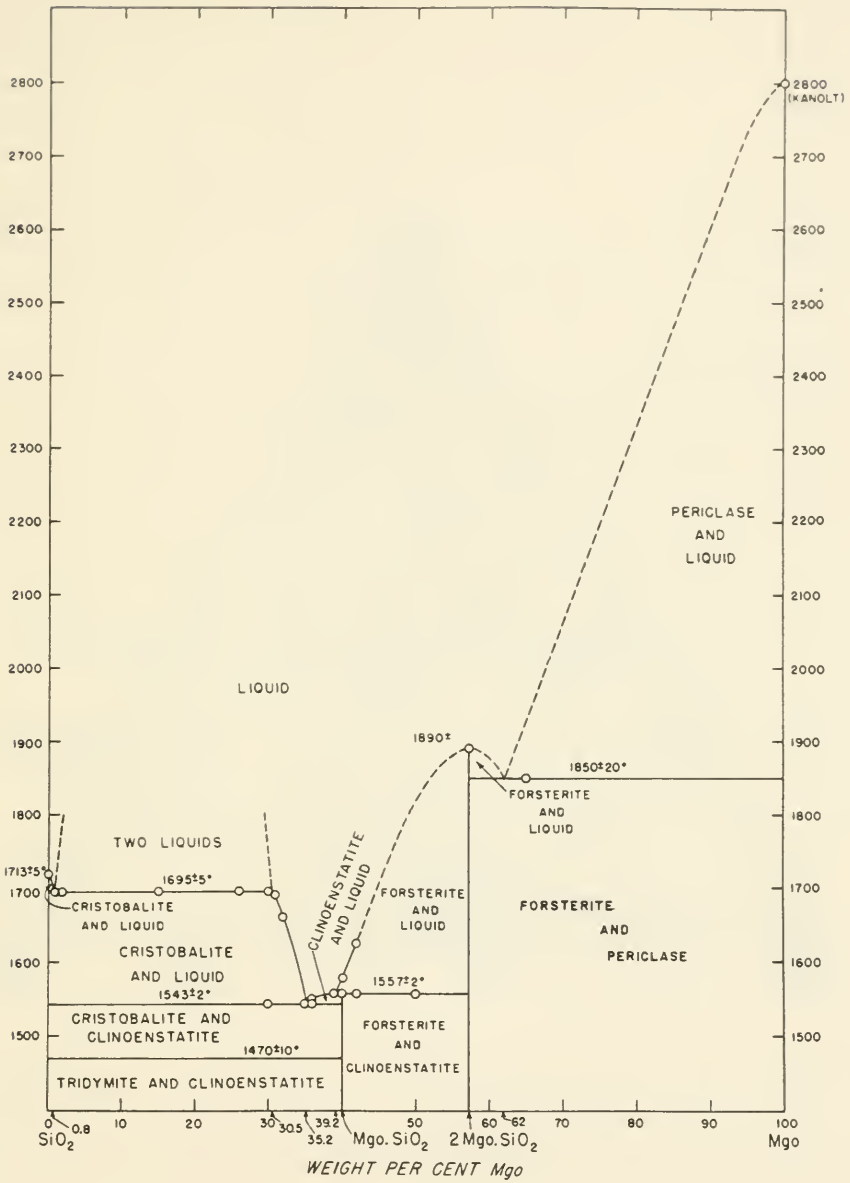

Figure 5.— The system: SiO_2-MgO. From J. W. Greig (written communication, 1958); based on Bowen and Andersen (1914) and Greig (1927a).

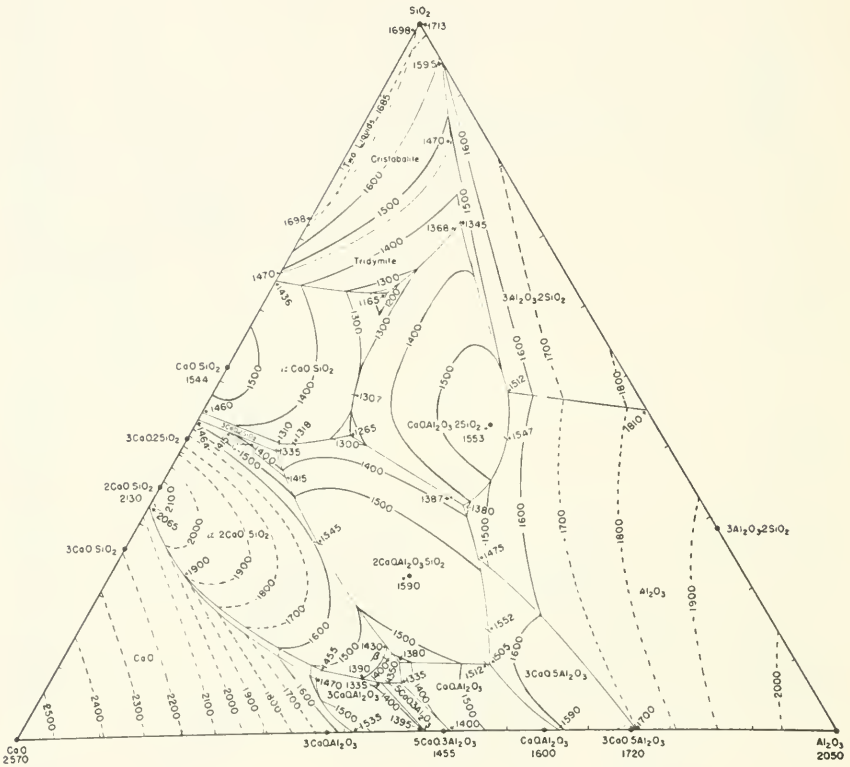

Figure 6.– The system: CaO-Al_2O_3-SiO_2. From Greig (1927a) with data from Rankin and Wright (1915). Goldsmith (1948) suggested that the compound designated 3 $CaO \cdot 5\ Al_2O_3$ is probably $CaO \cdot 2\ Al_2O_3$.

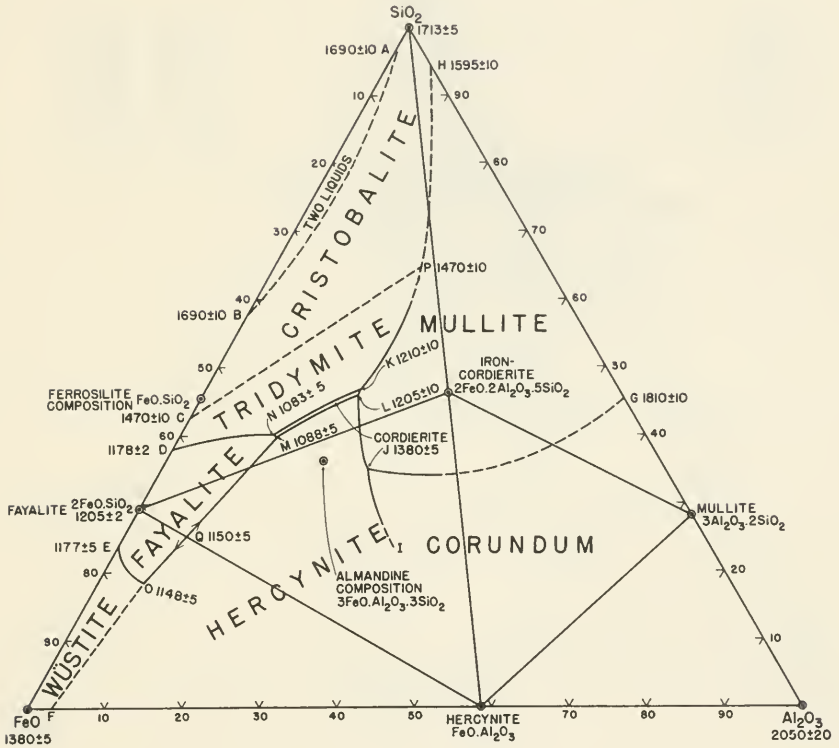

Figure 7.— The system: FeO-Al_2O_3. From Schairer and Yagi (1952); reprinted by permission of the American Journal of Science. The system is ternary only when a small content of Fe_2O_3 in the liquids is disregarded.

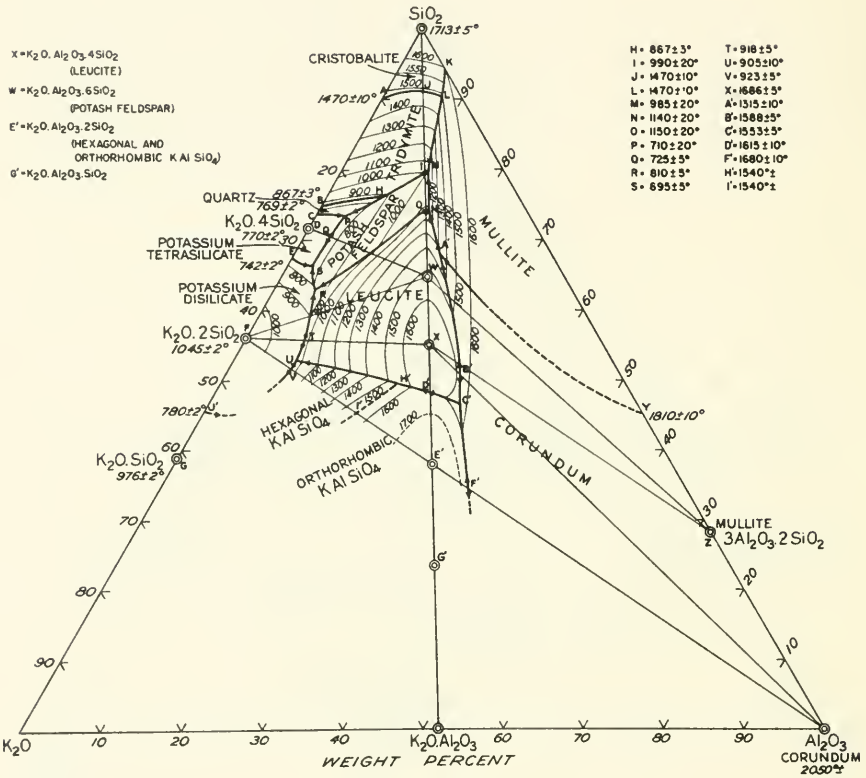

Figure 8.— The system: K_2O-Al_2O_3-SiO_2. From Schairer and Bowen (1955); reprinted by permission of the American Journal of Science.

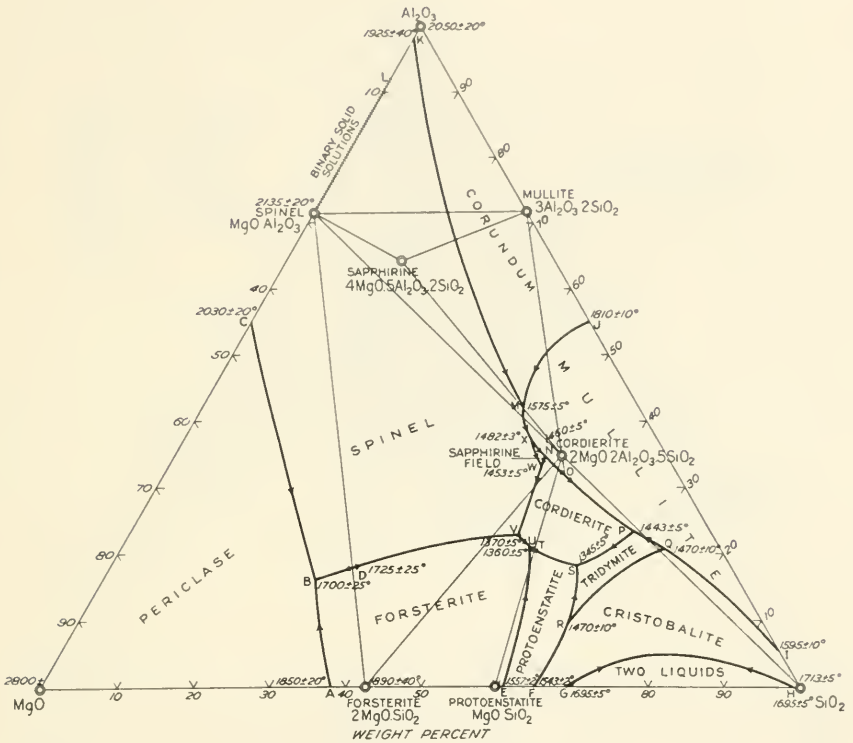

Figure 9.— The system: MgO-Al_2O_3-SiO_2. From Keith and Schairer (1952); reprinted by permission of the Journal of Geology; copyright, 1952, by the University of Chicago. Composite diagram based on Rankin and Merwin (1918), Bowen and Greig (1924), Greig (1927a), Schairer (1942), and Foster (1950).

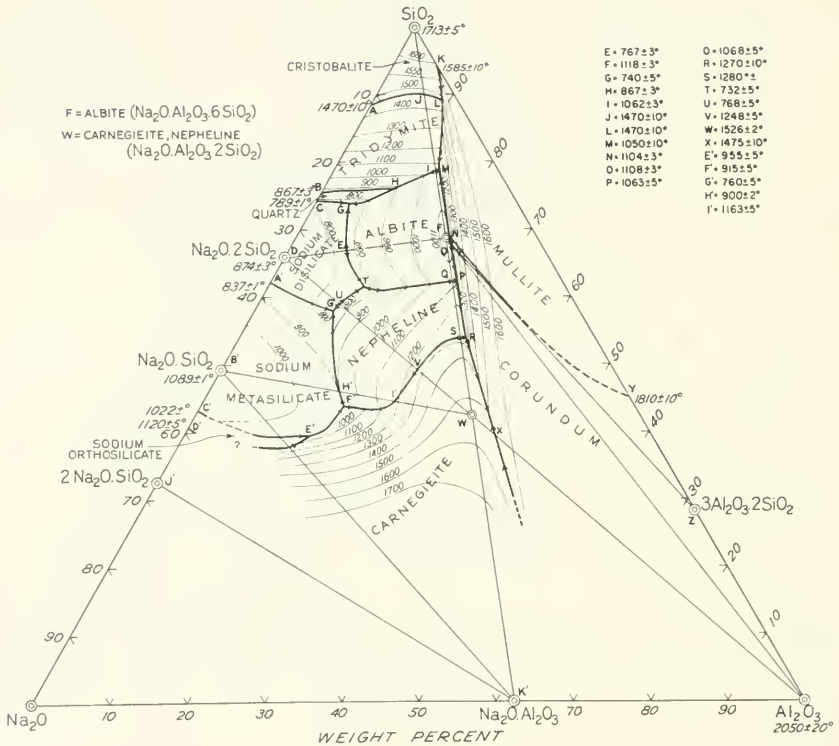

Figure 10.– The system: Na_2O-Al_2O_3-SiO_2. From Schairer and Bowen (1956); reprinted by permission of the American Journal of Science.

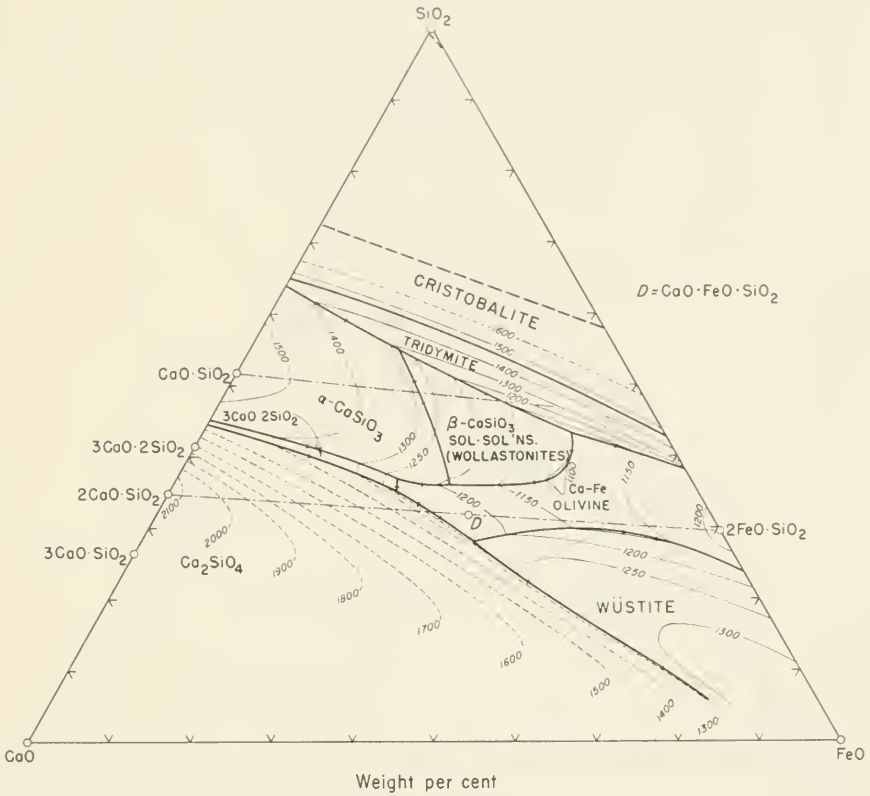

Figure 11.— The system: CaO-FeO-SiO_2. From S. P. Clark, Jr. (written communication, 1962), modified from Bowen, Schairer and Posnjak (1933). Estimated field boundaries are shown by broken lines. The system is ternary only if a small content of Fe_2O_3 in the liquids are disregarded.

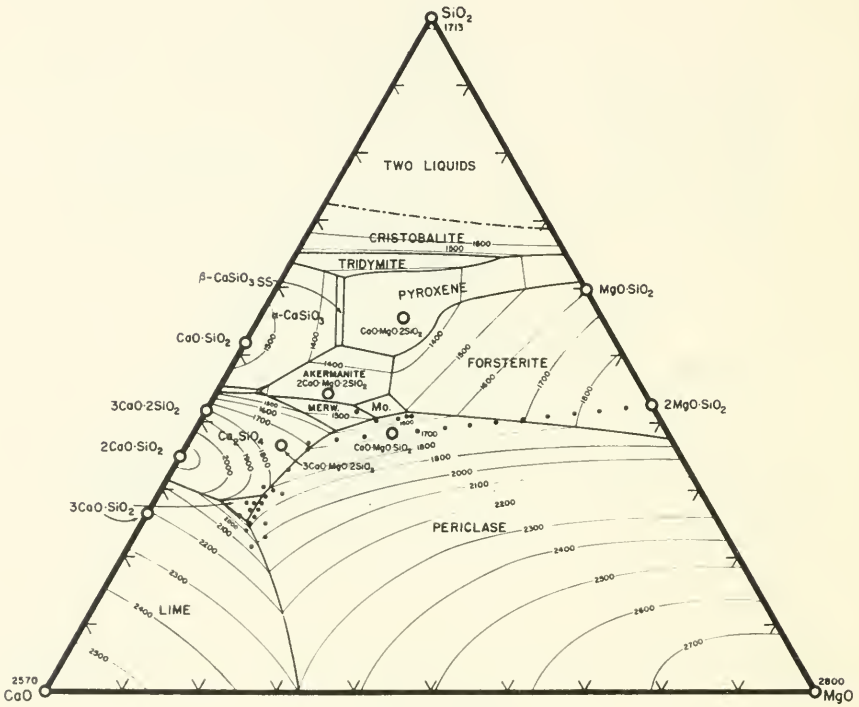

Figure 12.— The system: CaO-MgO-SiO_2. From Ricker and Osborn (1954); reprinted by permission of the American Ceramic Society. Composite diagram based on Ferguson and Merwin (1919), Greig (1927a), Bowen (1914), Osborn (1942), and Bredig (1950).

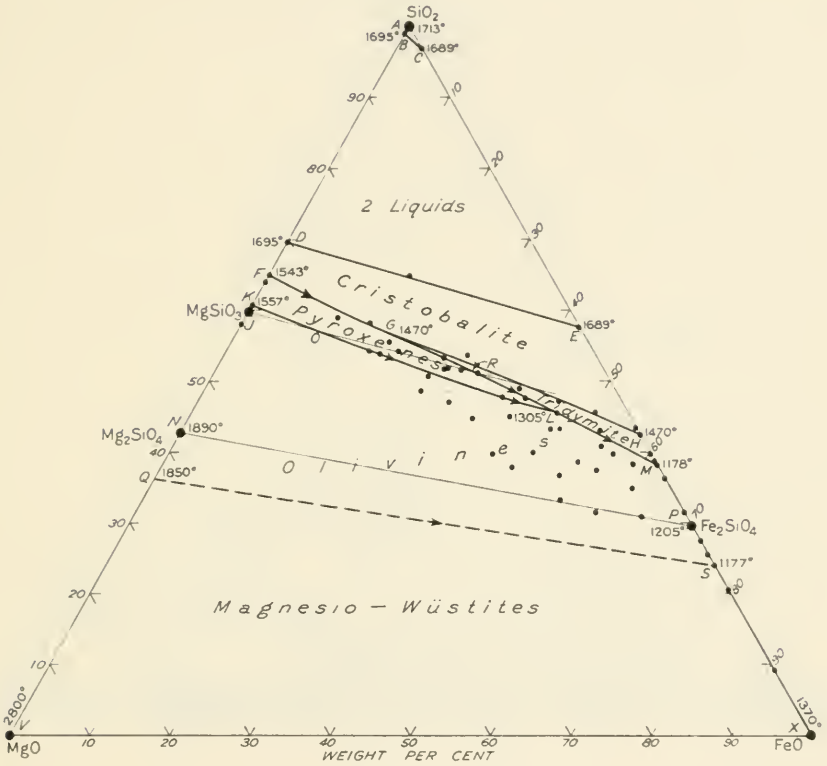

Figure 13.— The system: MgO-FeO-SiO_2. From Bowen and Schairer (1935); reprinted by permission of the American Journal of Science. The system is ternary only if a small content of Fe_2O_3 in the liquids is disregarded.

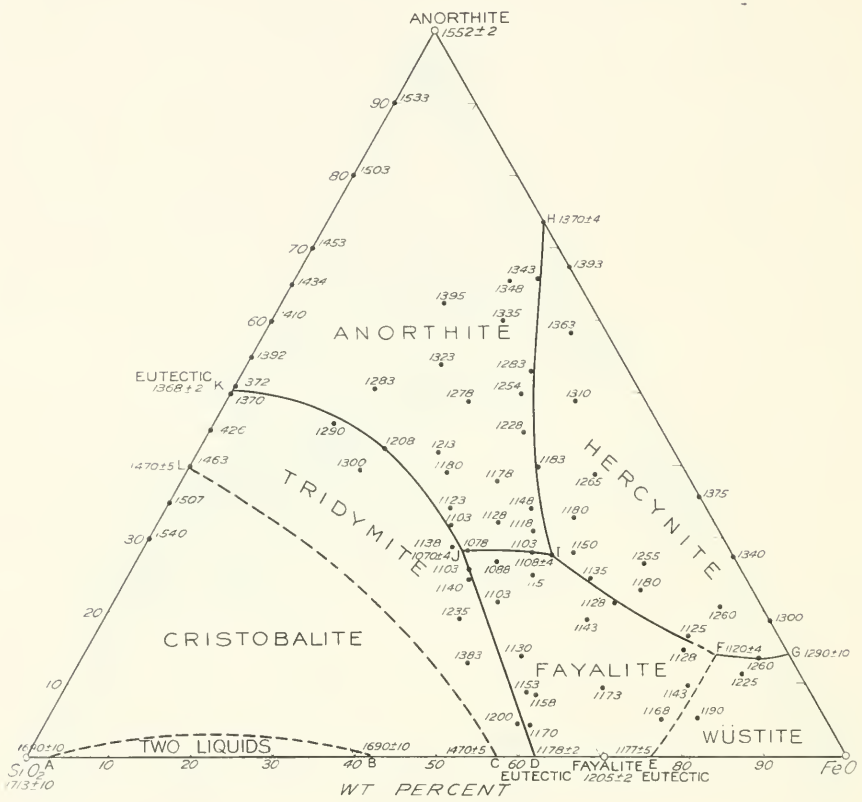

Figure 14.– The system: Al_2O_3-CaO-FeO-SiO_2; the join plane: SiO_2-FeO-$CaAl_2Si_2O_8$, Anorthite. From Schairer (1942); reprinted by permission of the American Ceramic Society. The join is not ternary in the field of hercynite, $FeAl_2O_4$.

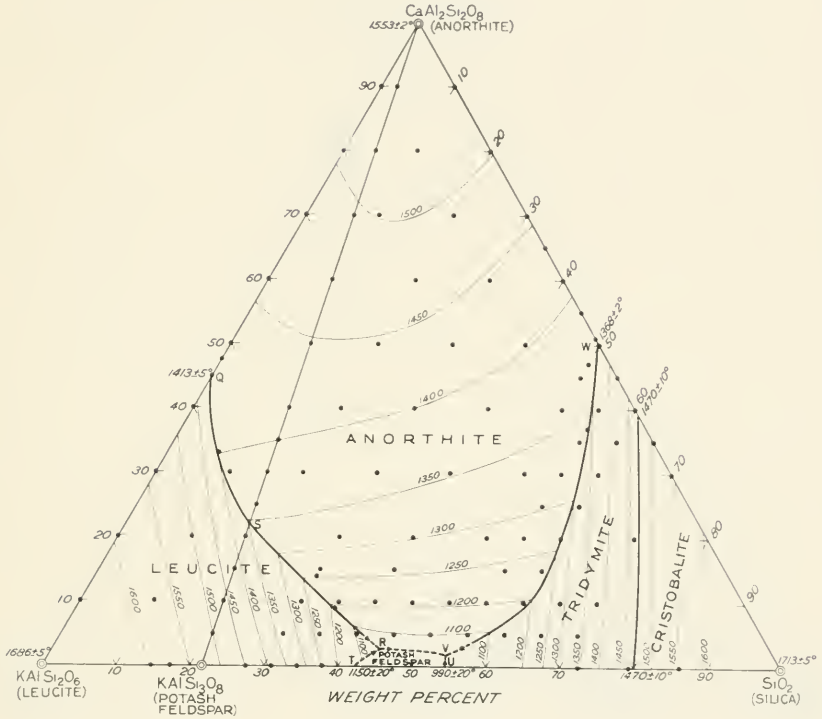

Figure 15.– The system: Al_2O_3-CaO-K_2O-SiO_2; the ternary section: $KAlSi_2O_6$, Leucite-SiO_2-$CaAl_2Si_2O_8$, Anorthite. From Schairer and Bowen (1947a); reprinted by permission of Commission Géologie de Finlande.

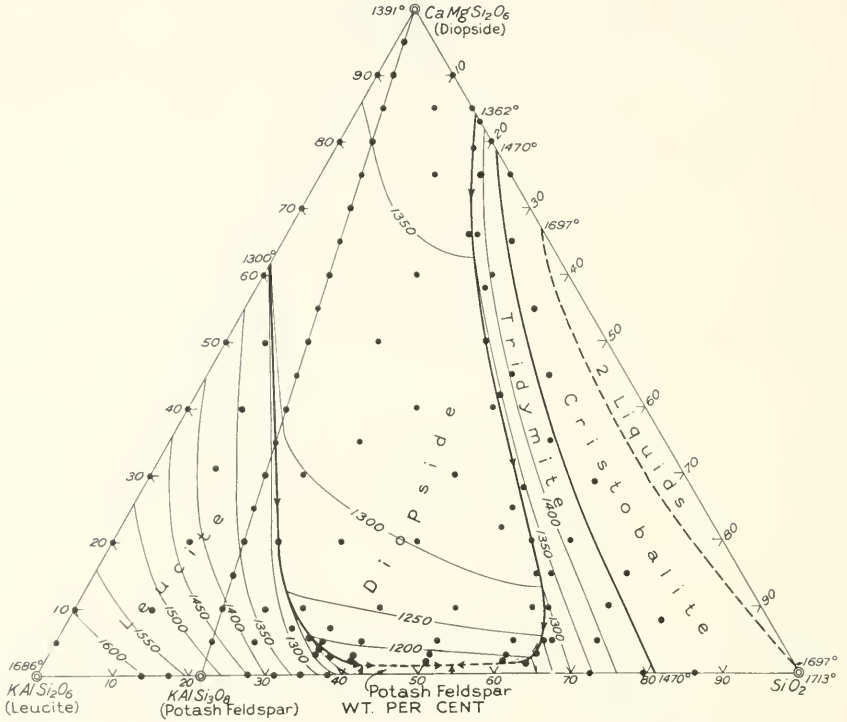

Figure 16.– The system: Al_2O_3-CaO-K_2O-MgO-SiO_2; the ternary section; $KAlSi_2O_6$, Leucite-SiO_2-$CaMgSi_2O_6$, Diopside. From Schairer and Bowen (1938); reprinted by permission of the American Journal of Science.

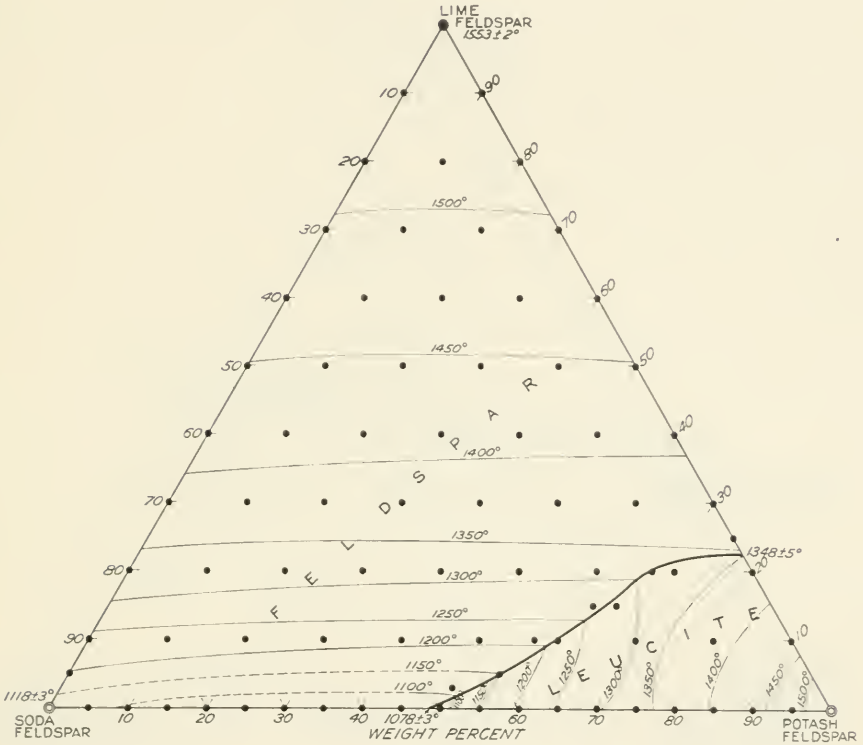

Figure 17.— The system: Al_2O_3-CaO-K_2O-Na_2O-SiO_2: the ternary section: $NaAlSi_3O_8$, Soda feldspar-$KAlSi_3O_8$, Potash feldspar-$CaAl_2Si_2O_8$, Lime feldspar. From Franco and Schairer (1951): reprinted by permission of the Journal of Geology; copyright, 1951, by the University of Chicago.

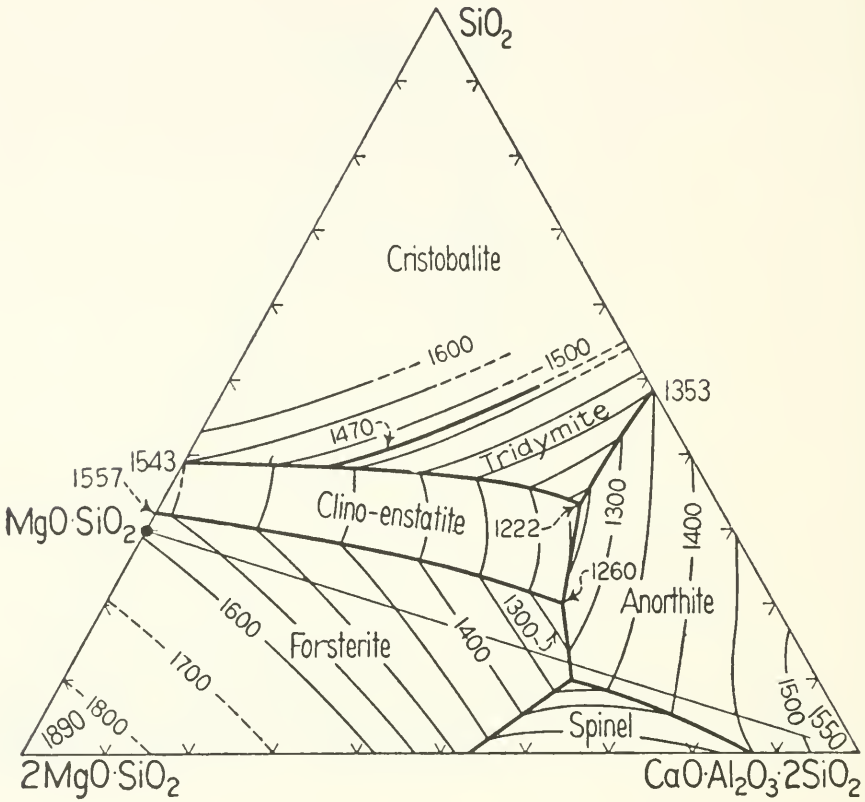

Figure 18.– The system: Al_2O_3-CaO-MgO-SiO_2: the join plane: Mg_2SiO_4, Forsterite-SiO_2-$CaAl_2Si_2O_8$, Anorthite. From Andersen (1915); reprinted by permission of the American Journal of Science. The join fails to be ternary in the field of spinel, $MgAl_2O_4$.

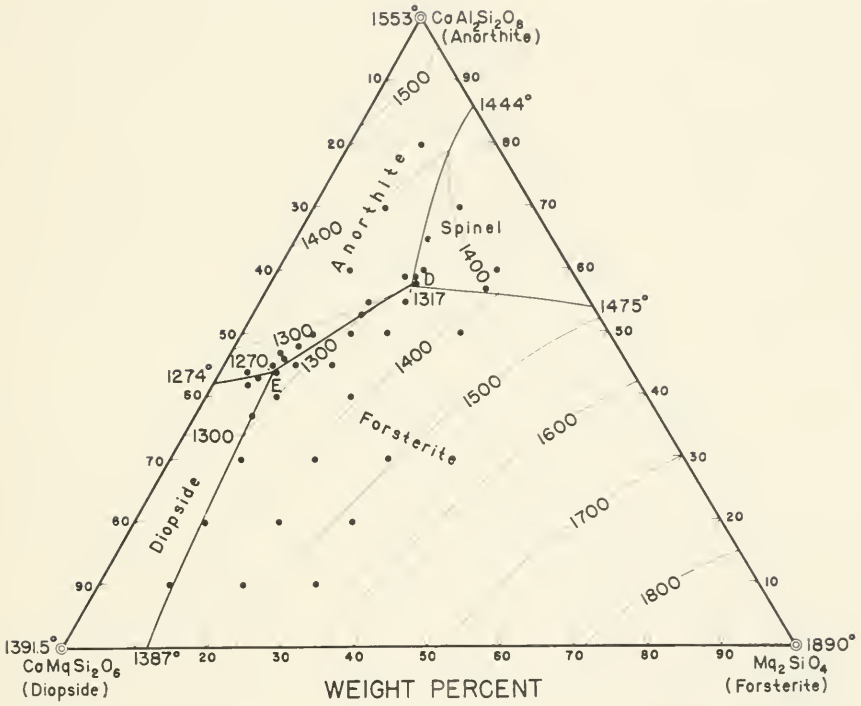

Figure 19.– The system: Al_2O_3-CaO-MgO-SiO_2; the ternary section: $CaMgSi_2O_6$, Diopside-Mg_2SiO_4, Forsterite-$CaAl_2Si_2O_8$, Anorthite. From Osborn and Tait (1952); reprinted by permission of the American Journal of Science.

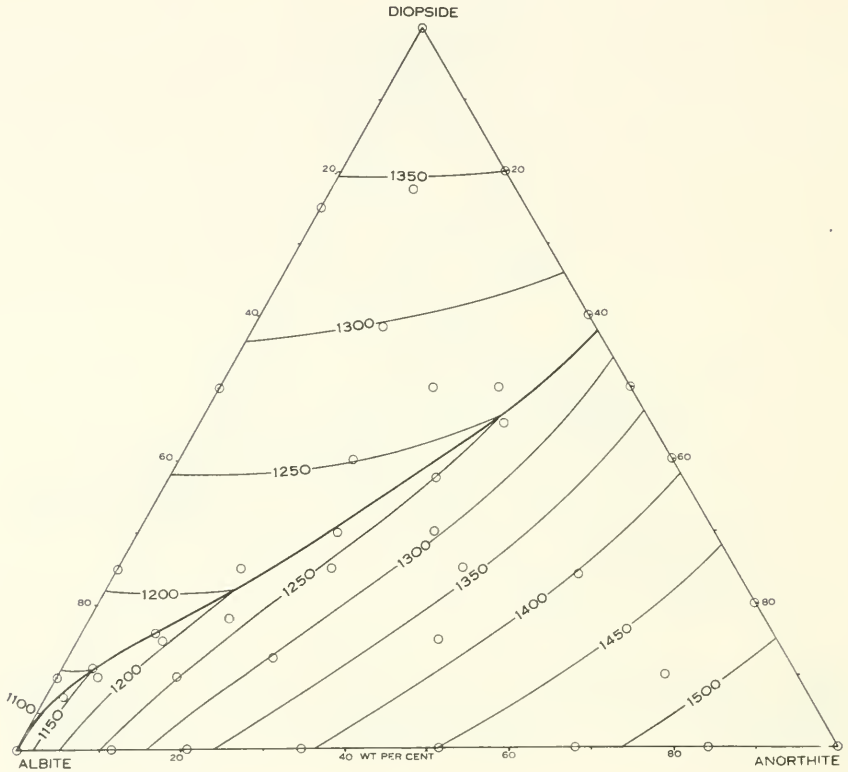

Figure 20.– The system: Al_2O_3-CaO-MgO-Na_2O-SiO_2: the ternary section: $NaAlSi_3O_8$, Albite-$CaAl_2Si_2O_8$, Anorthite-$CaMgSi_2O_6$, Diopside. From Bowen (1915); reprinted by permission of the American Journal of Science.

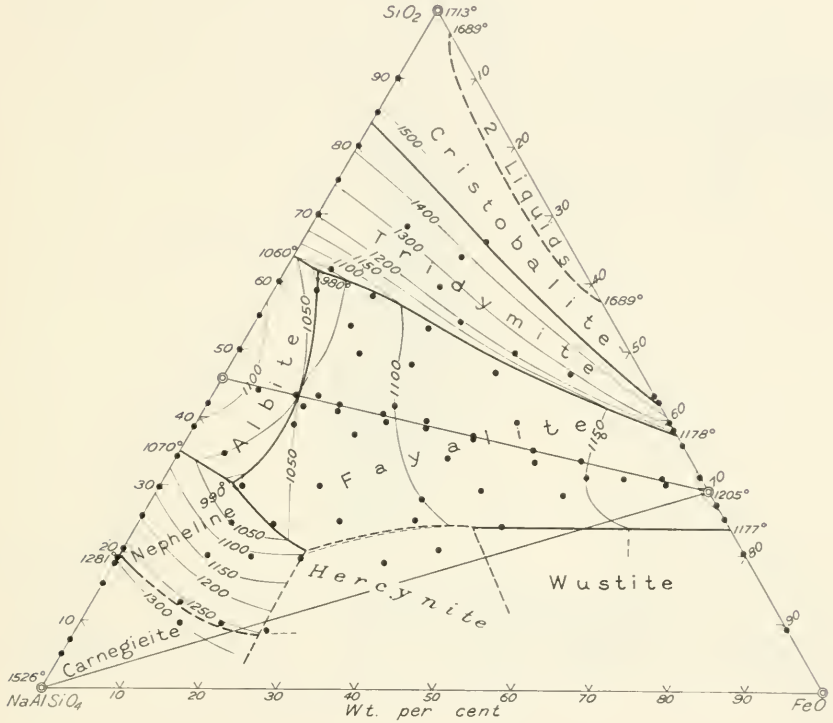

Figure 21.– The system: Al_2O_3-FeO-Na_2O-SiO_2; the join plane: $NaAlSiO_4$, Nepheline, Carnegieite-FeO-SiO_2. From Bowen (1937); reprinted by permission of the American Journal of Science. The join is not ternary in the field of hercynite, $FeAl_2O_4$.

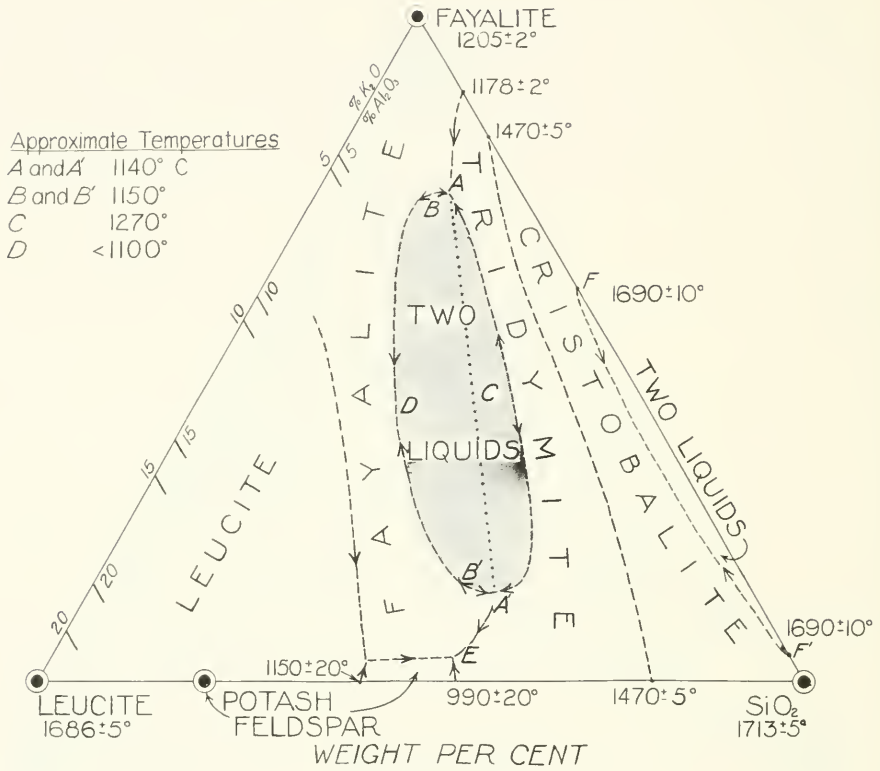

Figure 22.– The system: Al_2O_3-FeO-K_2O-SiO_2; the ternary section: $KAlSi_2O_6$, Leucite-SiO_2-Fe_2SiO_4, Fayalite. From Roedder (1951a); reprinted by permission of the Mineralogical Society of America. The section is ternary only when small contents of Fe_2O_3 in the liquids are disregarded.

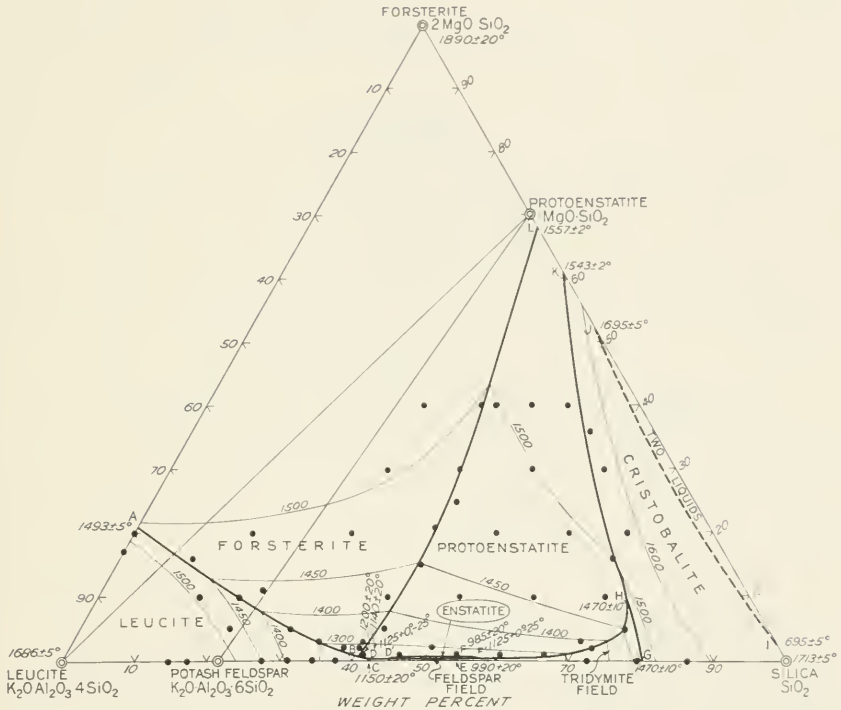

Figure 23.— The system: Al_2O_3-K_2O-MgO-SiO_2; the ternary section: $KAlSi_2O_6$, Leucite-SiO_2-Mg_2SiO_4, Forsterite. From Schairer (1954); reprinted by permission of the American Ceramic Society. The fields of $MgSiO_3$, Enstatite, and of $KAlSi_3O_8$, Potash Feldspar, are so narrow they could not be shown in the diagram without some exaggeration.

Figure 24.– The system: Al_2O_3-K_2O-Na_2O-SiO_2: the ternary section: $NaAlSiO_4$, Nepheline, Carnegieite-$KAlSiO_4$, Kalsilite, Kaliophillite-SiO_2. From Schairer (1950); reprinted by permission of the Journal of Geology; copyright, 1950, by the University of Chicago.

REFERENCES

Adams, L. H., 1919, Tables and curves for use in measuring temperatures with thermocouples: Am. Inst. Min. Metall. Engineers Bull., no. 153, p. 2111-2124.

—— 1926, International critical tables: New York McGraw-Hill Book Co., v. 1, p. 57-59.

Agamawi, Y. M., and White, J., 1951, The systems Al_2O_5-TiO_2-SiO_2: British Ceramic Soc. Trans., v. 51, no. 5, p. 293-325.

Alberman, K. B., Blakey, R. C., and Anderson, J. S., 1951, The oxides of uranium, Part II, The binary system UO_2-CaO: Chem. Soc. London Jour., 1951, p. 1352-1356.

Allen, W. C., and Snow, R. B., 1955, The orthosilicate-iron oxide portion of the system CaO-"FeO"-SiO_2: Am. Ceramic Soc. Jour., v. 38, no. 8, p. 264-280.

Andersen, Olaf, 1915, The system anorthite-forsterite-silica: Am. Jour. Sci., ser. 4, v. 39, no. 232, p. 407-454.

Andrussow, Leonid, 1925, Differential-methode und -apparat zur Bestimmung der Dissoziationsisochoren und Untersuchungen über die Kinetik der thermischen Dissoziation des Cadmiumkarbonats: Zeitschr. phys. Chemie, v. 115, no. 3 and 4, p. 273-288.

d'Ans, J., and Löffler, J., 1930, Untersuchungen im System Na_2O-SiO_2-ZrO_2: Zeitschr. anorg. u. allg. Chemie, v. 191, no. 1 and 2, p. 1-35.

Asanti, P., and Kohlmeyer, E. J., 1951, Über die thermischen Eigenschaften der Verbindungen von Kobalt mit Sauerstoff und Schwefel: Zeitschr. anorg. u. allg. Chemie, v. 265, no. 1-3, p. 90-98.

Asker, W. J., Segnit, E. R., and Wylie, A. W., 1952, The potassium thorium fluorides: Chem. Soc. London Jour., 1952, p. 4470-4479.

Atlas, Leon, 1952, The polymorphism of $MgSiO_3$ and solid-state equilibria in the system $MgSiO_3$-$CaMgSi_2O_6$: Jour. Geology, v. 60, no. 2, p. 125-147.

Barrett, R. L., and McCaughey, W. J., 1942, The system CaO-SiO_2-P_2O_5: Am. Mineralogist, v. 27, no. 10, p. 680-695.

Bellanca, Angello, and Carapezza, Marcello, 1951, L'aftitalite nel sistema ternario Na_2SO_4-K_2SO_4-$CuSO_4$: Periodico mineralogica, v. 20, no. 2-3, p. 272-307.

Belyayev, I. N., 1952, Obmennoye razlozheniye vo vzaimnov sisteme iz sul'fatov i vol'framatov natriya i svintsa: Zhur. Obshchey Khimii, v. 22 (84), no. 10, p. 1746-1756.

Belyayev, I. N., and Nesterova, A. K., 1952, Plavkost' troynoy sistem'i: okis' svintsa-pyatiokis' vanadiya-dvuokis' titana: Zhur. Obshchey Khimii, v. 22 (84), no. 3, p. 396-403.

Berezhnoy, A. S., 1950, Investigation of the system magnesia-lime-titanium oxide-silica: Ogneupory, v. 15, p. 350-359.

Berezhnoy, A. S., Karyakin, L. I., and Dudavskiy, 1952, O sisteme Cu_2O-SiO_2 i o sushestvanii bezvodnykh silikatov medi: Akad. Nauk SSSR, Doklady, v. 83, no. 3, p. 399-401.

Bergmann, A. G., and Dergunov, E. P., 1941, Das Schmelzdiagramm des System LiF-NaF-MgF_2: Acad. sci., U. R. S. S., Comptes rendus, v. 31, no. 8, p. 755-756.

Bergmann, A. G., and Sholokhovich, M. L., 1953, Vzaimnaya sistema adiagonal'no-poyasnogo evtekticheskogo tipa iz metafosfatov i sul'fatov litiya i kaliya: Zhur. Obshchey Khimii, v. 23 (85), no. 7, p. 1075-1085.

Berry, T. F., Allen, W. C., and Snow, R. B., 1950, Chemical changes in basic brick during service: Am. Ceramic Soc., Jour., v. 33, no. 4, p. 121-132.

Boak, Tryggve, and Olander, Arne, 1955, The system $CaSiO_3$-CaF_2: Acta Chem. Scandinavica, v. 9, no. 8, p. 1350-1354.

Bobrownicki, W., and Swiecki, Z., 1955, Phase diagrams for the production of silicate thermophosphates: Acad. polonaise Sci. Bull., Cl. 3, v. 3, no. 4, p. 233-237.

Boeke, H. E., 1912, Die Schmelzerscheinungen und die umkehrbare Umwandlung des Calciumcarbonats: Neues Jahrb. Mineralogie, Geologie, u. Paläontologie, v. 1, p. 91-121.

——1913, Karbonatschmelzen unter Kohlensäuredruck. II: Naturf. Gesell. Halle Mitt., v. 3, p. 13-24.

Booth, H. S., Starrs, B. A. and Bahnsen, M. J., 1933, The system sodium disilicate-sodium fluoride: Jour. Phys. Chemistry, v. 37, p. 1103-1107.

Bowen, N. L., 1914, The ternary system: diopside-forsterite-silica: Am. Jour. Sci., 4th ser., v. 38, no. 224, p. 207-264.

——1915, The crystallization of haplobasaltic, haplodioritic and related magmas: Am. Jour. Sci., 4th ser., v. 40, no. 236, p. 161-185.

——1917, The sodium-potassium nephelites: Am. Jour. Sci., 4th ser., v. 43, no. 254, p. 115-132.

——1922, Genetic features of alnoitic rocks at Isle Cadieux, Quebec: Am. Jour. Sci., ser. 5, v. 3, no. 13, p. 1-34.

——1928, The evolution of the igneous rocks: Princeton, N. J., Princeton Univ. Press, 332 p.

——1937, Recent high-temperature research on silicates and its significance in igneous geology: Am. Jour. Sci., 5th ser., v. 33, no. 193, p. 1-21.

——1940, Progressive metamorphism of siliceous limestone and dolomite: Jour. Geology, v. 48, no. 3, p. 225-274.

Bowen, N. L., and Andersen, Olaf, 1914, The binary system MgO-SiO_2: Am. Jour. Sci., 4th ser., v. 37, no. 222, p. 487-500.

Bowen, N. L., and Greig, J. W., 1924, The system Al_2O_3-SiO_2: Am. Ceramic Soc. Jour., v. 7, no. 4, p. 238-254.

Bowen, N. L., and Schairer, J. F., 1929, The system: leucite-diopside: Am. Jour. Sci., 5th ser., v. 18, no. 106, p. 301-312.

——1932, The system FeO-SiO_2: Am. Jour. Sci., 5th ser., v. 24, no. 141, p. 177-213.

——1935, The system MgO-FeO-SiO_2: Am. Jour. Sci., 5th ser., v. 29, no. 170, p. 151-217.

Bowen, N. L., Schairer, J. F., and Posnjak, E., 1933, The system CaO-FeO-SiO_2: Am. Jour. Sci., 5th ser., v. 26, p. 193-284.

Bowen, N. L., Schairer, J. F., and Willems, H. W. V., 1930, The ternary system: Na_2SiO_3-Fe_2O_3-SiO_2: Am. Jour. Sci., 5th ser., v. 20, no. 120, p. 405-455.

Bredig, M. A., 1943, Phase relations in the system calcium orthosilicate-orthophosphate: Am. Mineralogist, v. 28, no. 11 and 12, p. 594-601.

——1950, Polymorphism of calcium orthosilicate: Am. Ceramic Soc. Jour., v. 33, no. 6, p. 188-192.

Brewer, Leo, 1953, The thermodynamic properties of the oxides and their vaporization processes: Chem. Reviews, v. 52, p. 1-75.

Bridgman, P. W., 1937, The phase diagram of water to 45,000 kg./cm^2: Jour. Chem. Physics, v. 5, p. 964-966.

Brisi, Cesare, 1957, Role of cuspidine ($3CaO\text{-}2SiO_2\text{-}CaF_2$) in the system CaO-$SiO_2$-$CaF_2$: Am. Ceramic Soc. Jour., v. 40, no. 5, p. 174-178.

Brown, F. H., and Duwez, Pol, 1954, The zirconia-titania system: Am. Ceramic Soc. Jour., v. 37, no. 3, p. 129-132.

Brownmiller, L. T., 1935, A study of the system lime-potash-alumina: Am. Jour. Sci., 5th ser., v. 29, no. 171, p. 260-277.

Bružs, B., 1926, Velocity of thermal decomposition of carbonates: Jour. Phys. Chemistry, v. 30, no. 5, p. 680-693.
Bunting, E. N., 1930a, Phase equilibria in the system SiO_2-ZnO: [U.S.] Natl. Bur. Standards Jour. Research, v. 4, no. 1, p. 131-136.
——1930b, Phase equilibria in the system Cr_2O_3-SiO_2: [U.S.] Natl. Bur. Standards Jour. Research, v. 5, no. 2, p. 325-327.
——1931, Phase equilibria in the system Cr_2O_3-Al_2O_3: [U.S.] Natl. Bur. Standards Jour. Research, v. 6, no. 6, p. 947-949.
——1932, Phase equilibria in the system SiO_2-ZnO-Al_2O_3: [U.S.] Natl. Bur. Standards Jour. Research, v. 8, no. 2, p. 279-287.
——1933, Phase equilibria in the systems TiO_2, TiO_2-SiO_2 and TiO_2-Al_2O_3: [U.S.] Natl. Bur. Standards Jour. Research, v. 11, no. 5, p. 719-725.
Burdese, Aurelia, and Brisi, Cesare, 1952, Ricerche sul sistema CaO·Fe_2O_3-Fe_3O_4: Ricerca Sci., v. 22, no. 8, p. 1564-1567.
Burdick, M. D., 1940, Studies on the system lime-ferric oxide-silica: [U.S.] Natl. Bur. Standards Jour. Research, v. 25, no. 4, p. 475-488.
Carlson, E. T., 1932, The system: CaO-B_2O_3: [U.S.] Natl. Bur. Standards Jour. Research, v. 9, no. 6, p. 825-832.
Carter, P. I., and Ibrahim, M., 1952, The ternary system Na_2O-FeO-SiO_2: Soc. Glass Technology Jour., v. 36, Trans., p. 142-163.
Centnerszwer, M., 1930, Les Phénomènes de dissociation au point de vue de la regle des phases: Jour. Chimie Physique, v. 27, no. 1, p. 9-28.
Centnerszwer, M., and Bružs, B., 1924, Die stufenweise Dissoziation des Magnesiumkarbonats: Zeitschr. phys. Chemie, v. 114, no. 3 and 4, p. 237-250.
——1925, Zerfallsgeschwindigkeit fester Stoffe. I, Geschwindigkeit der Dissoziation des Magnesiumkarbonats: Zeitschr. phys. Chemie, v. 115, no. 5 and 6, p. 365-376.
Centnerszwer, M., Falk, G., and Awerbuch, A., 1925, Über die Dissoziation des Bleikarbonats: Zeitschr. phys. Chemie, v. 115, no. 1 and 2, p. 29-53.
Centnerszwer, M., and Krustinson, J., 1926, Beschreibung eines neuen Apparats zur dynamischen Bestimmung der Dissoziationsspannungen und die Dissoziation des Silberkarbonats: Zeitschr. phys. Chemie, v. 124, no. 3 and 4, p. 225-235.
Clark, S. P., Jr., 1957, A note on calcite-aragonite equilibrium: Am. Mineralogist, v. 42, no. 7 and 8, p. 564-566.
Clark, S. P., Jr., Robertson, E. C., and Birch, Francis, 1957, Experimental determination of kyanite-sillimanite equilibrium relations at high temperatures and pressures: Am. Jour. Sci., v. 225, no. 9, p. 628-640.
Colson, Albert, 1905, Applications diverses du principle de Watt à la dissociation des carbonates de plomb et d'argent: Acad. sci. [Paris] Comptes rendus, v. 140, p. 865-867.
——1909, Sur l'impossibilité de prévoir par la thermochimie la stabilité relative de composés comparables d'argent et de plomb: Acad. sci. [Paris] Comptes rendus, v. 148, p. 837-839.
Corruccini, R. J., 1949, Differences between the international temperature scales of 1948 and 1927: [U.S.] Natl. Bur. Standards Jour. Research, v. 43, no. 2, p. 133-136.
Coughanour, L. W., and DeProsse, V. A., 1953, Phase equilibria in the system MgO-TiO2: [U.S.] Natl. Bur. Standards Jour. Research, v. 51, no. 2, p. 85-88.
Coughanour, L. W., Roth, R. S., and DeProsse, V. A., 1954, Phase equilibrium relations in the systems lime-titania and zirconia-titania: [U.S.] Natl. Bur. Standards Jour. Research, v. 52, no. 1, p. 37-42.

Coughanour, L. W., Roth, R. S., Marzullo, S., and Sennett, F. E., 1955, Solid-state reactions and dielectric properties in the system magnesia-lime-tin oxide-titania: [U. S.] Natl. Bur. Standards Jour. Research, v. 54, no. 3, p. 149-162.

Counts, W. E., Roy, Rustum, and Osborn, E. F., 1953, Fluoride model systems. II, The binary systems CaF_2-BeF_2, MgF_2-BeF_2, and LiF-MgF_2: Am. Ceramic Soc. Jour., v. 36, no. 1, p. 12-17.

Curtis, C. E., and Sowman, H. G., 1953, Investigation of the thermal dissociation, reassociation, and synthesis of zircon: Am. Ceramic Soc. Jour., v. 36, no. 6, p. 190-198.

Darken, L. S., 1948, Melting points of iron oxides on silica; Phase equilibria in the system Fe-Si-O as a function of gas composition and temperature: Am. Chem. Soc. Jour., v. 70, no. 6, p. 2046-2053.

Darken, L. S., and Gurry, R. W., 1945, The system iron-oxygen. I. The wüstite field and related equilibria: Am. Chem. Soc. Jour., v. 67, p. 1398-1412.

———1946, The system iron-oxygen. II. Equilibrium and thermodynamics of liquid oxide and other phases: Am. Chem. Soc. Jour., v. 68, no. 5, p. 798-816.

———1950, The composition of CaO-FeO-Fe_2O_3 and MnO-FeO-Fe_2O_3 melts at several oxygen pressures in the vicinity of 1600°: Am. Chem. Soc., Jour., v. 72, no. 9, p. 3906-3910.

———1953, Physical chemistry of metals: New York, McGraw-Hill Book Co., 535 p.

Day, A. L., and Sosman, R. B., 1911, High temperature gas thermometry: Carnegie Inst. Washington Pub. 157, 129 p.

———1922, Realization of absolute scale of temperature, in a dictionary of applied physics: London, Macmillan and Co., v. 1, p. 836-871.

Dear, P. S., 1957, Subliquidus equilibrium for the ternary system SrO-Al_2O_3-SiO_2: Virginia Polytech. Inst. Bull., v. 50, no. 11, 12 p.

———1958, Subliquidus equilibrium for ternary system SrO-ZrO_2-SiO_2: Virginia Polytech. Inst. Bull., v. 51, no. 8, 10 p.

DeVries, R. C., and Osborn, E. F., 1957, Phase equilibria in high-alumina part of the system CaO-MgO-Al_2O_3-SiO_2: Am. Ceramic Soc. Jour., v. 40, no. 1, p. 6-15.

DeVries, R. C., and Roy, Rustum, 1953, Fluoride models for oxide systems of dielectric interest. The systems KF-MgF_2 and AgF-ZnF_2: Am. Chem. Soc. Jour., v. 75, no. 10, p. 2479-2484.

DeVries, R. C., Roy, R., and Osborn, E. F., 1953, Phase equilibria in the system CaO-TiO_2-SiO_2 and their significance: Pennsylvania State Coll., School Mineral Industries 8th Quart. Prog. Rept. (2nd Ann. Rept.) Apr. 1, 1953, to June 30, 1953, p. 26-118.

———1954a, Phase equilibria in the system CaO-TiO_2: Jour. Phys. Chemistry, v. 58, no. 12, p. 1069-1073.

———1954b, The system TiO_2-SiO_2: British Ceramic Soc. Trans., v. 53, no. 9, p. 525-540.

———1955, Phase equilibria in the system CaO-TiO_2-SiO_2: Am. Ceramic Soc. Jour., v. 38, no. 5, p. 158-71.

DeWys, E. C., and Foster, W. R., 1956, The binary system anorthite ($CaAl_2Si_2O_8$)-akermanite ($Ca_2MgSi_2O_7$): Am. Ceramic Soc. Jour., v. 39, no. 11, p. 372-376.

Dietzel, Adolf, and Scholze, Horst, 1955, Untersuchungen im System B_2O_3-Al_2O_3-SiO_2: Glastechnische Ber., v. 28, no. 2, p. 47-51.

Drake, L. C., and Benton, A. F., 1934, Adsorption of carbon dioxide and hydrogen on bare and oxygen-covered silver surfaces: Am. Chem. Soc. Jour., v. 56, no. 3, p. 506-511.

Drossbach, Paul, 1936, Zur Elektrometallurgie des Aluminiums: Zeitschr. Elektrochemie, v. 42, no. 2, p. 65-70.

Dutoit, William, 1927, Tensions de dissociations des carbonates de calcium de strontium et de baryum:Jour. chemie phys.,v. 24, no. 2, p. 110-114.

Duwez, Pol, and Odell, Francis, 1950, Phase relationships in the system zirconia-ceria: Am. Ceramic Soc. Jour., v. 33, no. 9, p. 274-283.

Eitel, Wilhelm, 1923, Über das binare System $CaCO_3$-Ca_2SiO_4 und den Spurrit: Neues Jahrb. Mineralogie, Geologic u. Paläontologie, Beilage-Band, v. 48, p. 63-74.

———1925, Über die Synthesen der Feldspatvertreter: Leipzig, Germany, Akad. Verlagsges., 258 p.

———1938a, Die Wirkung der Fluoride als Mineralisatoren beim Klinkerbrand: Zement, v. 27, no. 30 and 31, p. 455-459 and 469-472.

———1938b, Das System CaO-CaF_2-Ca_2SiO_4: Zeitschr. angew. Mineralogie, v. 1, no. 3, p. 269-284.

———1941, Physikalische Chemie der Silikate: 2d ed., Leipzig, Germany, J. A. Barth, 826 p.

Eitel, Wilhelm, and Skaliks, W., 1929, Über einige Doppelcarbonate der Alkalien und Erdalkalien: Zeitschr. anorg. u. allg. Chemie, v. 183, no. 3, p. 263-286.

Eskola, Pentti, 1922, The silicates of strontium and barium: Am. Jour. Sci., 5th ser., v. 4, no. 23, p. 331-375.

Eubank, W. R., and Bogue, R. H., 1948, Preliminary study on portions of the systems Na_2O-CaO-Al_2O_3-Fe_2O_3 and Na_2O-CaO-Fe_2O_5-SiO_3:[U.S.] Natl. Bur. Standards Jour. Research, v. 40, no. 3, p. 225-234.

Faust, G. T., 1936, The fusion relations of iron-orthoclase: Am. Mineralogist, v. 21, no. 12, p. 735-763.

Fenner, C. N., 1913, The stability relations of the silica minerals: Am. Jour. Sci., 4th ser., v. 36, no. 214, p. 331-384.

Ferguson, J. B., and Merwin, H. E., 1919, The ternary system CaO-MgO-SiO_2: Am. Jour. Sci., 4th ser., v. 48, no. 284, p. 81-123.

Ferguson, J. B., and Buddington, A. F., 1920, The binary system Akermanite-Gehlenite: Am. Jour. Sci., 4th ser., v. 50, no. 296, p. 131-140.

Finkelstein, Alexis, 1906, Die Dissociation des Baryumcarbonats: Deutsche chemische Gessell. Ber., v. 39, no. 7, p. 1585-1593.

Fischer, W. A., and Hoffman, A., 1957, Gleichgewichtsuntersuchungen in den Systemem des Zirkonoxyds und Kalziumoxyds mit Eisenoxyden: Archiv Eisenhüttenw., v. 28, no. 12, p. 771-776.

Fleissner, Hans, 1925, Über Erzröstung: Montanistische Rundschau, v. 17, no. 16, p. 523-529.

Flint, E. P., and Wells, L. S., 1936, The system lime-boric oxide-silica: [U.S.] Natl. Bur. Standards Jour. Research, v. 17, no. 5, p. 727-752.

Ford, W. F., and Rees, W. J., 1949, The CaO-MgO-Cr_2O_3 ternary system II: British Ceramic Soc. Trans., v. 48, no. 8, p. 291-321.

Ford, W. F., and White, J., 1949, The CaO-MgO-Cr_2O_3 ternary system. III: British Ceramic Soc. Trans., v. 48, no. 11, p. 417-427.

Foster, W. R., 1950, Synthetic sapphirine and its stability relations in the system MgO-Al_2O_3-SiO_2: Am. Ceramic Soc. Jour., v. 33, no. 3, p. 73-84.

———1951a, High-temperature X-ray diffraction study of the polymorphism of $MgSiO_3$: Am. Ceramic Soc. Jour., v. 34, no. 9, p. 255-259.

———1951b, A study of solid-state reaction in the ternary system MgO-ZrO_2-SiO_2: Am. Ceramic Soc. Jour., v. 34, no. 10, p. 302-305.

Foster, W. R., and Royal, H. F., 1949, An intermediate compound in the system BeO·Al_2O_3(chrysoberyl)-Al_2O_3(corundum): Am. Ceramic Soc. Jour., v. 32, no. 1, p. 26-34.

Franco, R. R., and Schairer, J. F., 1951, Liquidus temperatures in mixtures of the feldspars of soda, potash, and lime: Jour. Geology, v. 59, no. 3, p. 259-267.

Friedrich, K., 1911, Technisch-thermische Analyse von Hüttenprozessen: Stahl und Eisen, v. 31, no. 47, p. 1909-1917.

Friedrich, K., and Smith, L. G., 1912, The thermal dissociation and the constitution of easily decomposed minerals: Centralb. Mineralogie, Geologie u. Paläontologie, 1912, p. 616-626, 651-659, 684-693.

———1912, Thermische Data zu den Röstprozessen: Metallurgie, v. 9, no. 13, p. 409-418.

Geller, A., 1924, Über das Verhalten verschiedener Minerale der Salzlager bei hohen Drucken und wechselnden Temperaturen: Zeitsch. Kristallographie, v. 60, no. 5 and 6, p. 414-472.

Geller, R. F., and Bunting, E. N., 1936, The system K_2O-PbO-SiO_2: [U. S.] Natl. Bur. Standards Jour. Research, v. 17, no. 2, p. 277-289.

———1937, The system PbO-B_2O_3: [U. S.] Natl. Bur. Standards Jour. Research, v. 18, no. 5, p. 585-593.

———1939, The system PbO-B_2O_3-SiO_2: [U. S.] Natl. Bur. Standards Jour. Research, v. 23, no. 2, p. 275-283.

———1943, Report on the systems lead oxide-alumina and lead oxide-alumina-silica: [U. S.] Natl. Bur. Standards Jour. Research, v. 31, no. 5, p. 255-270.

Geller, R. F., Creamer, A. S., and Bunting, E. N., 1934, The system: PbO-SiO_2: [U. S.] Natl. Bur. Standards Jour. Research, v. 13, no. 2, p. 237-244.

Geller, R. F., and Lang, S. M., 1955, Personal communication.

Geller, R. F., Yavorsky, P. J., Steierman, B. L., and Creamer, A. S., 1946, Studies of binary and ternary combinations of magnesia, calcia, baria, beryllia, alumina, thoria, and zirconia in relation to their use as porcelains: [U. S.] Natl. Bur. Standards Jour. Research, v. 36, no. 3, p. 277-312.

Glasser, F. P., 1958a, The system MnO-SiO_2: Am. Jour. Sci., v. 256, no. 6, p. 398-412.

———1958b, The ternary system MgO-MnO-SiO_2: Dissertation Abs., v. 19, no. 1, p. 52, Library of Congress Card Microfilm 58-2260.

Glasser, F. P., and Osborn, E. F., 1958, Phase equilibrium studies in the system CaO-Cr_2O_3-SiO_2: Am. Ceramic Soc. Jour., v. 41, no. 9, p. 358-367.

Glushkova, V. B., 1957, Usloviya obrazovaniya silikatov bariya: Zhur. Neorganicheskoy Khimii, v. 2, no. 10, p. 2438-2448.

Goldsmith, J. R., 1948, The compound CaO·$2Al_2O_3$: Jour. Geology, v. 56, no. 1, p. 80-81.

Goldsmith, J. R., and Graf, D. L., 1957, The system CaO-MnO-CO_2, solid-solution and decomposition relations: Geochim. et Cosmochim. Acta, v. 11, no. 4, p. 310-334.

Goldsmith, J. R., Graf, D. L., and Joensuu, O. I., 1955, The occurrence of magnesian calcites in nature: Geochim. et Cosmochim. Acta, v. 7, no. 5-6, p. 212-230.

Goranson, R. W., and Kracek, F. C., 1932, An experimental investigation of the phase relations of $K_2Si_4O_9$ under pressure: Jour. Phys. Chemistry, v. 36, no. 3, p. 913-926.

Graf, D. L., and Goldsmith, J. R., 1955, Dolomite-magnesian calcite relations at elevated temperatures and carbon dioxide pressures: Geochim. et Cosmochim. Acta, v. 7, p. 109-128.

———1958, The solid solubility of $MgCO_3$ in $CaCO_3$: A revision: Geochim. et Cosmochim. Acta, v. 13, no. 2-3, p. 218-219.

Grahmann, Werner, 1913, Vergleich der Sulfate der Erdalkalien und des Bleis in den Temperatur-konzentrationsdiagrammen mit Kaliumsulfat unter besonderer Berücksichtigung der dimorphie von anhydrit, Colestin, Baryt und Anglesit: Zeitschr. anorg. Chemie, v. 81, no. 3, p. 257-314.

Grebenshchikov, I. V., 1949, Fiziko-khimicheskie svoystva troynoy sistemy, Okis' natriya-okis' svintsa-kremnezem: Moskva and Leningrad, Izdatel'stvo Akad. Nauk SSSR, 219 p.

Greene, K. T., and Morgan, W. R., 1941, The system sodium disilicate-barium disilicate: Am. Ceramic Soc. Jour., v. 24, no. 4, p. 111-116.

Greig, J. W., 1926, Formation of mullite from cyanite, andalusite, and sillimanite: Am. Jour. Sci., 5th ser., v. 11, no. 61, p. 1-26.

———1927a, Immiscibility in silicate melts: Am. Jour. Sci., 5th ser., v. 13, no. 73, p. 1-44, 133-154.

———1927b, On liquid immiscibility in the system $FeO-Fe_2O_3-Al_2O_3-SiO_2$: Am. Jour. Sci., 5th ser., v. 14, no. 84, p. 473-484.

Greig, J. W., and Barth, Tom. F. W., 1938, The system $Na_2O \cdot Al_2O_3 \cdot 2SiO_2$ (Nephelite, Carnegieite)-$Na_2O \cdot Al_2O_3 \cdot 6SiO_2$(albite): Am. Jour. Sci., 5th ser., v. 35A, p. 93-112.

Greig, J. W. Posnjak, E., Merwin, H. E., and Sosman, R. B., 1935, Equilibrium relationships of Fe_3O_4, Fe_2O_3, and oxygen: Am. Jour. Sci., 5th ser., v. 30, no. 177, p. 239-316.

Grieve, J., and White, J., 1939, The system $FeO-TiO_2$: Glasgow, Scotland, Royal Tech. College Jour., v. 4, pt. 3, p. 441-448.

———1940, The systems $MnO-TiO_2$ and $MnO-FeO-TiO_2$: Glasgow, Scotland, Royal Tech. College Jour., v. 4, pt. 4, p. 660-670.

Guinier, André, and Yannaquis, N., 1957, Sur le polymorphisme du silicate bicalcique: Acad. sci. [Paris] Comptes rendus, v. 244, no. 21, p. 2623-2625.

Gummer, W. K., 1943, The system $CaSiO_3-CaAl_2Si_2O_8-NaAlSiO_4$: Jour. Geology, v. 51, no. 8, p. 503-530.

Gurry, R. W., and Darken, L. S., 1950, The composition of $CaO-FeO-Fe_2O_3$ and $MnO-FeO-Fe_2O_3$ melts at several oxygen pressures in the vicinity of 1600°: Am. Chem. Soc. Jour., v. 72, no. 9, p. 3906-3910.

Hansen, W. C., Brownmiller, L. T., and Bogue, R. H., 1928, Studies on the system calcium oxide-alumina-ferric oxide: Am. Chem. Soc. Jour., v. 50, no. 2, p. 396-406.

Harker, R. I., 1958, The system $MgO-CO_2$-A and the effect of inert pressure on certain types of hydrothermal reactions: Am. Jour. Sci., v. 256, p. 128-138.

Harker, R. I., and Hutta, J. J., 1956, The stability of smithsonite: Econ. Geology, v. 51, no. 4, p. 375-381.

Harker, R. I., and Tuttle, O. F., 1955, Studies in the system $CaO-MgO-CO_2$: Am. Jour. Sci., v. 253, p. 209-224, 274-282.

———1956, The lower limit of stability of akermanite ($Ca_2MgSI_2O_7$): Am. Jour. Sci., v. 254, p. 468-478.

Hartmann, H., and Haegermann, H., 1953, Untersuchungen im system $CaO-P_2O_5-Al_2O_3$ und $CaO-P_2O_5-SiO_2-Al_2O_3$: Zement-Kalk-Gips, v. 6, no. 3, p. 81-89.

Hatch, R. A., 1943, Phase equilibrium in the system: $Li_2O \cdot Al_2O_3 \cdot SiO_2$: Am. Mineralogist, v. 28, no. 9-10, p. 471-496.

Hay, R., Howat, D. D., and White, James, 1934, Slag systems: West of Scotland Iron and Steel Inst., v. 41, pt. 6, p. 97-103.

Hay, R., White, James, and McIntosh, A. B., 1935, Slag systems: West of Scotland Iron and Steel Inst., v. 42, pt. 6, p. 99-104.

Hay, R., McIntosh, A. B., Rait, J. R., and White, Jr., 1937, Slag systems: West of Scotland Iron and Steel Inst., v. 44, pt. 6, p. 85-89.

Herold, P. G., and Smothers, W. J., 1954, Solid-state equilibrium relations in the system MgO-Al_2O_3-SiO_2-ZrO_2: Am. Ceramic Soc. Jour., v. 37, no. 8, p. 351-353.

Hill, W. L., Faust, G. T., and Hendricks, S. B., 1943, Polymorphism of phosphoric oxide: Am. Chem. Soc. Jour., v. 65, no. 5, p. 794-802.

Hill, W. L., Faust, G. T., and Reynolds, D. S., 1944, The binary system P_2O_5-$2CaO \cdot P_2O_5$, Part I: Am. Jour. Sci., v. 242, no. 9, p. 457-477.

Hill, V. G., Roy, Rustum, and Osborn, E. F., 1952, The system alumina-gallia-water: Am. Ceramic Soc. Jour., v. 35, no. 6, p. 135-142.

Horn, W. F., and Hummel, F. A., 1955, Notes on the system B_2O_3-SiO_2-P_2O_5, Part I. The BPO_4-SiO_4 join: Soc. Glass Technology, Jour., v. 39, Trans., p. 113-120.

Howarth, J. T., and Turner, W. E. S., 1930, The decomposition of sodium carbonate by heat: Soc. Glass Technology, Jour., v. 14, Trans., p. 394-401.

———1931, The dissociation of lithium carbonate and potassium carbonate: Soc. Glass Technology, Jour., v. 15, Trans., p. 360-364.

Hummel, F. A., and Englert, W. J., 1955, Notes on the system B_2O_3-SiO_2-P_2O_5, Part II. The ternary system: Soc. Glass Technology, Jour., v. 39, Trans., p. 121-127.

Hüttig, G. F., and Frankenstein, W., 1930, Study of oxide hydrates, XIX. The system, magnesium oxide-carbon dioxide: Zeitschr. anorg. allg. Chemie, v. 185, p. 413-416.

Hüttner, K., 1908, Über die Einwirkung der Phosphorsäure auf Kieselsäure und Silikatgläser: Zeitschr. anorg. Chemie, v. 59, no. 2, p. 216-224.

Ingerson, Earl, Morey, G. W., and Tuttle, O. F., 1948, The systems K_2O-ZnO-SiO_2, ZnO-B_2O_3-SiO_2, and Zn_2SiO_4-Zn_2GeO_4: Am. Jour. Sci., v. 246, no. 1, p. 31-40.

Iwasé, Keizô, and Fukusima, Masaji, 1936, Metastable crystallization of $CaTiO_3$, TiO_2, SiO_2, and $CaSiO_3$ in place of CaO-SiO_2-TiO_2 due to supercooling of the latter: Tôhoku Imp. Univ. Sci. Repts., 1st ser. (Honda Anniversary Volume,) p. 454-462.

Iwasé, Keizô, and Nisioka, Usaburô, 1936, The equilibrium diagram of the system, $CaO \cdot TiO_2$-SiO_2-$MnO \cdot TiO_2$: Tôhoku Imp. Univ. Sci. Repts., 1st ser., v. 25, no. 3, p. 504-509.

———1938, The equilibrium diagrams of the three binary systems; (1) $CaO \cdot SiO_2$-TiO_2-$MgO \cdot TiO_2$, (2) $CaO \cdot MgO \cdot 2SiO_2$-$MnO \cdot TiO_2$ and (3) $CaO \cdot SiO_2$-$2CaO \cdot Fe_2O_3$: Tôhoku Imp. Univ. Sci. Repts., 1st ser., v. 26, no. 4, p. 592-601.

Jaeger, F. M., and Germs, H. C., 1921, III. Über die binären Systeme der Sulfate, Chromate, Molybdate, und Wolframate des Bleies: Zeitschr. anorg. u. allg. Chemie, v. 119, no. 2, p. 145-173.

Jaeger, F. M., and Klooster, H. S., 1914, Studiën op het gebied der Silikaatchemie. I. Over de Verbindingen van Lithiumoxyde en Kiezelzuur: Koninkl. Akad. Wetensch., Amsterdam, Verslag, v. 22, p. 900-923.

Jamieson, J. C., 1953, Phase equilibrium in the system calcite-aragonite: Jour. Chem. Physics, v. 21, no. 8, p. 1385-1390.

Jander, Wilhelm, 1928, Reaktionen im festen Zustande bei höheren Temperaturen. III. Mitteilung. Heterogene Gleichgewichte bei Systemen, die mit einer Gasentwicklung verbunden sind: Zeitschr. anorg. u. allg. Chemie, v. 168, no. 2, p. 113-124.

Johnston, John, 1910, The thermal dissociation of calcium carbonate: Am. Chem. Soc. Jour., v. 32, no. 8, p. 938-946.

Kallenberg, S., 1914, Preliminary communication on the system $CaSiO_3$-$MnSiO_3$: Centralb. Mineralogie, Geologie u. Paläontologie, 1914, p. 388-391.

Karandeeff, B., 1910, Über die binärem Systeme des Calciummetasilikats mit Calciumfluorid und Calciumchlorid: Zeitschr. anorg. Chemie, v. 68, no. 3, p. 188-197.

Karkhanavala, M. D., and Hummel, F. A., 1953, Reactions in the system Li_2O-MgO-Al_2O_3-SiO_2, 1, The cordierite-spodumene join: Am. Ceramic Soc. Jour., v. 36, no. 12, p. 393-397.

Keith, M. L., 1954, Phase equilibria in the system MgO-Cr_2O_2-SiO_2: Am. Ceramic Soc. Jour., v. 37, no. 10, p. 490-496.

Keith, M. L., and Schairer, J. F., 1952, The stability field of sapphirine in the system MgO-Al_2O_3-SiO_2: Jour. Geology, v. 60, no. 2, p. 181-186.

Kelley, K. K., 1949, Contributions to the data on theoretical metallurgy. X, High-temperature heat-content, heat-capacity, and entropy data for inorganic compounds: U.S. Bur. Mines Bull. 476.

Kelley, K. K., and Anderson, C. T., 1935, Contributions to the data on theoretical metallurgy, IV. Metal carbonates-correlations and applications of thermodynamic properties: U.S. Bur. Mines Bull. 384.

Kelley, K. K., Southard, J. C., and Anderson, C. T., 1941, Thermodynamic properties of gypsum and its dehydration products: U.S. Bur. Mines Tech. Paper 625.

Kelley, K. K., Todd, S. S., Orr, R. L., King, E. G., and Boonickson, K. R., 1953, Thermodynamic properties of sodium-aluminum and potassium-aluminum silicates: U.S. Bur. Mines Rept. Inv. 4955.

Kendall, James, and Davidson, A. W., 1921, Compound formation and solubility in systems of the type sulfuric acid, Metal sulfate: Am. Chem. Soc. Jour., v. 43, no. 5, p. 979-990.

Klooster, van H. S., 1910a, Über das Verhalten der Metabor-und der Metaphosphorsäure in den Schmelzen ihrer Alkalisalze: Zeitschr. anorg. Chemie, v. 69, no. 2, p. 122-134.

———1910b, Über die binären Systeme: Li_2O-SiO_2, Li_2SiO_3-$ZnSiO_3$, $ZnSiO_3$-$CdSiO_3$, Li_2SiO_3-$LiBO_2$, Na_2SiO_3-$NaBO_2$ und Na_2SiO_3-Na_2WO_4: Zeitschr. anorg. Chemie, v. 69, no. 2, p. 135-157.

Kordes, Ernest, Zofelt, Bernhard, and Proger, Hansjurgen, 1951, Die Mischungslucke im flussigen Zustand zwischen Na-Ca-Silikaten und Na_2SO_4: Zeitschr. anorg. u. allg. Chemie, v. 264, no. 5-6, p. 255-271.

Kracek, F. C., 1930a, The system sodium oxide-silica: Jour. Phys. Chemistry, v. 34, p. 1583-1598.

———1930b, The binary system Li_2O-SiO_2: Jour. Phys. Chemistry, v. 34, p. 2641-2650.

———1932, The ternary system, K_2SiO_3-$NaSiO_3$-SiO_2: Jour. Phys. Chemistry, v. 36, p. 2529-2542.

———1933, Studies on alkali silicates: Carnegie Inst. Washington Year Book 32, Ann. Rept. of the Director, Geophysical Lab., p. 61-65.

———1939a, Phase equilibrium relations in the system, Na_2SiO_3-Li_2SiO_3: Am. Chem. Soc. Jour., v. 61, no. 8, p. 2157-2161.

———1939b, Phase equilibrium relations in the system, Na_2SiO_3-Li_2SiO_3-SiO_2: Am. Chem. Soc. Jour., v. 61, no. 10, p. 2863-2877.

Kracek, F. C., Bowen, N. L., and Morey, G. W., 1937, Equilibrium relations and factors influencing their determination in the system K_2SiO_3-SiO_3: Jour. Phys. Chemistry, v. 41, no. 9, p. 1183-1193.

Kracek, F. C., Morey, G. W., and England, J. L., 1953, Polymorphism of sodium disilicate, $Na_2Si_2O_5$: Carnegie Inst. Washington Year Book 52, Ann. Rept. of the Director, Geophysical Lab., p. 58-60.

Kracek, F. C., Morey, G. W., and Merwin, H. E., 1938, The system water-boron oxide: Am. Jour. Sci., 5th ser., v. 35A, p. 143-171.

Kracek, F. C., Neuvonen, K. J., and Burley, Gordon, 1951, Thermochemistry of mineral substances, 1, A thermodynamic study of the stability of jadeite: Washington Acad. Sci. Jour., v. 41, no. 12, p. 373-383.

Krakau, K. A., Mukhin, E. J., and Heinrich, M. S., 1937, Equilibrium diagram of the ternary system Na_2SiO_3-$PbSiO_3$-SiO_2: Acad. sci. U.R.S.S. Comptes rendus, v. 14, no. 5, p. 281-285.

Krings, W., and Schackmann, H., 1935, Die Sauerstoffdrucke flüssiger Eisenoxyd-Eisenoxydulschmelzen: Zeitschr. Electrochemie, v. 41, no. 7b, p. 479-487.

Krishna Murthy, M., and Hummel, F. A., 1954, Phase equilibria in the system lithium metasilicate-β-eucryptite: Am. Ceramic Soc. Jour., v. 37, no. 1, p. 14-17.

———1955, Phase equilibria in the system lithium metasilicate-forsterite-silica: Am. Ceramic Soc. Jour., v. 38, no. 2, p. 55-63.

Kröger, Von C., Illner, K. W., and Graeser, W., 1943, Über die Systeme Alkalloxyd-CaO-Al_2O_3-SiO_2. XI, Die Reaktionsdrucke im System K_2O-CaO-SiO_2CO_2: Zeitschr. anorg. u. allg. Chemie, v. 251, no. 3, p. 270-284.

Krustinsons, J., 1932, Die Dissoziation des Manganspats und des Mangancarbonats: Zeitschr. Elektrochemie, v. 38, no. 10, p. 780-783.

———1933, Die thermische Dissoziation des normalen Mangancarbonats und Cobaltcarbonats: Zeitschr. Elektrochemie: v. 39, no. 12, p. 936-939.

Lambertson, W. A., and Mueller, M. H., 1953a, Uranium oxide phase equilibrium systems, 1, $UO_2Al_2O_3$: Am. Ceramic Soc. Jour., v. 36, no. 10, p. 329-331.

———1953b, Uranium oxide phase equilibrium system II, UO_2-MgO: Am. Ceramic Soc. Jour., v. 36, no. 10, p. 332-334.

———1953c, Uranium oxide phase equilibrium system III, UO_2-ZrO_2: Am. Ceramic Soc. Jour., v. 36, no. 11, p. 365-368.

Lambertson, W. A., Mueller, M. H., and Gunzel, F. H., Jr., 1953, Uranium oxide phase equilibrium systems, IV, UO_2-ThO_2: Am. Ceramic Jour., v. 36, no. 12, p. 397-399.

Lander, J. J., 1949, Polymorphism and anion rotational disorder in the alkaline earth carbonates: Jour. Chem. Physics, v. 17, no. 10, p. 892-901.

———1951a, Experimental heat contents of SrO, BaO, CaO, $BaCO_3$ and $SrCO_3$ at high temperatures, dissociation pressures of $BaCO_3$ and $SrCO_3$: Am. Chem. Soc. Jour., v. 73, no. 12, p. 5794-5797.

———1951b, The phase system BaO-$BaCO_3$: Am. Chem. Soc. Jour., v. 73, no. 12, p. 5893-5894.

Lang, S. M., Fillmore, C. L., and Maxwell, L. H., 1952, The system beryllia-alumina-titania, phase relations and general physical properties of three-component porcelains: [U.S.] Natl. Bur. Standards Jour. Research, v. 48, no. 4, p. 298-312.

Lang, S. M., Maxwell, L. H., and Geller, R. F., 1949, Some physical properties of porcelains in the systems magnesia-beryllia-zirconia and magnesia-beryllia-thoria and their phase relations: [U.S.] Natl. Bur. Standards Jour. Research, v. 43, no. 5, p. 429-447.

Lang, S. M., Roth, R. S., and Fillmore, C. L., 1954, Some properties of porcelains and phase relations in the ternary systems of beryllia and zirconia with titania, ceria, and chromia: [U.S.] Natl. Bur. Standards Jour. Research, v. 53, no. 4, p. 201-210.

Langenberg, F. C., and Chipman, John, 1956, Determination of 1600° and 1700°C liquidus lines in $CaO \cdot 2Al_2O_3$ and Al_2O_3 stability fields of the system CaO-Al_2O_3-SiO_2: Am. Ceramic Soc. Jour., v. 39, no. 12, p. 432-433.

Lea, F. M., and Parker, T. W., 1934, Investigations on a portion of the quaternary system $CaO-Al_2O_3-SiO_2-Fe_2O_3$. The quarternary system $CaO-2CaO\cdot SiO_2-5CaO\cdot 3Al_2O_3-4CaO\cdot Al_2O_3\cdot Fe_2O_3$: Royal Soc. [London] Philos. Trans., ser. A, v. 234, p. 1-41.

Le Chatelier, H., 1887, Sur la determination de quelques points de fusion et de decomposition aux temperatures élevées: Soc. chim. France Bull., 2nd ser., v. 47, p. 300.

Levin, E. M., and Cleek, G. W., 1958, Shape of liquid immiscibility volume in the system barium oxide-boric oxide-silica: Am. Ceramic Soc. Jour., v. 41, no. 5, p. 175-179.

Levin, E. M., and Ugrinic, G. M., 1953, The system barium oxide-boric oxide-silica: [U.S.] Natl. Bur. Standards Jour. Research, v. 51, no. 1, p. 37-56.

MacDonald, G. J. F., 1956, Experimental determination of calcite-aragonite equilibrium relations at elevated temperatures and pressures: Am. Mineralogist, v. 41, no. 9 and 10, p. 744-756.

McIntosh, A. B., Rait, J. R., and Hay, R., 1937, The binary system, $FeO-Al_2O_3$: Glasgow, Scotland, Royal Tech. College Jour., v.4, pt. 1, p. 72-76.

Mackenzie, W. S., 1957, The crystalline modifications of $NaAlSi_3O_8$: Am. Jour. Sci., v. 255, no. 7, p. 481-516.

McMurdie, H. F., 1937, Studies on a portion of the system: $CaO-Al_2O_3-Fe_2O_3$: [U.S.] Natl. Bur. Standards Jour. Research, v. 18, no. 4, p. 475-484.

McMurdie, H. F., and Insley, H., 1936, Studies on the quaternary system $CaO-MgO-2CaO\cdot SiO_2-5CaO\cdot 3Al_2O_3$: [U. S.] Natl. Bur. Standards Jour. Research, v. 16, no. 5, p. 467-474.

McTaggart, G. D., and Andrews, A. I., 1957, Immiscibility area in the system $TiO_2ZrO_2-SiO_2$: Am. Ceramic Soc. Jour., v. 40, no. 5, p. 167-170.

Maddocks, W. R., 1935, The ternary system $FeO-MnO-SiO_2$: London, Iron and Steel Inst., Carnegie Scholarship Mem., v. 24, p. 51-68.

Maier, C. G., 1929, Oxide cells of cadmium, copper, tin and lead: Am. Chem. Soc. Jour., v. 51, no. 1, p. 194-207.

Marc, R., and Simek, A., 1913, Über die thermische Dissoziation des magnesiumkarbonats: Zeitschr. anorg. Chemie, v. 82, no. 1, p. 17-49.

Marchal, Germaine, 1923, Sur la dissociation du sulfate d' argent: Acad. sci. [Paris] Comptus rendus, v. 176, p. 299-301.

———1925, Recherches sur la decomposition des sulfates métalliques par la chaleur: Jour. chimie phys., v. 22, no. 5, p. 325-348.

Martin, Erich, and Vogel, Rudolf, 1932, Das System Eisenoxydul-Eisenoxyduloxyd: Archiv Eisenhüttenw., v. 6, no. 3, p. 109-111.

Mason, Brian, 1944, The system $Fe_2O_3-Mn_2O_3$, Some comments on the names bixbyite, sitaparite, and partridgeite: Am. Mineralogist, v. 29, no. 1 and 2, p. 66-69.

Massazza, Franco, 1955, Ricerche sui sisteme $SrO-SiO_2$ e $SrO-SiO_2-CaO$: La Chimica e L'Industria, v. 37, no. 12, p. 939-943.

Massazza, Franco, and Sirchia, Efisia, 1958, Il sistema $MgO-SiO_2-TiO_2$, Nota II - Gli equilibri allo stato solido e alla fusione: La Chimicae L'Industria, v. 40, no. 6, p. 460-467.

Mazzetti, C., and Carli, F., 1926, Borati anidri di litio, cadmio, piombo, manganese: Gazz. chim. italiana, v. 56, no. 1, p. 19-28.

Melent'ev, B. N., and Ol'Shanskiy, 1952, Ravnovesie nesmeshivayushchikhsya zhidkostey v sisteme $NaO-Al_2O_3-SiO_2-Ca_3(PO_4)_2$: Akad. Nauk SSSR, Doklady, v. 86, no. 6, p. 1125-1128.

Menzel, Heinrich, 1922, Über Dissoziations - und Hydrolysengleichgewichte in Lösungen kohlensäuer und borsaurer Salze: Zeitschr. phys. Chemie, v. 100, p. 276-315.

Menzel, Heinrich, and Brückner, Arndt, 1930, Studien an kohlensäuren Magnesiumsalzen. I. Basische Magnesiumcarbonate: Zeitschr. Elektrochemie, v. 36, no. 2, p. 63-87.

Menzel, Heinrich, Brückner, Arndt, and Schulz, H., 1930, Studien an kohlensäuren Magnesiumsalzen. II, Normales Magnesiumcarbonat: Zeitschr. Elektrochemie, v. 36, no. 3, p. 188-196.

Miyashiro, Akiho, 1957, Cordierite-indialite relations: Am. Jour. Sci., v. 255, no. 1, p. 43-62.

Morey, G. W., 1930, The devitrification of soda-lime-silica glasses: Am. Ceramic Soc. Jour., v. 13, no. 10, p. 683-713.

——— 1932, The effect of boric oxide on the devitrification of the soda-lime-silica glasses. The quaternary system Na_2O-CaO-B_2O_3-SiO_2: Am. Ceramic Soc. Jour., v. 15, no. 9, p. 457-475.

——— 1951, The ternary system Na_2O-B_2O_3-SiO_2: Soc. Glass Technology Jour., v. 35, Trans. p. 270-283.

——— 1952, The system sodium metaphosphate-calcium metaphosphate: Am. Chem. Soc. Jour., v. 74, no. 22, p. 5783-5784.

Morey, G. W., and Bowen, N. L., 1925, The ternary system sodium metasilicate-calcium metasilicate-silica: Soc. Glass Technology, Jour., v. 9, Trans., p. 226-262.

Morey, G. W., and Ingerson, Earl, 1937, The melting of danburite. A study of liquid immiscibility in the system, CaO-B_2O_3-SiO_2: Am. Mineralogist, v. 22, no. 1, p. 37-47.

——— 1944, The binary system $NaPO_3$-$Na_4P_2O_7$: Am. Jour. Sci., v. 242, no. 1, p. 1-6.

Morey, G. W., Kracek, F. C., and Bowen, N. L., 1930, The ternary system K_2O-CaO-SiO_2: Soc. Glass Technology, Jour., v. 14, Trans., p. 149-187.

Morey, G. W., and Merwin, H. E., 1936, Phase equilibrium relationships in the binary system, sodium oxide-boric oxide, with some measurements of the optical properties of the glasses: Am. Chem. Soc. Jour., v. 58, no. 11, p. 2248-2254.

Morgan, R. A., and Hummel, F. A., 1949, Reactions of BeO and SiO_2; synthesis and decomposition of phenacite: Am. Ceramic Soc. Jour., v. 32, no. 8, p. 250-255.

Muan, Arnulf, 1955, Phase equilibria in the system FeO-Fe_2O_3-SiO_2: Am. Inst. Mining Metall. Engineers Trans., v. 203, p. 965-976.

——— 1957a, Phase equilibria at liquidus temperatures in the system iron oxide-Al_2O_3-SiO_2 in air atmosphere: Am. Ceramic Soc. Jour., v. 40, no. 4, p. 121-133.

——— 1957b, Phase equilibrium relationships at liquidus temperatures in the system FeO-Fe_2O_3-Al_2O_3-SiO_2: Am. Ceramic Soc. Jour., v. 40, no. 12, p. 420-431.

——— 1958a, On the stability of the phase $Fe_2O_3 \cdot Al_2O_3$: Am. Jour. Sci., v. 256, no. 6, p. 413-422.

——— 1958b, Reactions between iron oxides and alumina-silica refractories: Am. Ceramic Soc. Jour., v. 41, no. 8, p. 275-286.

——— 1958c, Phase equilibria at high temperatures in iron silicate systems: Am. Ceramic Soc. Bull., v. 37, p. 81-84.

——— 1958d, Phase equilibria at high temperatures in oxide systems involving changes in oxidation states: Am. Jour. Sci., v. 256, no. 3, p. 171-207.

——— 1959, Phase equilibria in the system manganese oxide-SiO_2 in air: Am. Jour. Sci., v. 257, no. 4, p. 297-315.

Muan, Arnulf, and Gee, G. L., 1956, Phase equilibrium studies in the system iron oxide-Al_2O_3 in air and at 1 atm. O_2 pressure: Am. Ceramic Soc. Jour., v. 39, no. 6, p. 207-214.

Muan, Arnulf, and Osborn, E. F., 1951, Fundamental investigation of steel plant refractories problems. I, Phase relations in the system $2CaO \cdot SiO_2$-$CaO \cdot SiO_2$-$2CaO \cdot Al_2O_3 \cdot SiO_2$-FeO: Am. Iron and Steel Inst. Year Book, 1951, p. 325-359.

——— 1956, Phase equilibria at liquidus temperatures in the system MgO-FeO-Fe_2O_3-SiO_2: Am. Ceramic Soc. Jour., v. 39, no. 4, p. 121-140.

Nacken, Richard, 1907, Über die Bildung und Umwandlung von Mischkristallen und Doppelsalzen in den binärem Systemen der dimorphen Sulfate von Lithium, Natrium, Kalium und Silber: Neues Jahrb. Mineralogie, Geologie u. Paläontologie, Beilage-Band, v. 24, no. 1, p. 1-68.

Niggli, Paul, 1916, Gleichgewichte zwischen TiO_2 und CO_2, sowie SiO_2 und CO_2 in Alkali-, Kalk-Alkali und Alkali-Aluminatschmelzen: Zeitschr. anorg. u. allg. Chemie, v. 98, no. 4, p. 241-326.

——— 1919, Untersuchungen an Karbonat-und-Chloridschmelzen: Zeitschr. anorg. u. allg. Chemie, v. 106, no. 2, p. 126-142.

Nisioka, Usaburō, 1935, The equilibrium diagram of the system $CaO \cdot MgO \cdot 2SiO_2$-$CaOTiO_2$: Tōhoku Imp. Univ. Sci. Repts., 1st ser., v. 24, no. 5, p. 714-717.

Nowotny, H., and Funk, R., 1951, Ein Beitrag zum System: Al_2O_3-Fe_2O_3-SiO_2: Radex-Rundschau, 1951, no. 8, p. 334-340.

Oelsen, Willey, and Maetz, Helmut, 1941, Das Verhalten des Flusspates und der Kalziumphosphate gegenüber dem Eisenoxydul im Schmelzfluss und seine metallurgische Bedeutung: Düsseldorf, Germany, Kaiser-Wilhelm-Inst. Eisenforschung, Mitt., v. 23, p. 195-245.

Ol'Shanskiy, Ya. I., 1950, Sisteme FeS-FeO-SiO_3: Akad. Nauk SSSR Doklady, v. 70, no. 2, p. 245-248.

Osborn, E. F., 1942, The system $CaSiO_3$-diopside-anorthite: Am. Jour. Sci., v. 240, no. 11, p. 751-788.

——— 1943, The compound merwinite ($3CaO \cdot MgO \cdot 2SiO_2$) and its stability relations within the system CaO-MgO-SiO_2 (Preliminary report): Am. Ceramic Soc. Jour., v. 26, no. 10, p. 321-332.

——— 1953, Subsolidus reactions in oxide systems in the presence of water at high pressures: Am. Ceramic Soc. Jour., v. 36, no. 5, p. 147-151.

Osborn, E. F., and Schairer, J. F., 1941, The ternary system pseudowollastonite-akermanite-gehlenite: Am. Jour. Sci., v. 239, no. 10, p. 715-763.

Osborn, E. F., and Tait, D. B., 1952, The system diopside-forsterite-anorthite: Am. Jour. Sci., Bowen Volume, p. 413-433.

Paetsch, H. H., and Dietzel, Adolf, 1956, Untersuchungen über das System PbO-SiO_2-P_2O_5: Glastechnische Ber., v. 29, no. 9, p. 345-356.

Pascal, Paul, 1913, Die Elektrometallurgie des Aluminiums. I, Das ternäre System Tonerde-Fluorit-Kryolith: Zeitschr. Elektrochemie, v. 19, no. 16, p. 610-617.

Peretti, E. A., 1957, Thermal decomposition of lead carbonate: Am. Ceramic Soc. Jour., v. 40, no. 5, p. 171-173.

Phillips, Bert, and Muan, Arnulf, 1958, Phase equilibria in the system CaO-iron oxide-SiO_2 in air and at 1 atm. O_2 pressure: Am. Ceramic Soc. Jour., v. 41, no. 11, p. 445-454.

Posnjak, E., and Tunell, G., 1929, The system, cupric oxide-sulphur trioxide-water: Am. Jour. Sci., 5th ser., v. 18, no. 103, p. 1-34.

Prince, A. T., 1943, The system albite-anorthite-sphene: Jour. Geology, v. 51, no. 1, p. 1-16.

——— 1951, Phase equilibrium relationships in a portion of the system MgO-Al_2O_3-$2CaO \cdot SiO_2$: Am. Ceramic Soc., v. 34, no. 2, p. 44-51.

——— 1954, Liquidus relationships on 10 percent MgO plane of the system lime-magnesia-alumina-silica: Am. Ceramic Soc. Jour., v. 37, no. 9, p. 402-408.

Prokopowitz, T. I., and Hummel, F. A., 1956, Reactions in the system Li_2O-MgO-Al_2O_3-SiO_2. II, Phase equilibria in the high-silica region: Am. Ceramic Soc. Jour., v. 39, no. 8, p. 266-278.

Rait, J. R., 1949, Basic refractories: Iron and Steel, v. 22, p. 187-193, 289-293, 493-498, 623-628.

Rankin, G. A., and Merwin, H. E., 1916, The ternary system CaO-Al_2O_3-MgO: Am. Chem. Soc. Jour., v. 38, no. 3, p. 568-588.

——— 1918, The ternary system MgO-Al_2O_3-SiO_2: Am. Jour. Sci., 4th ser., v. 45, no. 268, p. 301-325.

Rankin, G. A., and Wright, F. E., 1915, The ternary system CaO-Al_2O_3-SiO_2, with optical study: Am. Jour. Sci., 4th ser., v. 39, no. 229, p. 1-79.

Rao, M. R., 1957, Melting points and certain phase relations in the system MgO-Fe_2O_3-TiO_2-SiO_2: Jour. Sci. and Indus. Research [India], sec. B, v. 16, p. 444-451.

Rase, D. E., and Roy, Rustum, 1955a, Phase equilibria in the system BaO-TiO_2: Am. Ceramic Soc. Jour., v. 38, no. 3, p. 102-113.

——— 1955b, Phase equilibria in the system $BaTiO_3$-SiO_2: Am. Ceramic Soc. Jour., v. 38, no. 11, p. 389-395.

Rea, R. F., 1938, Temperature measuring cones: Am. Ceramic Soc. Jour., v. 21, no. 3, p. 98-101.

Reisman, Arnold, 1958, Reactions of the group VB pentoxides with alkali oxides and carbonates. IX, A DTA study of alkali metal carbonates: Am. Chem. Soc. Jour., v. 80, no. 14, p. 3558-3561.

——— 1959, Heterogeneous equilibria in the system K_2CO_3-Na_2CO_3: Am. Chem. Soc. Jour., v. 81, no. 4, p. 807-811.

Ricker, R. W., and Osborn, E. F., 1954, Additional phase equilibrium data for the system CaO-MgO-SiO_2: Am. Ceramic Soc. Jour., v. 37, no. 3, p. 133-139.

Rigby, G. R., and Richardson, H. M., 1947, The occurrence of artificial kalsilite and allied potassium aluminum silicates in blast-furnace linings: Mineralog. Mag., v. 28, no. 197, p. 75-89.

Robbins, C. R., and Levin, E. M., 1959, The system magnesium oxide-germanium dioxide: Am. Jour. Sci., v. 257, no. 1, p. 63-70.

Roberts, H. S., and Merwin, H. E., 1931, The system MgO-FeO-Fe_2O_3 in air at one atmosphere: Am. Jour. Sci., 5th ser., v. 21, no. 122, p. 145-157.

Robertson, E. C., Birch, Francis, and MacDonald, G. J. F., 1957, Experimental determination of jadeite stability relations to 25,000 bars: Am. Jour. Sci., v. 255, no. 2, p. 115-137.

Roedder, E. W., 1951a, Low temperature liquid immiscibility in the system K_2O-FeO-Al_2O_3-SiO_2: Am. Mineralogist, v. 36, no. 3 and 4, p. 282-286.

——— 1951b, The system K_2O-MgO-SiO_2: Am. Jour. Sci., v. 249, no. 2 and 3, p. 81-130, 224-248.

——— 1952, A reconnaissance of liquidus relations in the system $K_2O \cdot 2SiO_2$-FeO-SiO_2: Am. Jour. Sci., Bowen Volume, p. 435-456.

Rollet, A. P., 1935, Sur les borates de potassium. Étude du systeme B_2O_3-K_2O: Acad. sci. [Paris] Comptes rendus, v. 200, no. 21, p. 1763-1765.

——— 1936, Sur le polymorphisme du pentaborate de potassium $5B_2O_3 \cdot K_2O$: Acad. sci. [Paris] Comptes rendus, v. 202, no. 22, p. 1863-1865.

Rossini, F. D., Wagman, D. C., Evans, W. H., Levine, S., and Jaffe, I., 1952, Selected values of chemical thermodynamic properties: [U.S.] Nat. Bur. Standards Circ. 500, 1268 p.

Roth, R. S., 1958, Revision of the phase equilibrium diagram of the binary system calcia-titania, showing the compound $Ca_4Ti_3O_{10}$: [U.S.] Natl. Bur. Standards Jour. Research, v. 61, no. 5, p. 437-440.

Roy, D. M., 1954, Hydrothermal synthesis of andalusite: Am. Mineralogist, v. 39, no. 1 and 2, p. 140-143.

——— 1958, Studies in the system CaO-Al_2O_3-SiO_2-H_2O: III, New data on the polymorphism of Ca_2SiO_4 and its stability in the system CaO-SiO_2-H_2O: Am. Ceramic Soc. Jour., v. 41, no. 8, p. 293-299.

Roy, D. M., Roy, Rustum, and Osborn, E. F., 1953, Fluoride model systems. III, The system NaF-BeF_2 and the polymorphism of Na_2BeF_4 and BeF_2: Am. Ceramic Soc. Jour., v. 36, no. 6, p. 185-190.

——— 1954, Fluoride model systems. IV, The systems LiF-BeF_2 and PbF_2-BeF_2: Am. Ceramic Soc. Jour., v. 37, no. 7, p. 300-305.

Roy, Rustum, DeVries, R. C., Rase, D. E., Shafer, M. W., and Osborn, E. F., 1952, Hydrothermal crystal studies: Pennsylvania State Coll., School Mineral Industries 6th Quart. Prog. Rept., Oct. 1, 1952, to Dec. 31, 1952, p. 10-11.

——— 1953, Hydrothermal crystal studies: Pennsylvania State Coll., School of Mineral Industries 8th Quart. Prog. Rept. (2nd Ann. Rept.), Apr. 1, 1953, to June 30, 1953, p. 15-17.

Roy, Rustum, and Osborn, E. F., 1949, The system lithium metasilicate-spodumene-silica: Am. Chem. Soc. Jour., v. 71, no. 6, p. 2086-2095.

Roy, Rustum, Roy, D. M., and Osborn, E. F., 1950, Compositional and stability relationships among the lithium aluminosilicates: eucryptite, spodumene, and petalite: Am. Ceramic Soc. Jour., v. 33, no. 5, p. 152-159.

Royster, P. H., 1949, Treatment of titaniferous iron ores: U.S. Patent 2,471,242, May 24, 1949; See Chem. Abs., v. 43, no. 16, col. 6142h.

Ruff, Otto, Ebert, Fritz, and Loerpabel, Wilhelm, 1932, Beiträge zur Keramik hochfeuerfester Stoffe. V. Die terären Systeme: ZrO_2-ThO_2-CaO, ZrO_2-ThO_2MgO, ZrO_2-BeO-CaO, ZrO_2-BeO-CeO_2: Zeitschr. anorg. u. allg. Chemie, v. 207, no. 3, p. 308-312.

Ruff, Otto, Ebert, Fritz, and Stephan, Edward, 1929, Beiträge zur Keramik hochfeuerfester Stoffe. II, Das System ZrO_2-CaO: Zeitschr. anorg. u. allg. Chemie, v. 180, no. 2, p. 215-224.

Ruff, Otto, Ebert, Fritz, and Woitinek, Hans, 1929, Beiträge zur Keramik hochfeuerfester Stoffe. III, Das System ZrO_2-ThO_2: Zeitschr. anorg. u. allg. Chemie, v. 180, no. 3, p. 252-256.

Russell, A. S., Gitzen, W. H., Newsome, J. W., Ricker, R. W., Stowe, V. W., Stumpf, H. C., Wall, J. R., Wallace, Paul, 1956, Alumina properties: Aluminum Co. of America, Alcoa Research Laboratories Tech. Paper 10 (revised), 65 p.

Sabatier, G., 1957, Chaleurs de transition des forms de basse température aux formes de haute température du quartz, de la tridymite et de la cristobalite: Soc. française minéralogie et cristallographie Bull., v. 80, no. 10-12, p. 444-449.

Sal'dau, I. Ya., and Zhirnova, N. A., 1945, Fusion diagram of the ternary system ZrO_2-MgO-Al_2O_3. The problem of new superrefractory materials: Acad. sci. URSS, Cl. sciences chim., Bull., v. 6, p. 669-671.

Sata, Toshiyuki, 1958, Phase relationship in the system $3CaO \cdot P_2O_5$-$MgO \cdot SiO_2$-SiO_2: Chem. Soc. Japan Bull., v. 31, no. 4, p. 408-412.

Schairer, J. F., 1942, The system CaO-FeO-Al_2O_3-SiO_2. I, Results of quenching experiments on five joins: Am. Ceramic Soc. Jour., v. 25, no. 10, p. 241-274.

——— 1950, The alkali-feldspar join in the system $NaAlSiO_4$-$KAlSiO_4$-SiO_2: Jour. Geology, v. 58, no. 5, p. 512-517.

——— 1954, The system K_2O-MgO-Al_2O_3-SiO_2. I, Results of quenching experiments on four joins in the tetrahedron cordierite-forsterite-leucite-silica and on the join cordierite-mullite-potash feldspar: Am. Ceramic Soc. Jour., v. 37, no. 11, p. 501-533.

Schairer, J. F., 1955, The ternary systems leucite-corundum-spinel and leucite-forsterite-spinel: Am. Ceramic Soc. Jour., v. 38, no. 5, p.153-158.

Schairer, J. F., and Bowen, N. L., 1938, The system, leucite-diopside-silica: Am. Jour. Sci., 5th ser., v. 35A, p. 289-309.

——— 1942, The binary system $CaSiO_3$-diopside and the relations between $CaSiO_3$ and akermanite: Am. Jour. Sci., v. 240, no. 10, p. 725-742.

——— 1947a, The system anorthite-leucite-silica: [Finland] Comm. Géol. Bull., v. 24, Suomen Geologinen Seuran Julkaisuja, no. 20, p. 67-87.

——— 1947b, Melting relations in the systems Na_2O-Al_2O_3-SiO_2 and K_2O-Al_2O_3-SiO_2: Am. Jour. Sci., v. 245, no. 4, p. 193-204.

——— 1955, The system K_2O-Al_2O_3-SiO_2: Am. Jour. Sci., v. 253, no. 12, p. 681-746.

——— 1956, The system Na_2O-Al_2O_3-SiO_2: Am. Jour. Sci., v. 254, no. 3, p. 129-195.

Schairer, J. F., and Osborn, E. F., 1950, The system CaO-MgO-FeO-SiO_2: I, Preliminary data on the join $CaSiO_3$-MgO-FeO: Am. Ceramic Soc. Jour., v. 33, no. 5, p. 160-167.

Schairer, J. F., and Yagi, Kenzo, 1952, The system FeO-Al_2O_3-SiO_2: Am. Jour. Sci., Bowen Volume, p. 471-512.

Schwarz, Robert, 1921, Über die binären Systeme des Lithium-Orthosilikates mit Zirkon-Orthosilikat und Kalzium-Orthosilikat: Zeitschr. anorg. u. allg. Chemie, v. 115, no. 1 and 2, p. 87-99.

——— 1929, Beiträge zur Chemie des Germaniums: Deutsche Chemische Gesell. Ber., v. 62, no. 9, p. 2477-2483.

Schwarz, Robert, and Lewinsohn, Michael, 1930, Beiträge zur Chemie des Germaniums. IV, Mitteil.: Über die Systeme Na_2GeO_3-Na_2SiO_3 und K_2GeO_3-GeO_2: Deutsche Chemische Gesell. Ber., v. 63 B, no. 4, p. 783-787.

Segnit, E. R., 1954, The system CaO-ZnO-SiO_2: Am. Ceramic Soc. Jour., v. 37, no. 6, p. 273-277.

Sheybany, H. A., 1948, De la structure des verres alcalino-silicatés mixtes (suite): Verres et Réfractaires, v. 2, no. 6, p. 363-375.

Smith, J. V., and Tuttle, O. F., 1957, The nepheline-kalsilite system. I, X-ray data for the crystalline phases: Am. Jour. Sci., v. 255, no. 4, p. 282-305.

Smolensky, S., 1912, Schmelzversuche mit Bisilikaten und Titanaten: Zeitschr. anorg. Chemie, v. 73, no. 3, p. 293-303.

Smyth, F. H., and Adams, L. H., 1923, The system, calcium oxide-carbon dioxide: Am. Chem. Soc. Jour., v. 45, no. 5, p. 1167-1184.

Smyth, F. H., and Roberts, H. S., 1920, The system cupric oxide, cuprous oxide, oxygen: Am. Chem. Soc. Jour., v. 42, no. 12, p. 2582-2607.

Snow, R. B., 1943, Equilibrium relationships on the liquidus surface in part of the Mn -Al_2O_3-SiO_2 system: Am. Ceramic Soc. Jour., v. 26, no. 1, p. 11-20.

Sosman, R. B., 1952, Temperature scales and silicate research: Am. Jour. Sci., Bowen Volume, p. 517-528.

Sosman, R. B., and Merwin, H. E., 1916, Preliminary report on the system, lime: ferric oxide: Washington Acad. Sci. Jour., v. 6, no. 15, p. 532-537.

Sowman, H. G., and Andrews, A. I., 1951, A study of the phase relations of ZrO_2-TiO_2 and ZrO_2-TiO_2-SiO_2: Am. Ceramic Soc. Jour., v. 34, no. 10, p. 298-301.

Spencer, L. J., 1942, Barium-felspars (celsian and paracelsian) from Wales: Mineralog. Mag., v. 26, no. 178, p. 231-145.

Spivak, Joseph, 1944, The system $NaAlSiO_4$-$CaSiO_3$-Na_2SiO_3: Jour. Geology, v. 52, no. 1, p. 24-52.

Stimson, H. F., 1949, The International Temperature Scale of 1948: [U.S.] Natl. Bur. Standards Jour. Research, v. 42, no. 3, p. 209-217.

Stone, R. L., 1943, Physical chemistry of firing steatite ceramics: Am. Ceramic Soc. Jour., v. 26, no. 10, p. 333-336, and personal communication.

Stone, P. E., Egan, E. P., and Lehr, J. R., 1956, Phase relationships in the system CaO-Al_2O_3-P_2O_5: Am. Ceramic Soc. Jour., v. 39, no. 3, p. 89-98.

St. Pierre, P. D. S., 1953, The constitution of bone china. Part I. High temperature phase equilibrium studies in the system tricalcium phosphate-alumina-silica: Canada Dept. Mines and Tech. Surveys, Mines Branch Tech. Paper 2, 107 p.

——— 1956, Note on the system CaO-Al_2O_3-P_2O_5: Am. Ceramic Soc. Jour., v. 39, no. 10, p. 361-362.

Stull, D. R., and Sinke, G. C., 1956, Thermodynamic properties of the elements: Am. Chem. Soc., Advances in Chemistry 18, 234 p.

Swayze, M. A., 1946a, A report on studies of - 1. The ternary system CaO-C_5A_3-C_2F, 2. The quaternary system CaO-C_5A_3-C_2F-C_2S, 3. The quaternary system as modified by 5 percent magnesia. Part I, Am. Jour. Sci., v. 244, no. 1, p. 1-30.

——— 1946b, A report on studies of - 1. The ternary system CaO-C_5A_3-C_2F, 2. The quaternary system CaO-C_5A_3-C_2F-C_2S, 3. The quaternary as modified by 5 percent magnesia. Part II, Am. Jour. Sci., v. 244, no. 2, p. 65-94.

Tammann, G., 1925, Über die Glaser als unterkühlte Flüssigkeiten: Glastechnische Ber., v. 3, no. 3, p. 73-87.

Tammann, G., and Oelsen, W., 1930, Die Reaktionen beim Zusammenschmelzen von. Glassätzen: Zeitschr. anorg. u. allg. Chemie, v. 193, no. 3, p. 245-269.

Taylor, W. C., 1938, Phase equilibria studies on mixtures of the compounds $4CaO \cdot Al_2O_3 \cdot Fe_2O_3$-$2CaO \cdot Fe_2O_3$-$K_2O \cdot Al_2O_3$: [U.S.] Natl. Bur. Standards Jour. Research, v. 21, no. 3, p. 315-325.

——— 1942, Further phase-equilibrium studies involving the potash compounds of Portland cement: [U.S.] Natl. Bur. Standards Jour. Research, v. 29, no. 6, p. 437-451.

Thilo, Erich, and Schröder, Hansjürgen, 1951, Über das System NaF-BeF_2 und seine Beziehungen zum System CaO-SiO_2: Zeitschr. phys. Chemie, v. 197, no. 1 and 2, p. 39-62.

Thomas, R. H., 1950, Phase equilibrium in a portion of the ternary system BaO-Al_2O_3-SiO_2: Am. Ceramic Soc. Jour., v. 33, no. 2, p. 35-44.

Tokody, L., 1928, The binary system: Mn_2SiO_4-Ca_2SiO_4: Zeitschr. anorg. u. allg. Chemie, v. 169, p. 51-56.

Toropov, N. A., and Galakhov, F. Ya., 1951, Novye dannye o sisteme Al_2O_3-SiO_2: Akad. Nauk SSSR Doklady, v. 78, no. 2, p. 299-302.

——— 1952, Diagramma sostoyaniya sistemy BaO-Al_2O_3: Akad. Nauk SSSR Doklady, v. 82, no. 1, p. 69-70.

——— 1958, Tverdye rastvory v sisteme Al_2O_3-SiO_2: Akad. Nauk SSSR Izv., Otdelenie Khimicheskikh Nauk, 1958, no. 1, p. 8-11.

Toropov, N. A., Galakhov, F. Ya., and Bondar', I. A., 1954, Diagramma sostoyaniya troynoy sisteme BaO-Al_2O_3-SiO_2: Akad. Nauk SSSR Izv., Otdelenie Khimicheskikh Nauk, 1954, no. 5, p. 753-764.

Toropov, N. A., Galakhov, F. Ya., and Bondar', I. A., 1955, Oblast' dibarievym trisilikatom bariya (sanbornitom): Akad. Nauk SSSR Izv., Otdeleinie Khimicheskikh Nauk, 1955, no. 1, p. 3-8.

Trömel, Gerhard, 1932, Untersuchungen über die Bildung eines halogenfreien Apatits aus basischen Calciumphosphaten: Zeitschr. phys. Chemie, ser. A, v. 158, no. 5 and 6, p. 422-433.

——— 1943, Untersuchungen im Dreistoffsystem $CaO-P_2O_5-SiO_2$ und ihre Bedeutung für die Erzeugung von Thomasschlacken: Stahl und Eisen, v. 63, no. 2, p. 21-30.

Trömel, G. Harkort, H. J., and Hotop, W., 1948, Untersuchungen im System $CaO-P_2O_5-SiO_2$: Zeitschr. anorg. Chemie, v. 256, no. 5-6, p. 253-348.

Trömel, G., Obst, K. H., Konopicky, K., Bauer, H., and Patzak, I., 1957, Untersuchungen im System $SiO_2-Al_2O_3$: Deutsche keramiche Gesell. Ber., v. 34, no. 12, p. 397-402.

Turkdogan, E. T., and Maddocks, W. R., 1952, Phase equilibrium investigation of the $Na_2O-P_2O_5-SiO_2$ ternary system: Iron and Steel Inst. Jour., v. 172, part 1, p. 1-15.

Tuttle, O. F., and Harker, R. I., 1957, Synthesis of spurrite and the reaction wollastonite + calcite $\rightleftharpoons$ spurrite + carbon dioxide: Am. Jour. Sci., v. 255, no. 3, p. 226-234.

Tuttle, O. F., and Smith, J. V., 1953, The system $KAlSiO_4-NaAlSiO_4$: Carnegie Inst. Washington Year Book 52, Ann. Rept. of the Director, Geophysical Lab., p. 53-56.

Van Hook, H. J., and Keith, M. L., 1958, The system $Fe_3O_4-Mn_3O_4$: Am. Mineralogist, v. 43, no. 1-2, p. 69-83.

Vasenin, F. I., 1939, Fazy ravnovesiya sistemy $CaO \cdot Cr_2O_3-CaO \cdot Al_2O_3$: Zhur. Prikladnoy Khimii, v. 12, no. 5, p. 651-654.

Voos, Ernst, 1935, Untersuchung des Schnittes $CaO \cdot SiO_2-MnO \cdot SiO_2$ im ternären System $SiO_2-CaO-MnO$: Zeitschr. anorg. u. allg. Chemie, v. 222, no. 2, p. 201-224.

Wallace, R. C., 1909, Über die binärem System des Natriummetasilicats mit Lithium-, Magnesium-, Calcium-, Strontium- und Barium-Metasilicat; des Lithiummetasilicats mit Kalium-, Magnesium-, Calcium-, Strontium- und Bariummetasilicat; und über das Dreistoff system $Na_2O-Al_2O_3-SiO_2$: Zeitschr. anorg. Chemie, v. 63, no. 1, p. 1-48.

Warshaw, I., and Keith, M. L., 1954, Solid solution and chromium oxide loss in part of the system $MgO-Al_2O_3-Cr_2O_3-SiO_2$: Am. Ceramic Soc. Jour., v. 37, no. 4, p. 161-168.

Wartenberg, H., and Eckhardt, K., 1937, Schmelzdiagramme höchstfeuerfester Oxyde. VIII, (Systeme mit CeO_2): Zeitschr. anorg. u. allg. Chemie, v. 232, no. 2, p. 179-186.

Wartenberg, H., and Gurr, W., 1931, Schmelzdiagramme höchstfeuerfester Oxide. III, Zeitschr. anorg. u. allg. Chemie, v. 196, no. 4, p. 374-383.

Wartenberg, H., and Prophet, E., 1932, Schmelzdiagramme höchstfeuerfester Oxyde. V, Zeitschr. anorg. u. allg. Chemie, v. 208, no. 4, p. 369-379.

Wartenberg, H., and Reusch, H. J., 1932, Schmelzdiagramme höchstfeuerfester Oxyde. IV, Zeitschr. anorg. u. allg. Chemie, v. 207, no. 1, p. 1-20.

Wartenberg, H., Reusch, H. J., and Saron, E., 1937, Schmelzpunktsdiagrame höchstfeuerfester Oxyde. VII, Systeme mit CaO und BeO: Zeitschr. anorg. u. allg. Chemie, v. 230, no. 3, p. 257-276.

Washburn, E. W., and Bunting, E. N., 1934, Note on phase equilibria in the system Na_2O-TiO_2: [U. S.] Natl. Bur. Standards Jour. Research, v. 12, no. 1, p. 239.

Watanabe, Motoo, 1933, On the dissociation pressure of silver carbonate: Tôhoku Imp. Univ. Sci. Repts., 1st ser., v. 22, no. 5, p. 1229-1239.

Welch, J. H., and Gutt, W., 1959, Tricalcium silicate and its stability within the system $CaO-SiO_2$: Am. Ceramic Soc. Jour., v. 42, no. 1, p. 11-15.

Wentrup, H., 1935, Beitrag zum System Eisen-Phosphor-Sauerstoff: Archiv Eisenhuttenw., v. 9, no. 1, p. 57-60.

White, James, 1938, Equilibrium at high temperatures in systems containing iron oxides: Iron and Steel Inst., Carnegie Scholarship Mem., v. 27, p. 1-75.

——— 1943, The physical chemistry of open-hearth slags: Iron and Steel Inst. Jour., v. 148, p. 579-694.

White, James, Howat, D. D., and Hay, R., 1934, The binary system, $MnO-SiO_2$: Glasgow, Scotland, Royal Tech. College Jour., v. 3, pt. 2, p. 231-240.

Whiteley, J. H., and Hallimond, A. F., 1919, The acid hearth and slag: Iron and Steel Inst. Jour., v. 99, p. 199-242.

Wilburn, F. W., 1954, Differential thermal analysis: Soc. Glass Technology, Jour., v. 38, Trans., p. 371-382.

Wilde, W. T., and Rees, W. J., 1943, The ternary system $MgO-Al_2O_3-CrO_3$: British Ceramic Soc. Trans., v. 42, no. 7, p. 123-155.

Winchell, A. N., and Winchell, H., 1951, Descriptions of minerals, pt. II of Elements of optical mineralogy: New York, John Wiley & Sons, 551 p.

Yoder, H. S., 1950, The jadeite problem: Am. Jour. Sci., v. 248, no. 5, p. 312-334.

Yoder, H. S., and Keith, M. L., 1951, Complete substitution of aluminum for silicon. The system $3MnO \cdot Al_2O_3 \cdot 3SiO_2-3Y_2O_3 \cdot 5Al_2O_3$: Am. Mineralogist, v. 36, no. 7 and 8, p. 519-533.

Zambonini, F., 1920, Wolframato e molibdato normali di bismuto, loro relazioni con i corrispondenti composti di piambo: Gazz. chim. italiana, v. 50, pt. 2, no. 3, p. 128-146.

Zhirnova, N. A., 1939, Diagramma plavkosti sistemy ZrO_2-MgO: Zhur. Prikladnoy Khimii, v. 12, no. 9, p. 1278-1286.

U. S. GOVERNMENT PRINTING OFFICE : 1963 O - 690-216